

Title	Surface tension of molten iron measured by oscillating droplet method using electromagnetic levitation : Influence of oxygen adsorption on surface tension
Author(s)	Ozawa, Shumpei; Takahashi, Suguru; Suzuki, Shoji et al.
Citation	Transactions of JWRI. 2010, 39(2), p. 130-132
Version Type	VoR
URL	<a href="https://doi.org/10.18910/10262">https://doi.org/10.18910/10262</a>
rights	
Note	

***Osaka University Knowledge Archive : OUKA***

<https://ir.library.osaka-u.ac.jp/>

Osaka University

# Surface tension of molten iron measured by oscillating droplet method using electromagnetic levitation<sup>†</sup>

—Influence of oxygen adsorption on surface tension—

OZAWA Shumpei\*, TAKAHASHI Suguru\*, SUZUKI Shoji\*\*, SUGAWARA Hiroharu\*\*,  
HIBIYA Taketoshi\*\*\*, and FUKUYAMA Hiroyuki\*\*\*\*

**KEY WORDS:** (Surface tension) (Molten iron) (Oxygen adsorption) (Marangoni convection) (electromagnetic levitation) (Oscillating droplet method) (High temperature melt) (Undercooling)

## 1. Introduction

Surface tension is one of the most important thermophysical properties to understand and optimize in a welding process through numerical simulation because its temperature coefficient is a driving force of Marangoni convection which affects the shape of a weld pool dramatically [1]. An accurate surface tension and its temperature coefficient at high temperature melt are strongly required.


The surface tension of molten metals is considerably influenced by oxygen partial pressure,  $P_{O_2}$ , of the ambient atmosphere because oxygen which acts as surfactant is adsorbed to a melt surface from the atmosphere gas [2]. Thus it is very crucial to consider the effect of  $P_{O_2}$  on surface tension measurement. When  $P_{O_2}$  is low, the surface tension of molten metal generally shows a negative temperature coefficient. In this case the Marangoni convection flows radially outward in a weld pool (**Fig. 1**) [1]. However, the temperature coefficient of surface tension increases with increasing  $P_{O_2}$ . Consequently it turns to a positive value as long as the molten metal is not oxidized under comparatively high  $P_{O_2}$ . In this case, Marangoni convection flows radially inward in a weld pool. Even when  $P_{O_2}$  is high, the temperature coefficient is changed from a positive value to a negative value like a “boomerang shape” at higher temperature because the temperature elevation

induce desorption of oxygen through an adsorption equilibrium mechanism. Although the boomerang shape temperature dependence of surface tension is expected for molten iron, it has not been experimentally confirmed yet because a conventional technique for a surface tension measurement such as the sessile drop method can assure only the measurement at a comparatively low temperature to prevent the contamination of the sample by the measurement device.


In this study the surface tension of molten iron was measured by an oscillating droplet method using electromagnetic levitation (EML). This technique enables us to measure the surface tension of molten metals over a wide temperature range including undercooling condition [3]. This technique can assure the  $P_{O_2}$  control of the measurement atmosphere. The purpose of this study was to measure an accurate surface tension and its temperature coefficient for high temperature molten iron in consideration of oxygen partial pressure dependence at a wide temperature range.

## 2. Experimental procedure

About 800mg of an electrolytic iron (purity: 99.99%) was electromagnetically levitated and then melted under the flow condition (2L/min) of the mixed gas of high purity argon and helium to fix the  $P_{O_2}$  of  $10^{-2}$ Pa. The sample was also melted under flow condition of the Ar/He-5% $H_2$  mixed gas with a moisture content of 2.66 ppm to lower the  $P_{O_2}$  by condensing of the  $H_2O$  formed from the following reaction;



The  $P_{O_2}$  of the inlet gas was confirmed by a zirconia oxygen sensor maintained at 1008K. The oscillation behavior and the temperature of the droplet were observed from the upper side using a high speed video camera and a pyrometer. The temperature of the sample was controlled by changing the flow rate of Ar and He gases.

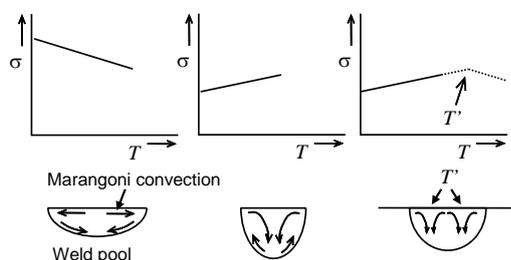

**Fig. 1** relationship between temperature coefficient of surface tension and shape of weld pool

<sup>†</sup> Received on 30 September 2010

\* Department of Aerospace Engineering, Tokyo Metropolitan University, Tokyo, Japan

\*\* Department of Human Mechatronics Systems, Tokyo Metropolitan University, Tokyo, Japan

\*\*\* Graduate School of System Design and Management, Keio

University, Tokyo, Japan

\*\*\*\* Institute of Multidisciplinary Research for Advanced, Tohoku University, Sendai, Japan

Transactions of JWRI is published by Joining and Welding Research Institute, Osaka University, Ibaraki, Osaka 567-0047, Japan

## Surface tension of molten iron measured by oscillating droplet method using electromagnetic levitation

The frequencies of the surface oscillations of the  $m = 0$ ,  $\pm 1$ , and  $\pm 2$  for the  $l = 2$  mode were analyzed from the observed images in consideration of the influence of the two types of droplet rotations, i. e. real rotation and apparent rotation [4]. The surface tension of molten iron was calculated from the Rayleigh equation [5] calibrated by the Cummings and Blackburn equation [6].


### 3. Results and discussions

When Ar/He-5% $H_2$  gas was used for the measurement, the oxygen sensor detected the  $P_{O_2}$  of  $2.0 \times 10^{-23}$  Pa at the inlet. However,  $P_{O_2}$  varies depending on the sample temperature because the equilibrium constant of the reaction (1) shows temperature dependence; the zirconia oxygen sensor can not measure the  $P_{O_2}$  of the gas surrounding the droplet maintained at certain temperature but it detects the  $P_{O_2}$  of an atmosphere introduced into the oxygen sensor operated at 1008K. The  $P_{O_2}$  of the Ar/He-5% $H_2$  gas was evaluated as a function of temperature using the standard Gibbs energy of formation of  $H_2O$ , in which the equilibrium constant of the reaction (1) is calculated from the  $P_{O_2}$  of  $2.0 \times 10^{-23}$  Pa of the inlet gas at 1008K measured by the oxygen sensor.

**Figure 2** shows surface tension of molten iron measured by the oscillating droplet method using EML under the flow condition of mixed gases of Ar/He ( $P_{O_2}$ ) and Ar/He-5% $H_2$  [7]. Uncertainty for the measurement plot was calculated based on the GUM (ISO Guide to the Expression of Uncertainty in Measurement) [8], in which the coverage factor of  $k_p=2$  was selected.

We successfully measured the surface tension of molten iron over a very wide temperature range over 780K including undercooling regions regardless of measurement atmosphere. When the  $P_{O_2}$  of the measurement atmosphere is fixed at  $10^{-2}$  Pa regardless of sample temperature under the flow condition of high purity Ar and He gases, we succeeded in the experimental observation of a “boomerang shape” temperature dependence of surface tension of molten iron involving  $P_{O_2}$  for the first time; the surface tension increases as the sample temperature rises up to about 2150K, and then it decreases above this temperature because the  $P_{O_2}$  becomes less effective due to the temperature dependence of oxygen adsorption equilibrium constant. The pure surface tension of molten iron free from oxygen adsorption can be deduced from the negative temperature coefficient observed above 2150K described as a dotted line.

When the measurement of the surface tension is carried out under the flow condition of mixed gas of Ar/He-5% $H_2$ , the surface tension decreases as the sample temperature rises. However, it does not appear to change with temperature uniformly but to show a kink at around 1850K. Since the variation of the surface tension at this kink is beyond the uncertainty of the measurement, it is not the scattering of the measurement originating from the measurement accuracy. This anomalous temperature dependence of the surface tension can be explained by the temperature dependence of the  $P_{O_2}$  of the mixed gas of Ar/He-5% $H_2$ .

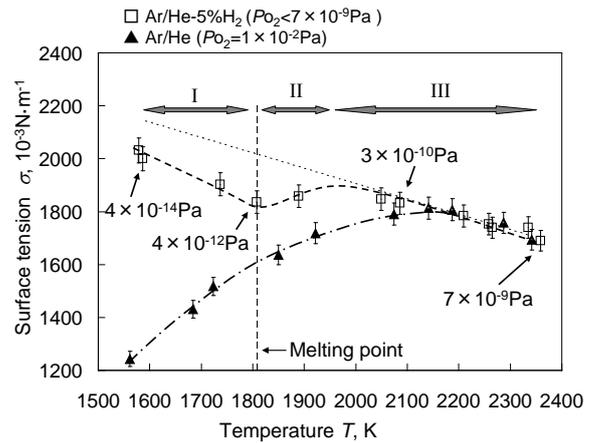

**Fig. 2** surface tension of molten iron

When the sample temperature rises from 1580K to 1810K, the  $P_{O_2}$  of Ar/He-5% $H_2$  gas increased from  $4 \times 10^{-14}$  Pa to  $4 \times 10^{-12}$  Pa due to the chemical equilibrium of reaction (1). Since higher  $P_{O_2}$  normally induces a lower surface tension of molten metal due to oxygen adsorption at comparatively low temperature, surface tension becomes lower than that of the pure value as shown at the region I. What has to be noted is that the temperature elevation induces not only the increase of the  $P_{O_2}$  but also desorption of oxygen due to the temperature dependence of equilibrium constant for oxygen adsorption under  $H_2$ -containing gas atmosphere at the same time. The amount of oxygen adsorption is decided from the competition between these two mechanisms. When the oxygen adsorption becomes small due to high temperature even at high  $P_{O_2}$ , the surface tension would approach the pure value as shown at the region II. When the equilibrium constant of oxygen adsorption becomes zero at high temperature, the surface tension of molten iron measured under the mixed gas of Ar/He-5% $H_2$  shows pure value at the region III.

Thus, the temperature dependence of surface tension of molten metals can not be described as a linear relationship against temperatures as long as pure surface of it does not appear when the  $P_{O_2}$  shows temperature dependence under reducing gas atmosphere such as  $H_2$  and CO. The surface tension of molten metals should be described as functions of temperature and  $P_{O_2}$  as is the case for molten silver [4].

### 4. Summary

The surface tension of molten iron was measured by oscillating droplet method using EML under flow conditions of mixed gases of Ar/He and Ar/He-5% $H_2$ . The surface tension was measured over wide temperature range of about 780K including undercooling condition. The “boomerang shape” temperature dependence of surface tension was experimentally confirmed at the  $P_{O_2}$  of  $10^{-2}$  Pa. The temperature dependence of the surface tension showed kink at around 1850K under the Ar/He-5% $H_2$  atmosphere due to the competition between the temperature dependence of  $P_{O_2}$  and equilibrium constant of oxygen adsorption.

**Acknowledgements**

This study was funded by Japanese Science and Technology (JST) Agency. One of the authors (SO) wishes to thank the support from the Cooperative Research Program of Institute for Joining and Welding Research Institute, Osaka University.

**References**

- [1] C. R. Heiple and J. R. Roper: *Welding J*, 61, (1982), pp. 97-117.
- [2] K. Mukai, Z. Yuan, K. Nogi and T. Hibiya: *ISIJ International* 40, (2000), pp. 148-152.
- [3] S. Ozawa, K. Morohoshi, T. Hibiya and H. Fukuyama: *J Appl. Phys.*, 107 014910, (2010), pp. 1-7.
- [4] S. Ozawa, T. Koda, M. Adachi, K. Morohoshi, M. Watanabe and T. Hibiya: *J. Appl. Phys.*, 106, 034907, (2009), pp. 1-7.
- [5] Lord Rayleigh: *Proceedings of the Royal Society of London* 29, (1879), pp. 71-97.
- [6] D. L. Cummings and D. A. Blackburn: *J. Fluid Mech.*, 224, (1991), pp. 395-416.
- [7] S. Ozawa, S. Suzuki, H. Sugawara, T. Hibiya, H. Fukuyama: *J. Appl. Phys.*, submitted.
- [8] *Guide to the Expression of Uncertainty in Measurement*, ISO, (1995).