

Title	The Determination of Empirical Pair-Potential Functions for CaCl ₂ Crystal and Melt by Molecular Dynamics Calculation
Author(s)	Umesaki, Norimasa; Iwamoto, Nobuya
Citation	Transactions of JWRI. 19(2) P.283-P.287
Issue Date	1990-12
Text Version	publisher
URL	http://hdl.handle.net/11094/10843
DOI	
rights	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/repo/ouka/all/>

The Determination of Empirical Pair-Potential Functions for CaCl₂ Crystal and Melt by Molecular Dynamics Calculation†

Norimasa UMESAKI* and Nobuya IWAMOTO**

KEY WORDS: (Molecular Dynamics) (CaCl₂) (Structure) (Crystal) (Melt)

In recent years, a molecular dynamics (MD) method is increasingly being used to study physical properties of computer-simulated solids and liquids. Unfortunately, most of the calculated systems have been simple ionic liquids such as molten alkali chlorides¹⁾. However, complex ionic liquids such as molten alkaline-earth chlorides are of interest from many points of view. The most remarkable difference in physical properties between alkali chlorides and alkaline-earth chlorides is the volume expansion $\Delta V_m/V_m^s$ (%) on melting. It is well known that alkali chlorides have rather large $\Delta V_m/V_m^s$ values, i.e., LiCl (26.2%), NaCl (25.0%) and KCl (17.3%), whereas alkaline-earth chlorides have much smaller than values, i.e., CaCl₂ (0.9%), SrCl₂ (4.2%) and BaCl₂ (3.5%), as listed in Table 1²⁾. This property of alkaline-earth chlorides may be attributed to the small change of coordination numbers and the minimal structural disordering on melting. However, the structures of molten alkaline-earth chlorides and the mixed systems of them have hardly been studied³⁻⁶⁾ and are not yet clear.

The purpose of this note is, therefore, to present the following suitable pair potential functions of CaCl₂

Table 1 Volume change $\Delta V_m/V_m^s$ (%) of alkali and alkaline earth chlorides of melting²⁾.

Salt	r_c/r_a	m.p. temp. (K)	$\Delta V_m/V_m^s$ (%)
LiCl	0.33	887	26.2
NaCl	0.53	1092	25.0
KCl	0.79	1063	17.3
RbCl	0.82	999	14.3
CsCl	0.91	919	10.5
CaCl ₂	0.55	1045	0.5
SrCl ₂	0.64	1147	2.3
BaCl ₂	0.75	1234	2.3

r_c/r_a : ratio of ionic radii of cation and anion

crystal and melt for the MD calculation:

$$u_{ij} = \frac{z_i z_j e^2}{r_{ij}} + f_0 (b_i + b_j) \exp \left[\frac{(a_i + a_j - r_{ij})}{(b_i + b_j)} \right] \quad (1)$$

where z_i is the formal charge number of ion i (e.g., +2 for Ca²⁺ ion), e the unit charge, r_{ij} the distance between ion i and j , f_0 a force constant arbitrarily taken here to be 1 kcal·mol⁻¹·Å⁻¹, and a_i and b_i are the crystal constant and compressibility of ion i , respectively. The simple expression used for the lattice energy of CaCl₂ crystal and melt described above, Busing form potential⁷⁾, consists of the terms in the Coulomb energy and repulsive energy. For any successful MD calculation, the proper choice of potential parameters is of prime importance. As the potential parameters for Ca²⁺ and Cl⁻ have not been reported yet, we have empirically determined these values by performing MD runs. In order to check the validity of the parameters for Ca²⁺ and Cl⁻, we have performed a MD simulation of CaCl₂ crystal.

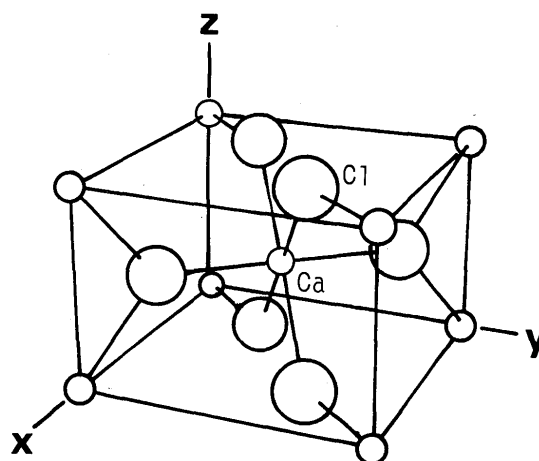


Fig. 1 The orthorhombic unit cell of calcium chloride. The small spheres represent calcium ions and the large ones chloride ions. This is a distorted rutile structure.

† Received on November 2, 1990

* Instructor

** Professor

The structure of CaCl₂ crystal (Space group: P_{nnm}^{7} ; Distorted rutile structure) is shown in Figure 1⁸. The symmetry is orthorhombic with calcium ions at 0, 0, 0, and 1/2, 1/2, 1/2. All chloride ions are equivalent and lie in mirror planes at $x, y, 0; \bar{x}, \bar{y}, 0; \bar{x}, y, 1/2$; and $x, \bar{y}, 1/2$. Thus each calcium ion is coordinated to six chloride ions in an almost perfect octahedral arrangement, and each chloride ion adjoins three calcium ions in nearly planar triangular coordination. This observed calcium chloride structure is a slight distortion of the tetragonal rutile arrangement in which the lattice

$$\Phi_2 = \frac{q_i}{\pi V} \sum_n \left\{ \exp\left(\frac{-\pi^2 |\mathbf{n}'|^2}{\alpha^2}\right) \cdot \frac{1}{|\mathbf{n}'|^2} \cdot [\cos(2\pi \mathbf{n} \cdot \mathbf{r}'_i) \sum_j q_j \cos(2\pi \mathbf{n} \cdot \mathbf{r}'_j) - \sin(2\pi \mathbf{n} \cdot \mathbf{r}'_i) \sum_j q_j \sin(2\pi \mathbf{n} \cdot \mathbf{r}'_j)] \right\} \quad (4)$$

$$\Phi_{3i} = \frac{q_i^2 \alpha}{\sqrt{\pi}} \quad (5)$$

where erf is the usual error function defined by $\text{erf}(x) = (2/\sqrt{\pi}) \int_0^x \exp(-u^2) du$, and \mathbf{n} denotes the reciprocal

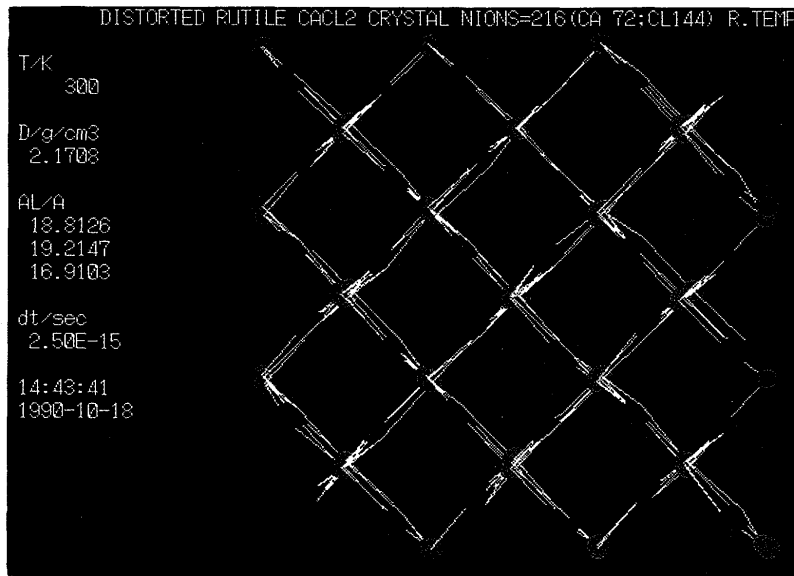


Fig. 2 The structural view of a typical instantaneous configuration of the MD-simulated CaCl₂ crystal at 300 K.

parameters a and b are equal as are the anion parameters x and y .

The potential parameters used in MD calculation of CaCl₂ crystal at room temperature are given in Table 2. The MD calculation assumed an orthorhombic cell as a basic cell. The number of particles within the basic cell was 216 (Ca: 72; Cl: 144). In evaluating the potential energy and force, the Coulombic term was calculated at each time step by the application of the Ewald technique¹⁾ given by

$$\Phi_i = \Phi_{1i} + \Phi_{2i} - \Phi_{3i} \quad (2)$$

$$\Phi_1 = q_i \sum_j q_j \frac{\text{erf}(\alpha |r_{ij}|)}{|r_{ij}|} \quad (3)$$

Table 2 Values for the potential parameters considered in this work.

	W	z	a	b
Ca	40.08	+2	1.414	0.080
Cl	35.453	-1	1.920	0.085

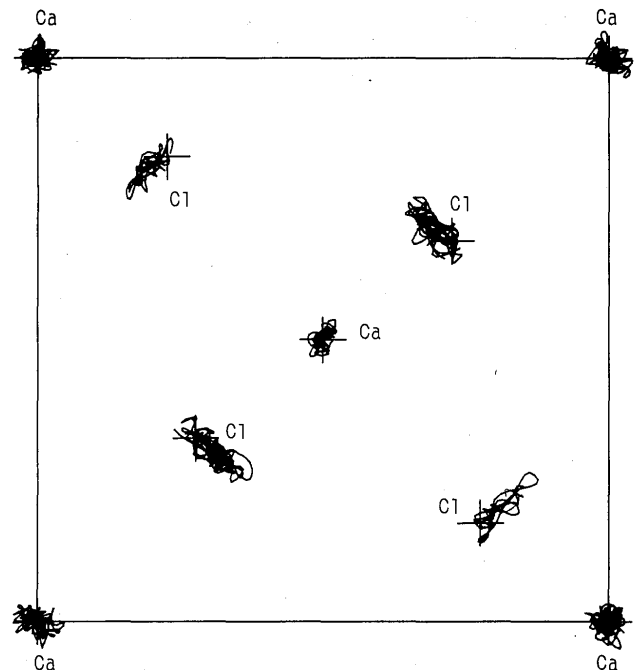


Fig. 3 The X-Y plane of the trajectories of Ca²⁺ and Cl⁻ in the MD-simulated CaCl₂ crystal at 300 K.

lattice position vectors corresponding to the real cell vectors \mathbf{h} . The force on each ion is obtained by differentiating the computed interatomic potential energy for every ion:

$$F_i = -(d\Phi_{ij}/dr_{ij})(dr_{ij}/du_i) \quad (6)$$

where F_i is the force on ion i in the u direction ($u=x, y, z$), Φ_{ij} potential energy between ions i and j , r_{ij} the distance between ions i and j , and du the x, y , or z component of ion i . Once the instantaneous force on each ion has been determined, its position and velocity are calculated for the next time step by using the algorithm of Verlet¹⁾:

$$\mathbf{r}_i(t+\Delta t) = 2\mathbf{r}_i(t) - \mathbf{r}_i(t-\Delta t) + (\Delta t)^2 \mathbf{F}_i(t)/m_i \quad (7)$$

Table 3 Comparison of observed and calculated quantities for calcium chloride crystal.

Parameter	Observation	Calculation	
		M.D.	Lattice Energy ²⁾
a_0 (Å)	6.24 ⁸⁾	6.26	6.310
b_0 (Å)	6.43 ⁸⁾	6.46	6.310
c_0 (Å)	4.20 ⁸⁾	4.26	4.261
u Cl	0.275 ⁸⁾	0.273	0.304
v	0.325 ⁸⁾	0.357	0.304
Distance			
Ca-Cl (Å)	2.70 ⁸⁾	2.76	2.72
	2.76 ⁸⁾	2.76	2.76
Density (g/cm ³)	2.40 ⁷⁾	2.14	
Energy	-538.2 ⁷⁾	-575.2	-537.3

$$\Delta \mathbf{r}_i(t) = \Delta_i \mathbf{r}(t-\Delta t) + (\Delta t)^2 \mathbf{F}_i(t)/m_i \quad (8)$$

$$\mathbf{r}_i(t+\Delta t) = \mathbf{r}_i(t) + \Delta \mathbf{r}_i(t) \quad (6)$$

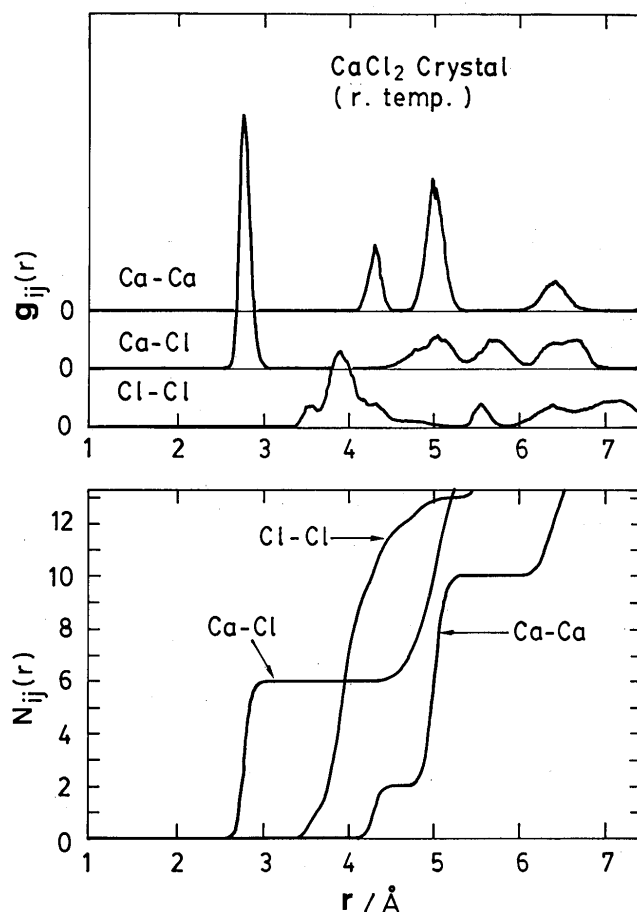


Fig. 4 The pair correlation functions $g_{ij}(r)$ and the distribution of coordination numbers $N_{ij}(r)$ of ionic pairs Cl-Cl, Ca-Cl and Ca-Ca in MD-simulated CaCl₂ crystal at 300 K.

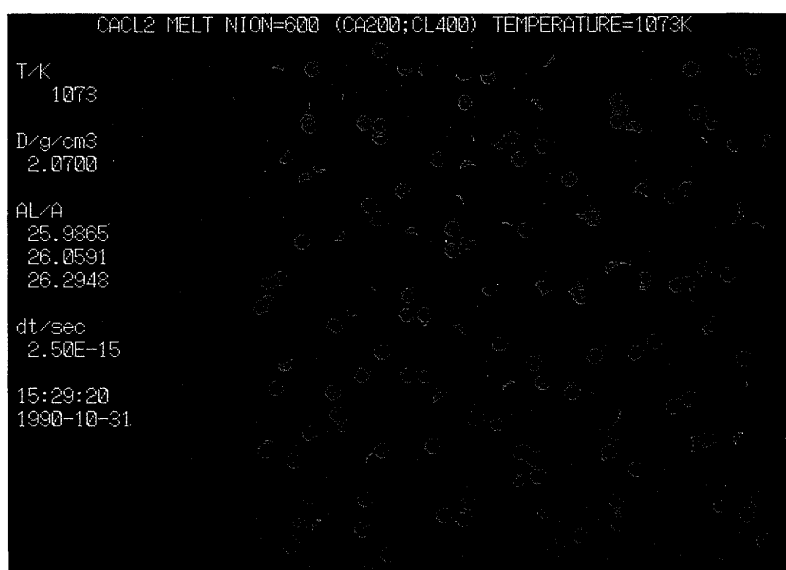


Fig. 5 The structural view of a typical instantaneous configuration of MD-simulated CaCl₂ melt at 1073 K.

where $r(t)$ is the position of an ion at time t . The value of Δt in our MD run was 2.5×10^{-15} sec at room temperature. As shown in **Figures 2 and 3** and **Table 3**, the distorted rutile structure of CaCl_2 crystal was reproduced by our MD calculation. The pair correlation functions $g_{ij}(r)$ and the distribution of the coordination numbers $N_{ij}(r)$ of the ionic pairs Cl-Cl, Ca-Cl and Ca-Ca in CaCl_2 crystal at room temperature are illustrated in **Figure 4**. The lattice parameters a and b change by less than one percent to become equal, and the cation/anion coordinates become equal in a similar way. The calculated nearest-neighbor distances differ by at most 0.04 \AA from those observed⁸⁾. Our MD runs were made on a personal computer systems—NEC PC-9801RA (CPU80386/16MHz+WTK3167) and PC-9801RA21 (CPU80386/20MHz+IIT2C87). For 216 particles, interacting a Coulombic potential, a single time step could be done in about 6~8 seconds.

Figure 5 shows the structural view of a typical instantaneous configuration of molten CaCl_2 at 1073K.

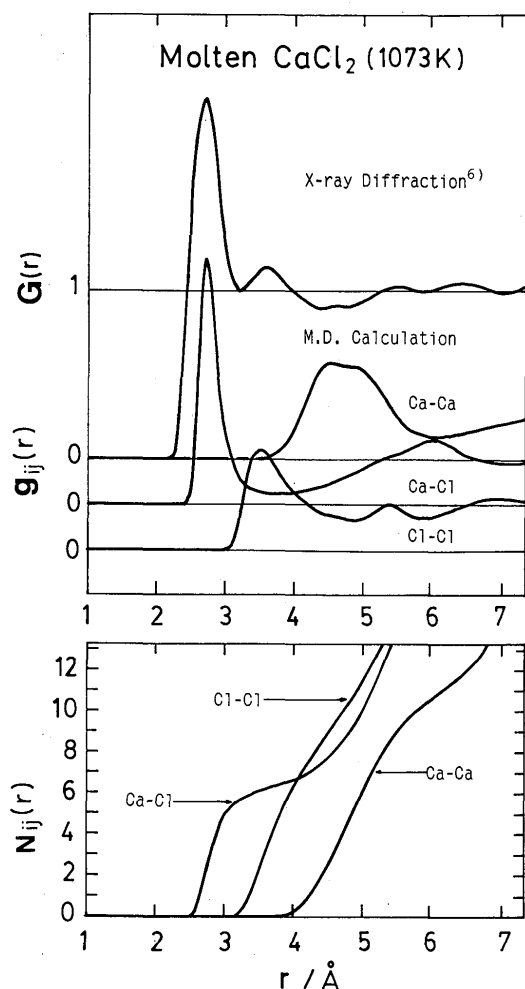


Fig. 6 A comparison of the pair correlation functions $g_{ij}(r)$ and the distribution of coordination numbers $N_{ij}(r)$ obtained from our MD simulation with the total X-ray correlation function $G(r)$ ⁶⁾ for molten CaCl_2 at 1073 K.

The MD calculation assumed a cube as a basic cell. The edge length of the basic cell was calculated from the observed value of density of the molten CaCl_2 at 1073K ($\rho = 2.07 \text{ g/cm}^3$)⁹⁾. The number of particles within the basic cell were 360 (Ca: 120; Cl: 240) and 600 (Ca: 200, Cl: 400), respectively. The pair correlation functions $g_{ij}(r)$ and the distribution of the coordination numbers $N_{ij}(r)$ of the ionic pairs Cl-Cl, Ca-Cl and Ca-Ca in molten CaCl_2 at 1073K are illustrated in **Figure 6** in comparison with the corresponding total correlation function $G(r)$ obtained from our X-ray structural analysis⁶⁾. The calculated coordination number $N_{\text{Ca/Cl}} = 5.6$ is closed to the $N_{\text{Ca/Cl}} = 5.8$ estimated from volume expansion given by

$$\frac{\Delta V_m}{V_m^s} = \frac{(r_{\text{Ca-Cl}}^s)^3}{(r_{\text{Ca-Cl}}^l)^3} \times \frac{N_{\text{Ca-Cl}}^l}{N_{\text{Ca-Cl}}^s} \quad (10)$$

where subscripts s and l mean solid and liquid states at the melting point, respectively. The distances calculated, $r_{\text{Ca-Cl}}$ and $r_{\text{Cl-Cl}}$, and the coordination numbers, $N_{\text{Ca/Cl}}$ and $N_{\text{Cl/Cl}}$, of the nearest-neighbor pairs Ca-Cl and Cl-Cl are close to those found in the crystalline form⁸⁾, which are consistent with the extraordinary small value of $\Delta V_m/V_m^s$ on melting. Since CaCl_2 has a rutile structure, Ca^{2+} cations are centered at slightly distorted CaCl_6 clusters composed of six Cl^- ions with Ca-Cl distance of $2.7 \sim 2.76 \text{ \AA}$. It is, therefore, believed that the distances and the coordination numbers of the nearest-neighbor ionic pairs scarcely change on melting. **Figure 7** shows a comparison between the calculated and observed⁶⁾ interference function curves $S \cdot i(S)$ in the reciprocal lattice

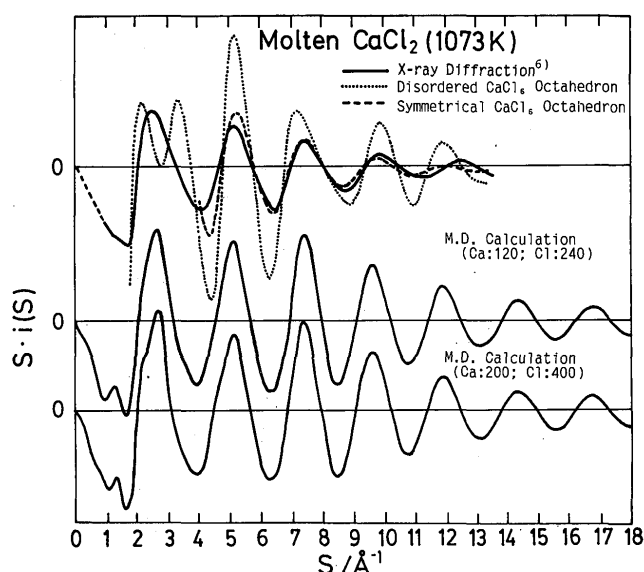


Fig. 7 The X-ray total interference functions $S \cdot i(S)$ of molten CaCl_2 at 1073 K for our MD simulation compared to X-ray experiment⁶⁾.

space. Unfortunately, it is considered that calculated $S \cdot i(S)$ may contain some calculation errors, such as Fourier transformation error caused by small size of the basic cell used, whereas observed $S \cdot i(S)$ may contain some experimental errors, so that no quantitative discussion is possible. However, our MD simulation reveals that the $S \cdot i(S)$ curves calculated are in good agreement with that from X-ray diffraction⁶⁾, as shown in Figure 7.

References

- 1) L.V. Woodcock: Advances in Molten Salt Chemistry Vol. 3, ed. by J. Braunstein, G. Mamantov and G.P. Smith, Plenum Press, 1975, p. 1-74.
- 2) H. Schinke and F. Sauerwald: Z. Anorg. Allg. Chem., **287** (1956) 832.
- 3) F.G. Edwards, R.A. Howe, J.E. Enderby and D.I. Page: J. Phys. C: Solid State Phys., **11** (1978) 1053.
- 4) S. Biggin and J.E. Enderby: J. Phys. C: Solid State Phys., **14** (1981) 3577.
- 5) S. Biggin, M. Gay and J.E. Enderby: J. Phys. C: Solid State Phys., **17** (1984) 977.
- 6) N. Iwamoto, N. Umesaki, T. Asahina and M. Kosaka: High Temp. Sci., **23** (1987) 1.
- 7) W.R. Busing: Trans. Am. Cryst. Assoc., **6** (1970) 57.
- 8) Ralph W.G. Wyckoff: Crystal Structures, Vol. 1, Second Edition, Interscience Publisher, p. 252-253.
- 9) G. Brautigam, H.H. Emons and H. Vogt: Z. Chem., **10** (1970) 344.