

Title	Fundamental Investigation on Electroslag Welding (Report III) : The Effects of CaF <sub>2</sub> Addition to (CaO)-MnO-SiO <sub>2</sub> Fluxes on Inclusion Morphology
Author(s)	Iwamoto, Nobuya; Makino, Yukio; Nose, Jiro et al.
Citation	Transactions of JWRI. 1978, 7(2), p. 161-164
Version Type	VoR
URL	<a href="https://doi.org/10.18910/12014">https://doi.org/10.18910/12014</a>
rights	
Note	

*Osaka University Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

Osaka University

# Fundamental Investigation on Electroslag Welding (Report III) †

## – The Effects of CaF<sub>2</sub> Addition to (CaO)-MnO-SiO<sub>2</sub> Fluxes on Inclusion Morphology –

Nobuya IWAMOTO\*, Yukio MAKINO\*\*, Jiro NOSE\*\*\*,  
Yutaka NAGANAWA\*\*\* and Yoshiaki TSUNAWAKI\*\*\*\*

### Abstract

*The effects of CaF<sub>2</sub> addition to (CaO)-MnO-SiO<sub>2</sub> fluxes on inclusion morphology were investigated with SEM observation and X-ray microanalysis. Inclusion morphology was scarcely changed by the addition of CaF<sub>2</sub> and main inclusions were (Mn, Fe) (S, O), silicate containing sulphur and iron manganosilicate. The existence ratio of oxide to all inclusions decreased by the addition of CaF<sub>2</sub>. However, it was indicated that the existence ratio of main inclusion was more closely related to the composition of parent slag (slag without CaF<sub>2</sub>) rather than the content of CaF<sub>2</sub> added.*

### 1. Introduction

It is well known that many sorts of inclusions are detected in steel and various harmful influences are produced from them. Similar phenomena are shown in weld metal and oxide and sulphide are the most trouble inclusions in the case of using low carbon steel as substrate. When alloy elements such as Cr and Nb are contained in steel, carbide and nitride inclusions are generally formed and these inclusions have various effects aparting from the fact whether or not they have good influences on the properties of weld metal.

Generally, it is considered that the addition of fluoride to slag can lower the oxygen potential in slag. As described in the previous papers<sup>1),2)</sup>, the addition of CaF<sub>2</sub> is effective to lower the oxygen content in weld metal though the effective amount of CaF<sub>2</sub> depends on slag component. In this study, the effects of CaF<sub>2</sub> addition to silicate slag on inclusion morphologies of oxide, oxysulphide and sulphide were investigated with SEM observation and X-ray microanalysis.

### 2. Experimental Procedures

Specimens and their notations used in this study were the same ones used in the previous paper<sup>2)</sup>. The experimental conditions of ESW and the compositions of fluxes, wire and substrate steel were also described in the previous paper<sup>2)</sup>. After cutting off specimen pieces from

weld metal, they were polished by SiC and ZrO<sub>2</sub> abrasives using water or ethylalcohol as coolant. Then, specimens for SEM observation were prepared by deeply etching them with 5% nital. The conditions of SEM observation were as follows:

Voltage and Current : 20kV x 100~110μA,  
Sensitivity in XMA : 100 cps,  
Type of microscope : Hitachi HSM-2B.

### 3. Results and Discussion

As described above, the effects of CaF<sub>2</sub> addition to two kinds of fluxes (MnO-SiO<sub>2</sub> and CaO-MnO-SiO<sub>2</sub>) on inclusion morphology were investigated by SEM observation and X-ray microanalysis. These results are shown in Photos. 1-3. The shape, composition and kind of inclusions were essentially independent upon the addition of CaF<sub>2</sub> and the main inclusions were (Mn, Fe) (S, O), silicate containing sulphur and manganosilicate with iron. Then, SiO<sub>2</sub> (or iron silicate) was also found out as shown in Photo. 4.

Subsequently, the ratio of main inclusions was investigated and the result is shown in Table 1. The result shows that existence ratio of oxide inclusion is lowered by the addition of CaF<sub>2</sub>. This agrees with general consideration in which oxygen potential in slag is lowered by the addition of CaF<sub>2</sub>. However, the existence ratio of oxide inclusions was nearly constant in spite of adding different

† Received on October 14th, 1978.

\* Professor

\*\* Lecturer

\*\*\* Nippon Kokan K.K.

\*\*\*\* Research Instructor





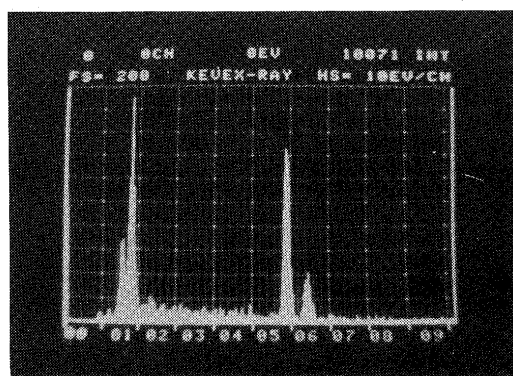


Photo. 1 Typical oxide inclusion in ESW metal using (CaO)-MnO-SiO<sub>2</sub> flux with CaF<sub>2</sub> (x5000)

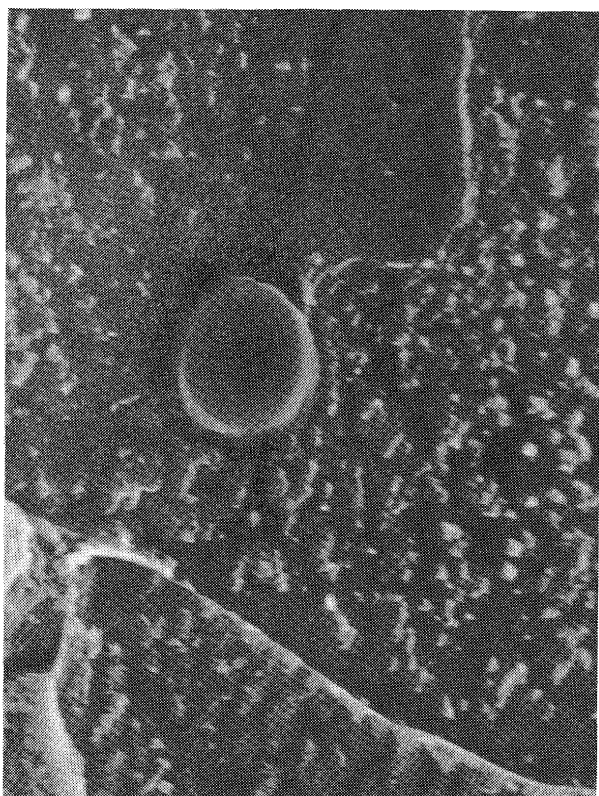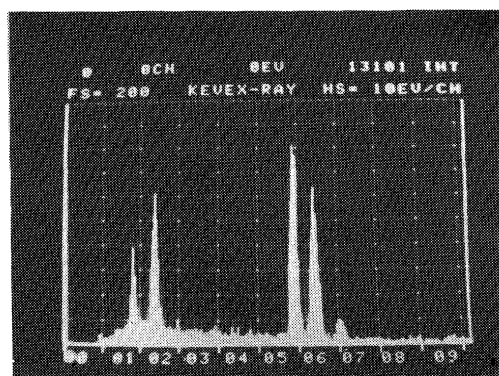
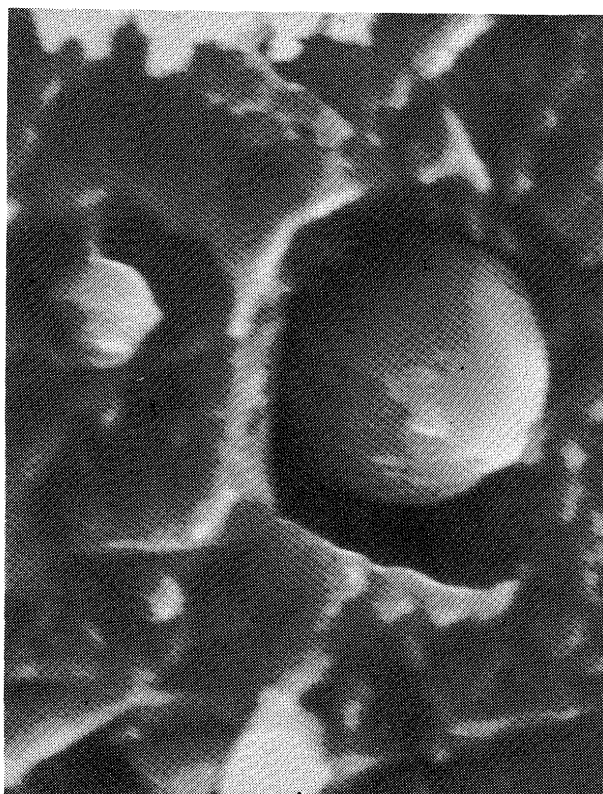


upper region

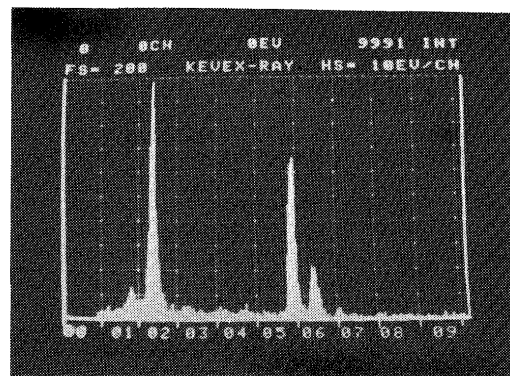


lower region

Photo. 2 Typical duplex inclusion in ESW metal using (CaO)-MnO-SiO<sub>2</sub> flux with CaF<sub>2</sub> [from No. 7 specimen] (x15000)

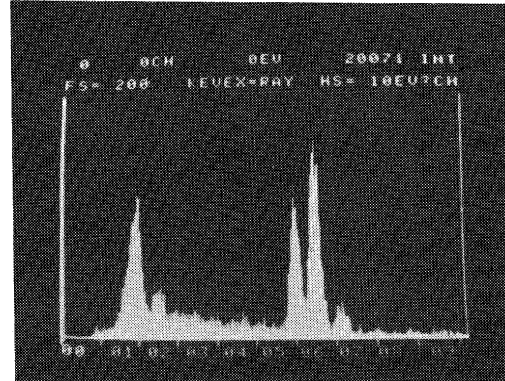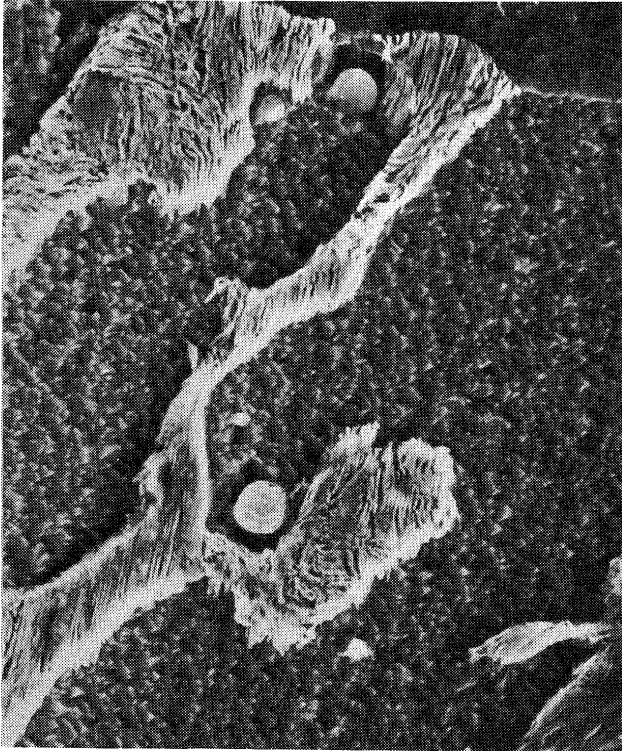

Spectrum from the largest inclusion

**Photo. 3** Typical inclusion of silicate containing sulphur in ESW metal using (CaO)-MnO-SiO<sub>2</sub> flux with CaF<sub>2</sub> (x3000)

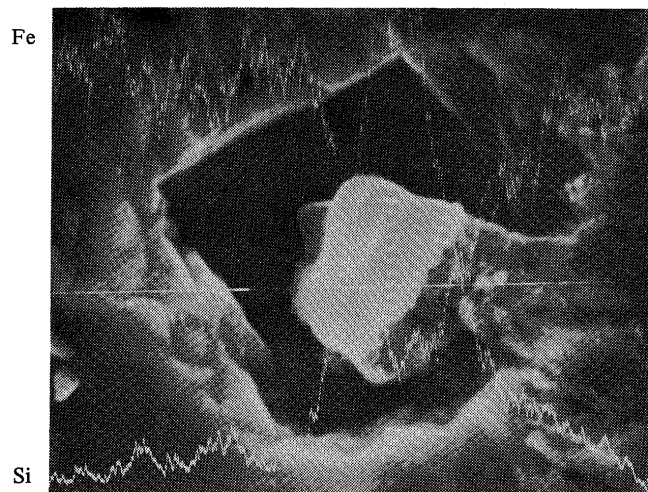

**Photo. 4** The inclusion identified as SiO<sub>2</sub> or iron silicate (x15000)

content of CaF<sub>2</sub>. According to the previous studies<sup>1),3)</sup>, it is indicated that all fluorine ion is not effective to breaking Si-O bond in silicate when fluoride of 30 mol% or over is added to silicate. In other words, fluorine ion changes a certain state to another in the vicinity of 20 mol%. Taking the result into consideration, it is reasonable to interpret that only the addition of initial several percentage CaF<sub>2</sub> is effective to lowering the existence ratio of oxide inclusions. This disagreement in the quantity of CaF<sub>2</sub> is maybe due to the difference of slag

composition between in this study and in the previous study. In addition, physical effects such as the difference of viscosity may superimpose on chemical effects.

Similar tendency was shown in the relation of existence ratio between sulphide and silicate containing sulphur. That is, the dependences of these inclusions on additive amount of CaF<sub>2</sub> were scarcely recognized and the quantity of sulphide increased with increasing CaO content in slag. The result can be related to sulphide

**Table 1** The existence ratio of inclusions detected in ESW metal using (CaO)-MnO-SiO<sub>2</sub> flux with CaF<sub>2</sub>.

Specimen No.	CaF <sub>2</sub> Content	(Mn, Fe) (S, O)	Silicate Containing Sulphur	Silicate
No. 1	0.0%	34%	45%	21%
No. 7	8.3%	38%	50%	12%
No. 8	19.5%	28%	61%	11%
No. 9	31.0%	34%	50%	16%
No. 3	0.0%	29%	54%	17%
No. 10	13.0%	43%	49%	8%
No. 11	16.3%	45%	48%	6%
No. 12	30.9%	36%	54%	11%

capacity  $C_s (= (\%S) \frac{P_{O_2}}{P_{S_2}})$ . The value of  $C_s$  in the slag of

the system MnO-SiO<sub>2</sub> is larger than that in the system CaO-SiO<sub>2</sub><sup>4),5)</sup>. Therefore it is suggested that the formation of sulphide is easier with increasing CaO content in slag. Another interpretation can be performed on the basis of sulphur solubilities in these slags. As is general, it has been considered that to decrease the solubility of sulphide is to increase the activity coefficient. According to Sharma and Richardson<sup>6)</sup>, activity coefficient of sulphide in the slag of the system CaO-SiO<sub>2</sub> is several times as large as that in the system MnO-SiO<sub>2</sub>. Therefore, the amount of sulphide separated from slag becomes larger as the content of CaO in slag increases because the solubility of sulphide in slag decreases with increasing CaO content. The interpretation shows good agreement with the result shown in table 1 but the interpretation is not always reasonable when a large amount of CaF<sub>2</sub> is added to slag.

Thus, it is concluded that inclusion morphology in weld metal essentially depends upon oxygen potential and sulphide solubility of slag used. In order to decide the clear relation between inclusion morphology and slag properties or other conditions, however, further investigations using various fluxes are required because only two series of fluxes were used in this study.

#### 4. Summary

The effects of CaF<sub>2</sub> addition to two manganosilicate fluxes on inclusion morphology were investigated with

SEM observation and X-ray microanalysis. Inclusion morphology was almost similar to that in the case of using manganosilicate fluxes without CaF<sub>2</sub> and it was indicated that main inclusions were (Mn, Fe) (S, O), silicate containing sulphur and manganosilicate with iron. It was also shown that the existence ratio of these inclusions were scarcely dependent upon additive CaF<sub>2</sub> content and were related to the composition of parent slag which is manganosilicate with no CaF<sub>2</sub>. The ratio of oxide inclusions was influenced by the addition of CaF<sub>2</sub> but it can be considered that the addition of several percentage CaF<sub>2</sub> is effective to lowering the quantity of oxide inclusions because the ratio of oxide inclusions was nearly constant in spite of increasing CaF<sub>2</sub> content. However, inclusion morphology in weld metal using various fluxes must be investigated because existence ratios of various inclusions are influenced by chemical properties of slag as well as physical properties such as viscosity. Further, structural investigations on inclusion are necessitated.

#### References

- 1) N. Iwamoto, Y. Makino and N. Umesaki: Trans. JWRI, 5 (1976), P.37.
- 2) N. Iwamoto, J. Nose, Y. Naganawa, Y. Tsunawaki and Y. Makino: Trans. JWRI, 6 (1977), P.23.
- 3) N. Iwamoto, Y. Makino and N. Umesaki: Trans. JWRI, 4 (1975), P.111.
- 4) C. J. Fincham and F. D. Richardson: Proc. Royal Soc., A223 (1954), P.40.
- 5) K. P. Abraham and F. D. Richardson: J. Iron Steel Inst., 196 (1960), P.313.
- 6) R. A. Sharma and F. D. Richardson: Trans. AIME, 233 (1965), P.1586.