

Title	Wetting of Zirconia by Cu-Zr Alloys
Author(s)	Naka, Masaaki
Citation	Transactions of JWRI. 14(1) p193-p.194
Issue Date	1985-07
oaire:version	VoR
URL	<a href="https://hdl.handle.net/11094/12649">https://hdl.handle.net/11094/12649</a>
DOI	
rights	本文データはCiNiiから複製したものである
Note	

*Osaka University Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

Osaka University

# Wetting of Zirconia by Cu-Zr Alloys†

Masaaki NAKA\*, Masanori UEKI\*\*\* and Ikuo OKAMOTO\*\*

KEY WORDS: (Wetting) (Zirconia) (Copper-Zirconium Alloys) (Work of Adhesion) (Interfacial Energy) (Surface Energy) (Joining) (Filler Metals)

Brazing is used extensively in the joining of ceramics with metals. The wetting of ceramics by liquid phase is a major factor in producing an effective bond of ceramics with metals. The wetting behavior between ceramics and molten alloys can be measured in terms of the contact angle between the peripheral surface of a small sessile drop of molten alloy and the horizontal surface of the ceramic substrate as indicated in Fig. 1.

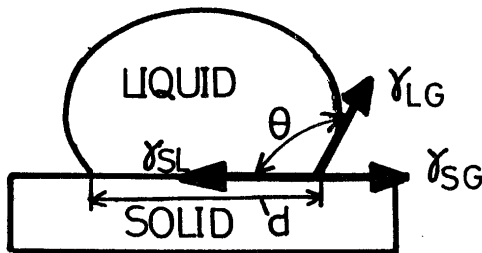


Fig. 1 Schematic of contact angle of liquid drop on ceramics.

This angle,  $\theta$ , is related to the solid and liquid surface energies,  $\gamma_{SG}$  and  $\gamma_{SL}$  and the solid-liquid interfacial energy,  $\gamma_{SL}$  by the Young's equation,

$$\gamma_{SG} = \gamma_{LG} \cos \theta + \gamma_{SL} \tag{1}$$

The zirconia substrate was in the form of 15 mm diameter disk 3 mm thick. The zirconia was polished up to No. 1000 with silicon carbide paper. The composition of zirconia used was 91 wt%  $ZrO_2$ , 5.5 wt% CaO and others and the structure stabilized with CaO was cubic. The nominal compositions of copper-zirconium alloys were 0, 30, 50 and 60 at% zirconium. In sessile drop apparatus as shown in Fig. 2 the alloys were placed on zirconia plate and the contact angles of molten drops were photo-

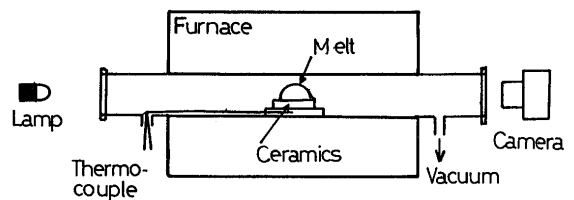


Fig. 2 Sessile drop apparatus.

graphically taken at regular time intervals at 1150°C. The heating rate up to desired temperature was about 85°C/min in  $2 \times 10^{-5}$  torr.

Fig. 3 shows the time dependence of contact angle of copper and copper-zirconium alloys at 1150°C. The contact angles of drops reach the equilibrium values at 60 min. The zirconium content dependence of the equilibrium contact angles of copper-zirconium alloys at 1150°C is shown in Fig. 4. The contact angles of the alloys change from 91° for copper to 45° for  $Cu_{45}Zr_{60}$  alloy. In contrast to the effect of titanium content on the contact angles of Cu-Ti alloys on alumina, the effect of zirconium content is not effective in decreasing the contact angles of alloys on zirconia. The copper-zirconium alloys can be said to be in wetting state because the equilibrium contact angles are below 90°. The work of adhesion,  $W_{ad}$ , which is the work required to separate a unit area of solid-liquid interface into two surfaces is provided by Young-Duprè equation as follows,

$$W_{ad} = \gamma_{LG} (1 + \cos \theta) \tag{2}$$

where  $\gamma_{LG}$  is the liquid surface energy in Fig. 1. For liquid copper  $\gamma_{LG} = 1300 \text{ erg/cm}^2$  (1083°C) and the temperature dependence,  $d\gamma_{LG}/dT = -0.45^{(1)}$ ,  $\gamma_{LG}$  of copper

† Received on April, 30

\* Associate Professor

\*\* Professor

\*\*\* Associate Professor of Kanazawa Institute of Technology

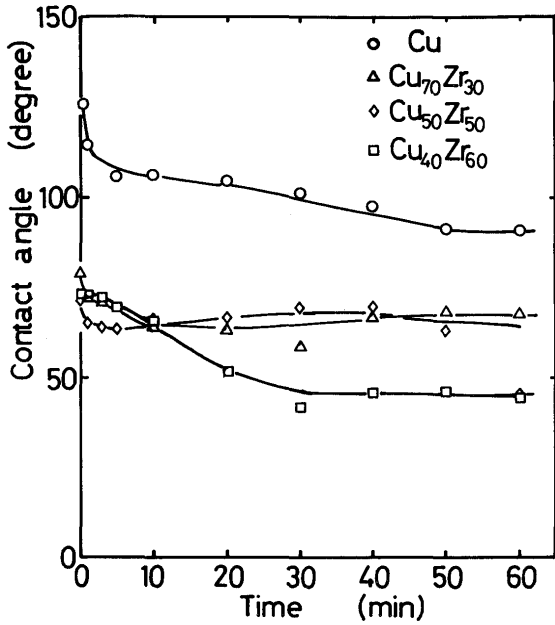


Fig. 3 Time dependence of contact angle of Cu-Zr alloys on ZrO<sub>2</sub> at 1150°C.

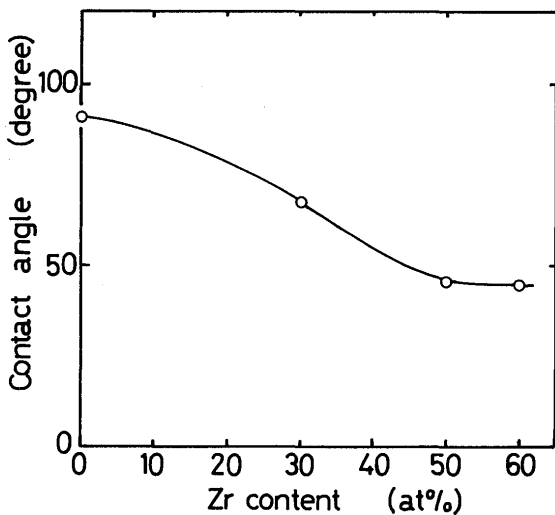


Fig. 4 Zirconium content dependence of contact angle of Cu-Zr alloys at 1150°C for 60 min.

at 1150°C is 1270 erg/cm<sup>2</sup>. From the  $\gamma_{LG}$  (at 1150°C) and observed  $\theta = 91^\circ$  (at 1150°C) of pure copper,  $W_{ad}$  (at 1150°C) of copper against ZrO<sub>2</sub> is 1248 erg/cm<sup>2</sup> (at 1150°C). This value is relatively larger than  $W_{ad}$  (517 erg/cm<sup>2</sup>) of copper against Al<sub>2</sub>O<sub>3</sub> at 1100°C.

$W_{ad}$  is defined by Duprè equation as,

$$W_{ad} = \gamma_{SG} + \gamma_{LG} - \gamma_{SL} \tag{3}$$

Since  $\gamma_{SG}$  (590 erg/cm<sup>2</sup>) of ZrO<sub>2</sub> stabilized with CaO at 1850°C is smaller than  $\gamma_{SG}$  (905 erg/cm<sup>2</sup>) of Al<sub>2</sub>O<sub>3</sub> at 1850°C<sup>2</sup>, the difference of  $W_{ad}$  between Cu/ZrO<sub>2</sub> and Cu/Al<sub>2</sub>O<sub>3</sub> comes from the difference of interface energy  $\gamma_{SL}$  between Cu/ZrO<sub>2</sub> and Cu/Al<sub>2</sub>O<sub>3</sub>. Thus  $\gamma_{SL}$  of Cu/ZrO<sub>2</sub> is smaller than  $\gamma_{SL}$  of Cu/Al<sub>2</sub>O<sub>3</sub> and the interface between Cu and ZrO<sub>2</sub> is stabler than that between Cu and Al<sub>2</sub>O<sub>3</sub>. The decrease in interface between liquid and solid is attributable to the adsorption of special alloying element on the interface or the formation of intermediate phase at the interface. For instance, TiO<sub>x</sub> is formed at the interface between Cu-Ti alloy and Al<sub>2</sub>O<sub>3</sub><sup>3</sup>. The interface between Cu<sub>50</sub>Zr<sub>50</sub> and ZrO<sub>2</sub> was also examined by X-ray diffractometry. Fig. 5 shows the X-ray diffraction pattern

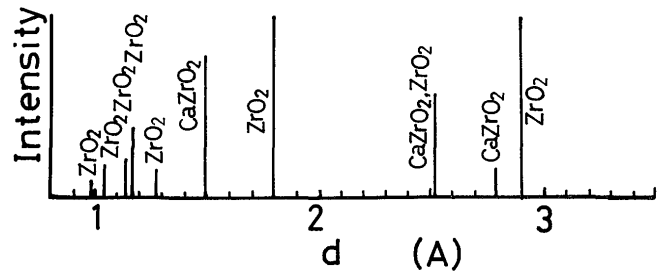


Fig. 5 X-ray diffraction pattern of separated surface of Cu<sub>50</sub>Zr<sub>50</sub> drop after sessile drop testing at 1150°C for 60 min.

of the interface of ZrO<sub>2</sub> side separated from the sessile drop cooled down from 1150°C for 60 min. The intermediate phase of orthorhombic CaZrO<sub>2</sub> is formed. The copper-zirconium alloys are not applicable to the filler of joining ZrO<sub>2</sub> since the difference of thermal expansion between the alloy and the ceramic causes the separation of the drop from the ceramic after cooling down.

References

- 1) L. Murr, Interfacial Phenomena in Metals and Alloys, Addison-Wesley, 1975.
- 2) W.D. Kingery, Ceramic Bulletin, 35 (1956), 108.
- 3) M. Naka and I. Okamoto, Trans. JWRI., 13 (1984), No. 2, 29.