



Title	Novel electrical and optical properties of discotic liquid crystals, substituted phthalocyanine rare-earth metal complexes
Author(s)	Yoshino, K. ; Sonoda, T. ; Lee, S. et al.
Citation	IEEE International Conference on Conduction and Breakdown in Dielectric Liquids, ICDL. 1999, p. 598-601
Version Type	VoR
URL	<a href="https://hdl.handle.net/11094/14069">https://hdl.handle.net/11094/14069</a>
rights	c1999 IEEE. Personal use of this material is permitted. However, permission to reprint/republish this material for advertising or promotional purposes or for creating new collective works for resale or redistribution to servers or lists, or to reuse any copyrighted component of this work in other works must be obtained from the IEEE.
Note	

*The University of Osaka Institutional Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

## Novel Electrical and Optical Properties of Discotic Liquid Crystals, Substituted Phthalocyanine Rare-Earth Metal Complexes

K. Yoshino<sup>1</sup>, T. Sonoda<sup>1</sup>, S. Lee<sup>1,2</sup>, R. Hidayat<sup>1</sup>, H. Nakayama<sup>1</sup>, L. Tong<sup>1,3</sup>,  
A. Fujii<sup>1</sup>, M. Ozaki<sup>1</sup>, K. Ban<sup>4</sup>, K. Nishizawa<sup>4</sup> and K. Ohta<sup>4</sup>

<sup>1</sup> Department of Electronic Engineering, Osaka University, 2-1 Yamada-Oka, Suita, Osaka 565-0871, Japan

<sup>2</sup> Heat Physics Department, Katartal 28, Tashkent 700135, Uzbekistan

<sup>3</sup> Inner Mongolia Nationality Normal College, People's Republic of China

<sup>4</sup> Department of Functional Polymer Science, Shinshu University, Ueda, Nagano 386-8567, Japan

### Abstract

Alkylthio-group-substituted phthalocyanine rare-earth metal sandwich complexes such as bis[octakis(alkylthio)phthalocyanineato]europium(II)  $\{[(C_nS)_8Pc]_2Eu\}$ , bis[octakis(alkylthio)phthalocyaninato]lutetium(III)  $\{[(C_nS)_8Pc]_2Lu\}$ , bis[octakis(alkylthio)phthalocyaninato]terbium(III)  $\{[(C_nS)_8Pc]_2Tb\}$  exhibit discotic liquid crystal phases.

Photoluminescence (PL) peaks of  $[(C_nS)_8Pc]_2Eu$  were observed at around 400-600nm and 730nm in chloroform solution. However, the strong narrow emission of  $Eu^{3+}$  ion was not observed compared with other Eu-complexes. The intensity and the decay time of the PL peak depends strongly on the phase. They have been explained by taking electronic energy schemes of both phthalocyanine ligands and  $Eu^{3+}$  ion into consideration. The role of triplet exciton is also discussed.

In the photoconductivity (PC) spectra of  $[(C_nS)_8Pc]_2Eu$  several peaks were observed corresponding to the absorption peaks. The behavior has been discussed in terms of carrier migration along the stack of phthalocyanine cores in the discotic phase.

Current-voltage characteristics and dielectric properties of these discotic liquid crystals have also been clarified.

### Introduction

Recently discotic liquid crystals which are composed of disc-shaped molecules stacked in columnar structures have attracted much attention, because extremely large hole mobility was observed in the discotic phase [1-5]. Discotic liquid crystals have a potential technological importance due to their semiconducting properties combined with their processability. One-dimensional nature of the columnar structure along which the fast carrier transport takes place, also stimulated much interest from both scientific and practical view

points. It should also be mentioned that by designing the molecular structure of central core parts of discotic liquid crystal various functionalities are also expected.

In this paper, electrical and optical properties of discotic liquid crystals with metal phthalocyanine cores such as  $\{[(C_nS)_8Pc]_2Eu\}$ ,  $\{[(C_nS)_8Pc]_2Lu\}$ ,  $\{[(C_nS)_8Pc]_2Tb\}$  are presented. The possibility of p- and n-type doping of Lutetium bis-phthalocyanine has been demonstrated by M. Maitrot et al. [6]. Here we show for the first time the  $C_{60}$  doping effect in thin film of  $C_{60}$ -doped  $[(C_nS)_8Pc]_2Eu$ .

### Experimental

Molecular structures of alkylthio-group-substituted phthalocyanine rare-earth metal sandwich complexes such as bis[octakis(alkylthio)phthalocyanineato]europium(III), bis[octakis(alkylthio)phthalocyaninato]lutetium(III), bis[octakis(alkylthio)phthalocyaninato]terbium(III) are shown in Fig.1. Synthetic route is also shown in this figure.

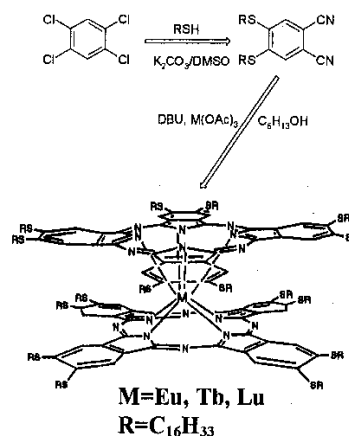


Fig.1 Synthetic route and chemical structure of  $[(C_nS)_8Pc]_2M$ .

Europium(III) acetate tetrahydrate in 1-hexanol was refluxed in the presence of DBU with stirring for 28 hours. A mixture of 5-bisdodecylthiophthalonitrile was prepared by mixing 1-dodecylthiol and 4,5-dichlorophthalonitrile in dry DMSO. Europium (III) acetate tetrahydrate and DBU were added to the mixture. Then the mixture was refluxed for additional 16 hours and the reaction mixture was cooled down. The precipitate was separated by filtration and washed with methanol. The residue was purified by column chromatography and recrystallization twice from ethyl acetate. Detailed preparation and purification procedures and results of analysis were reported separately [7].

Liquid crystal phase of these compounds were optically observed utilizing an optical polarizing microscope equipped with a Mettler FP 82HT hot stage controlled by Mettler FP 90 Central Processor, with which phase transition temperatures

were also evaluated. X-ray diffraction spectra were also studied in solid and discotic liquid crystal phases with Rigaku RINT X-ray diffractometer.

Absorption and PL spectra measurements were carried out utilizing a Hewlett-Packard 8452A diode array spectrophotometer and a Hitachi F-2000 fluorescence spectrophotometer. Time resolved PL was studied utilizing femtosecond laser system. Femtosecond laser pulses were obtained from Ti:Sapphire mode-locked laser (Tsunami, Spectra-Physics) with pulse width of 80 fs and pulse trains of 82 MHz. The frequency is then doubled by a second harmonic generator unit utilizing barium beta borate crystals to obtain laser pulse with wavelength of 390 nm. The time-resolved PL spectra and PL decays were observed using a streak scope camera with temporal resolution of about 15 ps.

Photoconductivity was measured by the conventional method as already reported by the authors [8].

Dielectric constants and its temperature dependence of the sample in a sandwich cell were studied utilizing impedance analyzer (Yokogawa Hewlett Packard 4192A) and temperature controller (Shimaden, FP21).

## Results and discussion

Figure 2 indicates phase transition temperatures of  $[(C_nS)_8Pc]_2Ln$  as a function of the alkylthio chain length ( $n$ ). As evident in this figure, this compound exhibits a discotic liquid crystal phase, Dh phase, in a relatively wide temperature range.




Fig.3 shows the large dielectric permittivities  $\epsilon_{||}$  and  $\epsilon_{\perp}$  in  $[(C_nS)_8Pc]_2Eu$  in the liquid crystalline state measured at various frequencies.

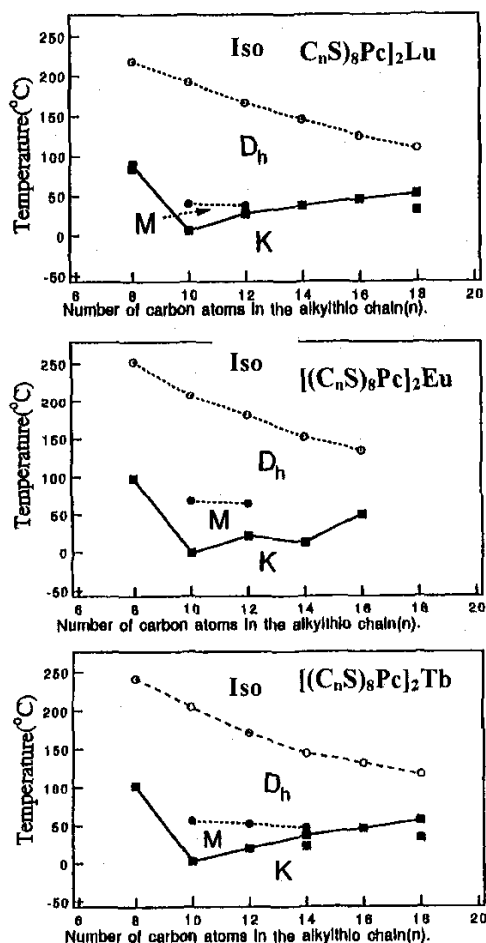


Fig.2 Phase transition temperatures of  $[(C_nS)_8Pc]_2Ln$  as function of the alkylthio chain length ( $n$ ).

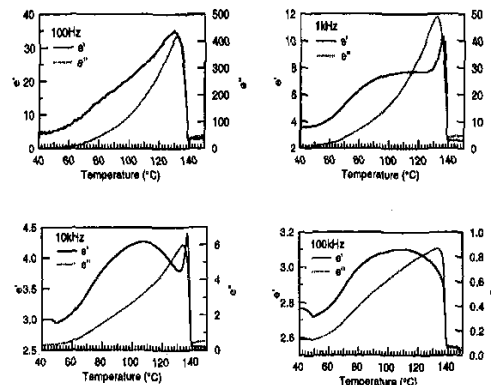


Fig.3 Dielectric permittivities  $\epsilon_{||}$  and  $\epsilon_{\perp}$  in  $[(C_nS)_8Pc]_2Eu$  measured at various frequencies.

Figure 4 shows the optical absorption spectra of  $[(C_nS)_8Pc]_2Eu$  in chloroform solution and a film. In this figure, two sets of absorption bands at 200~400 nm and 600~750 nm are clearly observed which is related to the Soret and Q-band of phthalocyanine. The several absorption peaks of Eu ion in visible range is too weak to be observed in absorption spectrum [9].

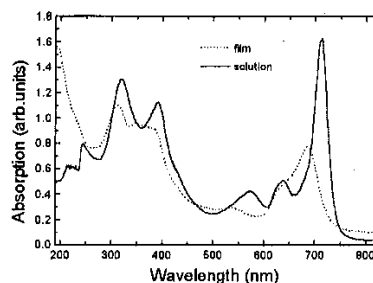


Fig.4 Absorption spectrum of  $[(C_nS)_8Pc]_2Eu$  in solution in chloroform and thin film.

Figure 5 shows PL emission and excitation spectra of  $[(C_nS)_8Pc]_2Eu$  in chloroform solution. PL was weak in comparison of metal free phthalocyanine in solution. However, it should be noted in this figure PL was observed both at around 400~600nm and at around 730nm, which may be related to the Soret and Q-bands of the absorption, respectively. The fine vibronic structure of higher energy emission band was observed in solution at room temperature. Generally in Eu-complex

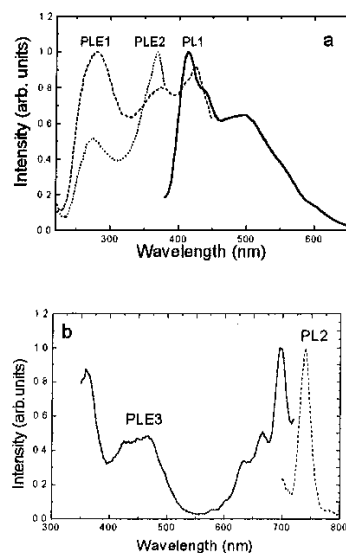


Fig. 5 (a) Photoluminescence emission (PL1) spectrum of  $[(C_nS)_8Pc]_2Eu$  in chloroform solution in visible range and its excitation spectra for  $\lambda_{em}=500nm$  (PLE1) and  $\lambda_{em}=415nm$  (PLE2). (b) PL emission (PL2) in near IR region and its excitation spectra (PLE3,  $\lambda_{em}=700 nm$ ).

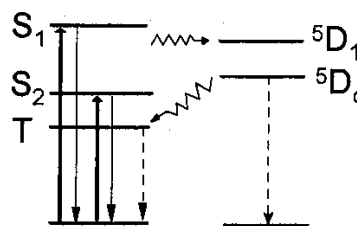


Fig. 6 Energy transfer processes in  $[(C_nS)_8Pc]_2Eu$  (dashed lines represent less probable processes).

narrow line PL is observed at wavelength of about 615 nm.

The weak PL intensity suggests that in  $[(C_nS)_8Pc]_2Eu$  the inter-system crossing from the singlet excited state to the triplet excited state should suppress the fluorescence strongly due to the large spin-orbit coupling in the presence of heavy Eu atom just as the case of Cu-phthalocyanine [10]. In Cu-phthalocyanine the fluorescence was totally suppressed and the phosphorescence was observed at around  $1.12\mu m$ . Indeed, the existence of the large spin-orbit coupling in bis(phthalocyaninato) lanthanide compounds has been shown experimentally [11]. This interpretation is reasonable if we take the energy levels of phthalocyanine  $\pi$ -electron system and f-electron states of Eu(III) into consideration (Fig.6). Direct excitation of  $Eu^{3+}$  ion has very low probability. Singlet energy transfer is also not significant [12]. Usually the narrow line emission of  $Eu^{3+}$  ion occurs by energy transfer through the triplet state of organic unit. However, in the case of  $[(C_nS)_8Pc]_2Eu$  the lowest triplet state of  $(C_nS)_8Pc$  is lower than the resonance levels of  $Eu^{3+}$  ion. Therefore, the triplet energy transfer to  $Eu^{3+}$  ion is impossible and the line emission of  $Eu^{3+}$  ion can not be observed. The experimental observation supports this mechanism. We should mention here that the photoluminescence of  $[(C_nS)_8Pc]_2Lu$  is much higher than  $[(C_nS)_8Pc]_2Eu$  since a 4f shell of Lu ion is filled [13]. A more detailed analysis of PL spectra will be published separately. The phosphorescence of  $[(C_nS)_8Pc]_2Eu$  is under investigation.

Figure 7 shows the decay of PL in this compound observed by the time-resolved PL spectroscopy at room temperature. It should be mentioned that the photoexcitation occurs in the highest absorption band (Soret band). The broad weak photoluminescence band was observed in dilute solution. The PL was completely suppressed in the film. In solution the decay curve can be fitted by double exponent with  $t_1=0.73 ns$  and  $t_2=2.2 ns$ .

Fig. 8 shows the strong photoluminescence quenching effect in chloroform solution of  $[(C_nS)_8Pc]_2Eu$  at different concentrations. Normalized PL spectra were divided by concentration.

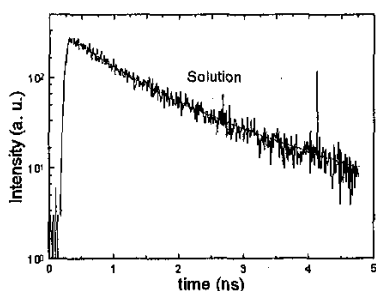


Fig. 7 The decay of photoluminescence of  $[(C_{60}S)_8Pc]_2Eu$  in chloroform solution upon excitation with laser light of 390 nm at room temperature.

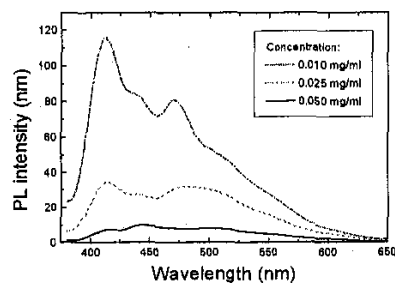


Fig. 8 Normalized photoluminescence spectra of  $[(C_{60}S)_8Pc]_2Eu$  in chloroform solution at different concentrations.

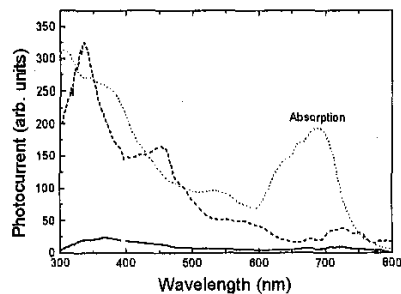


Fig. 9 Photocurrent spectra of undoped (solid line) and  $C_{60}$ -doped  $[(C_{60}S)_8Pc]_2Eu$  (5 mol%, dashed line) and absorption spectra of undoped cast film (dotted line).

The  $C_{60}$  doping effect was also observed in thin film of  $C_{60}$ -doped  $[(C_{60}S)_8Pc]_2Eu$ . In Figure 9 we show the spectral dependence of photoconductivity of  $[(C_{60}S)_8Pc]_2Eu$  before and after  $C_{60}$  doping and also absorption spectrum of undoped  $[(C_{60}S)_8Pc]_2Eu$  obtained by casting from solution. The photoconductivity peaks at the Soret and Q-bands positions were observed in undoped  $[(C_{60}S)_8Pc]_2Eu$ . In the phthalocyanine compounds the photogeneration occurs through the dissociation of

a loosely bound exciton at some dissociation center or at the interface. The enhancement of photoconductivity in  $C_{60}$ -doped  $[(C_{60}S)_8Pc]_2Eu$  is due to the efficient dissociation of excitons by  $C_{60}$ . The new strong peak at about 360 nm shows that the optical excitation at photon energy corresponding to the allowed transition ( $h_{1u}-t_{1g}$ ) in  $C_{60}$  also induces remarkable photoconductivity. In this case, a hole will be transferred from  $C_{60}$  to  $[(C_{60}S)_8Pc]_2Eu$ . An excited electron on  $C_{60}$  relaxes into negative polaron on  $C_{60}$ .

- [1] D. Adam et al., *Nature*, 371, 141 (1994).
- [2] N. Boden et al., *Phys. Rev. B* 52, 13274 (1995).
- [3] D. Wöhrle et al., *Synthesis*, 194 (1993)
- [4] H. Eichorn and D. Wöhrle, *Liq. Cryst.*, 22, 643 (1997).
- [5] K. Yoshino et al., *Jpn. J. Appl. Phys.* 36, 5183 (1997).
- [6] M. Maitrot et al., *Chem. Phys. Lett.* 133, 59 (1987)
- [7] K. Ban, K. Nishizawa and K. Ohta, to be published.
- [8] K. Yoshino et al., to be published in *Fullerene Science and Technology*, v. 7, no. 4, July, 1999.
- [9] M. H. V. Werts et al., *Chem. Phys. Lett.* 276, 196 (1997).
- [10] K. Yoshino et al., *J. Phys. Soc. Japan*, 34, 441 (1973).
- [11] K. L. Trojan et al., *J. Appl. Phys.* 69, 6007 (1991).
- [12] G. A. Crosby et al., *J. Chem. Phys.* 34, 743 (1961).
- [13] K. Yoshino et al., unpublished.