



Title	Evaluation of Interaction Parameters in Dilute Liquid Ternary Alloys by a Solution Model Based on the Free Volume Theory
Author(s)	Tanaka, Toshihiro; Gokcen, Nev A.; Spencer, Philip J. et al.
Citation	Zeitschrift für Metallkunde. 1993, 84(2), p. 100-105
Version Type	VoR
URL	<a href="https://hdl.handle.net/11094/26510">https://hdl.handle.net/11094/26510</a>
rights	©Carl Hanser Verlag, München
Note	

*The University of Osaka Institutional Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

Toshihiro Tanaka\*, Nev A. Gokcen\*\*, Philip J. Spencer\*\*\*, Zen-Ichiro Morita\* and Takamichi Iida\*

(\* Department of Materials Science and Processing, Faculty of Engineering, Osaka University, 2-1 Yamadaoka, Suita, Osaka, 565, Japan, \*\* Albany Research Center, U. S. Bureau of Mines, 1450 Queen Avenue SW, Albany, Oregon 97321-2198 USA, and \*\*\* Lehrstuhl für Theoretische Hüttenkunde und Metallurgie der Kernbrennstoffe, RWTH Aachen, Kopernikusstraße 16, 5100 Aachen, Germany)

# Evaluation of Interaction Parameters in Dilute Liquid Ternary Alloys by a Solution Model Based on the Free Volume Theory

A solution model based on the free volume theory has been applied to derive a Gibbs energy interaction parameter  $\varepsilon_B^C$ . The relation between an enthalpy interaction parameter  $\eta_B^C$  and an entropy interaction parameter  $\sigma_B^C$  has been obtained. These parameters were evaluated from some physical properties coupled with Miedema's semi-empirical method.

## 1 Introduction

In previous publications [1 to 5], a new solution model for liquid binary alloys based on the free volume theory has been presented. This model allows a successful description of the relation between partial enthalpy and partial excess entropy of mixing in infinitely dilute solutions of liquid binary alloys. In addition, it predicts the values of partial excess Gibbs energy of solutions, which are in reasonable agreement with experimental values.

In the present work, this solution model has been applied to ternary alloys to evaluate Gibbs energy interaction parameters in infinite dilution. Moreover, the relation between enthalpy and entropy interaction parameters is discussed.

## 2 Derivation of Thermodynamic Equations

The solution model is based on the free volume theory advanced by Shimoji and Niwa [6]. Assuming that an atom vibrates harmonically in its cell surrounded by the nearest-neighbor atoms, the partition functions for pure liquid A, B and C is given by the following equation:

$$Q_{XX} = V_{F,X}^{N_X} \cdot \exp(-E_X/kT) \\ = \{-\pi L_{XX}^2 kT/U_{XX}\}^{3N_X/2} \cdot \exp(-N_X U_{XX}/2kT) \\ (XX = AA, BB \text{ or } CC; X = A, B \text{ or } C) \quad (1)$$

where

$$U_{XX} = z \cdot u_{XX} \quad (2)$$

$V_{F,X}$  is the free volume of  $X$  atom in pure liquid ( $X = A, B$  or  $C$ );

$U_{XX}$  is the depth of potential energy of an atom  $X$  ( $X = A, B$  or  $C$ ) in its cell in pure liquid  $X$ , as shown in Fig. 1;  
 $u_{XX}$  is the energy of A-A, B-B or C-C pairs;  
 $z$  is the coordination number;  
 $L_{XX}$  is the distance which interatomic potential extends in a cell of pure liquid A, B or C, as shown in Fig. 1;  
 $N_X$  is the number of  $X$  atom ( $X = A, B$  or  $C$ );  
 $k$  is the Boltzmann constant and  
 $T$  is the temperature in K.

The partition function for an A-B-C ternary alloy is

$$Q = g \cdot \{-\pi L_A^2 kT/U_A\}^{3N_A/2} \cdot \{-\pi L_B^2 kT/U_B\}^{3N_B/2} \\ \cdot \{-\pi L_C^2 kT/U_C\}^{3N_C/2} \\ \cdot \exp\{-(N_A U_A + N_B U_B + N_C U_C)/2kT\} \quad (3)$$

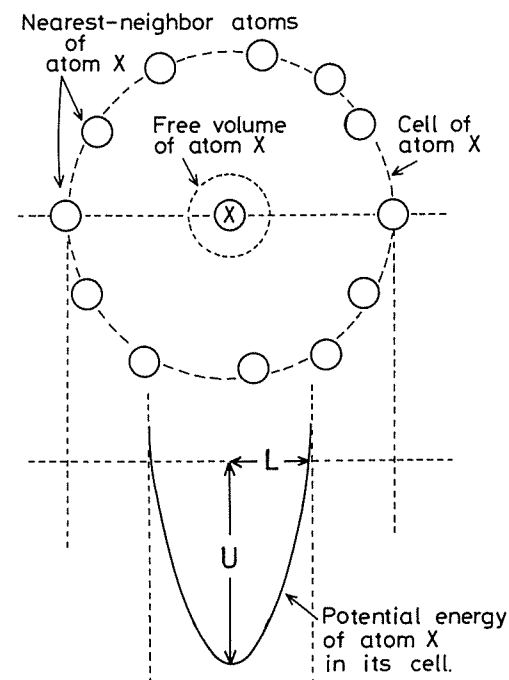


Fig. 1. Schematic diagram of potential energy in a cell of atom  $X$ .

where

$g$  is a degeneracy factor;

$U_X$  ( $X = A, B$  or  $C$ ) the depth of potential energy of an atom  $X$  ( $X = A, B$  or  $C$ ) in its cell in liquid A-B-C ternary alloy and

$L_X$  ( $X = A, B$  or  $C$ ) the distance which interatomic potential extends in a cell of an atom  $X$  ( $X = A, B$  or  $C$ ) in liquid A-B-C ternary alloy.

The energy  $E = (N_A U_A + N_B U_B + N_C U_C)/2$  of an A-B-C ternary alloy in Eq. (3) is assumed to be expressed in terms of the pair interaction energies A-A, B-B, C-C, A-B, A-C and B-C, namely  $u_{AA}, u_{BB}, u_{CC}, u_{AB}, u_{AC}$  and  $u_{BC}$  as follows:

$$E = N_A U_{AA}/2 + N_B U_{BB}/2 + N_C U_{CC}/2 + N_{AB} \Omega_{AB}/z + N_{BC} \Omega_{BC}/z + N_{AC} \Omega_{AC}/z \quad (4)$$

where  $U_{AA} = z \cdot u_{AA}$ ,  $U_{BB} = z \cdot u_{BB}$  and  $U_{CC} = z \cdot u_{CC}$

$N_{AB}, N_{AC}$  and  $N_{BC}$  in Eq. (4) are the numbers of A-B, A-C and B-C pairs, respectively.  $\Omega_{AB}, \Omega_{BC}$  and  $\Omega_{AC}$  are defined as follows:

$$\left. \begin{aligned} \Omega_{AB} &= z \cdot \{u_{AB} - 1/2 (u_{AA} + u_{BB})\} \\ \Omega_{BC} &= z \cdot \{u_{BC} - 1/2 (u_{BB} + u_{CC})\} \\ \Omega_{AC} &= z \cdot \{u_{AC} - 1/2 (u_{AA} + u_{CC})\} \end{aligned} \right\} \quad (5)$$

For condensed systems and at ordinary pressure levels, the Gibbs energy  $G$  may be equivalent to the Helmholtz energy  $F$  because their difference, the term  $PV$ , is usually negligible. Thus, for all practical purpose

$$G_{XX} \sim F_{XX} = -kT \ln Q_{XX} \quad (XX = AA, BB \text{ or } CC) \quad (6)$$

$$G \sim F = -kT \ln Q \quad (7)$$

From the above equations, the change in Gibbs energy of mixing,  $\Delta G_{MIX}$  is

$$\begin{aligned} \Delta G_{MIX} &= G - (G_{AA} + G_{BB} + G_{CC}) \\ &= (N_{AB} \Omega_{AB} + N_{BC} \Omega_{BC} + N_{AC} \Omega_{AC})/z - kT \cdot \ln g \\ &\quad - kT \cdot 3/2 [N_A \cdot \ln (-\pi L_A^2 kT/U_A) + \\ &\quad N_B \cdot \ln (-\pi L_B^2 kT/U_B) + N_C \cdot \ln (-\pi L_C^2 kT/U_C) \\ &\quad - \{N_A \cdot \ln (-\pi L_{AA}^2 kT/U_{AA}) + \\ &\quad N_B \cdot \ln (-\pi L_{BB}^2 kT/U_{BB}) + \\ &\quad N_C \cdot \ln (-\pi L_{CC}^2 kT/U_{CC})\}] \end{aligned} \quad (8)$$

In the following, the enthalpy and entropy terms in the A-B-C ternary alloy will be derived separately.

## 2.1 The Enthalpy Term

From Eq. (8),

$$\Delta H'_{MIX} = (N_{AB} \Omega_{AB} + N_{BC} \Omega_{BC} + N_{AC} \Omega_{AC})/z \quad (9)$$

With regard to the configuration of atoms in alloys, short range order is taken into account on the basis of the first approximation to the regular solution model proposed by one of the authors [7]. According to this model,  $N_{AB}, N_{BC}$  and  $N_{AC}$  are given by the following equations for dilute solutions:

$$N_{AB} = z \cdot N_0 \cdot x_A x_B (1 - x_A x_B \Omega_{AB}/kT) \quad (10)$$

$$N_{BC} = z \cdot N_0 \cdot x_B x_C (1 - x_B x_C \Omega_{BC}/kT) \quad (11)$$

$$N_{AC} = z \cdot N_0 \cdot x_A x_C (1 - x_A x_C \Omega_{AC}/kT) \quad (12)$$

where

$N_0$  is Avogadro's number,

$x_A, x_B$  and  $x_C$  are the mole fractions of A, B and C, respectively.

Consequently, the enthalpy of mixing per atom  $\Delta H_{MIX} = \Delta H'_{MIX}/N_0$  can be given by the following equation:

$$\begin{aligned} \Delta H_{MIX} &= \Omega_{AB} \cdot x_A \cdot x_B (1 - x_A x_B \Omega_{AB}/kT) \\ &\quad + \Omega_{BC} \cdot x_B \cdot x_C (1 - x_B x_C \Omega_{BC}/kT) \\ &\quad + \Omega_{AC} \cdot x_A \cdot x_C (1 - x_A x_C \Omega_{AC}/kT) \end{aligned} \quad (13)$$

## 2.2 Entropy Term

The entropy arising from the atomic configuration in the alloys,  $\Delta S_{CONF} = k \cdot \ln g$ , consists of the following two terms:

$$\Delta S_{CONF} = k \cdot \ln g = \Delta S_{CONF}^{Ideal} + \Delta S_{CONF}^{Ex} \quad (14)$$

For the excess configurational entropy in the alloys, the following equation based on the first approximation to the regular solution model [7] was also adopted.

$$\begin{aligned} \Delta S_{CONF}^{Ex} &= -x_A^2 x_B^2 \Omega_{AB}^2 / 2kT^2 - x_B^2 x_C^2 \Omega_{BC}^2 / 2kT^2 \\ &\quad - x_A^2 x_C^2 \Omega_{AC}^2 / 2kT^2 \end{aligned} \quad (15)$$

The excess entropy arising from nonconfigurational contributions, for example, from the vibration of atoms in their cell,  $\Delta S_{VIB}^{Ex}$  can be derived from Eq. (8) as follows:

$$\begin{aligned} \Delta S_{VIB}^{Ex} &= 3/2 \cdot kN_0 \{2x_A \cdot \ln (L_A/L_{AA}) + \\ &\quad 2x_B \cdot \ln (L_B/L_{BB}) + 2x_C \cdot \ln (L_C/L_{CC}) + \\ &\quad x_A \cdot \ln (U_{AA}/U_A) + x_B \cdot \ln (U_{BB}/U_B) + \\ &\quad x_C \cdot \ln (U_{CC}/U_C)\} \end{aligned} \quad (16)$$

In Eq. (16), it is necessary to have information on  $L_A, L_B, L_C, U_A, U_B$  and  $U_C$  in the A-B-C ternary alloy. In this work, the simplest relations were adopted from Shimoji and Niwa [6], i.e.,

$$\left. \begin{aligned} U_A &= x_A U_{AA} + x_B U_{AB} + x_C U_{AC} \\ U_B &= x_A U_{AB} + x_B U_{BB} + x_C U_{BC} \\ U_C &= x_A U_{AC} + x_B U_{BC} + x_C U_{CC} \end{aligned} \right\} \quad (17)$$

where

$$U_{AB} = z \cdot u_{AB} \quad U_{BC} = z \cdot u_{BC} \quad U_{AC} = z \cdot u_{AC} \quad (18)$$

$$\left. \begin{aligned} L_A &= 1/2 \{L_{AA} + (x_A L_{AA} + x_B L_{BB} + x_C L_{CC})\} \\ L_B &= 1/2 \{L_{BB} + (x_A L_{AA} + x_B L_{BB} + x_C L_{CC})\} \\ L_C &= 1/2 \{L_{CC} + (x_A L_{AA} + x_B L_{BB} + x_C L_{CC})\} \end{aligned} \right\} \quad (19)$$

Finally, the excess entropy for vibrational contributions of atoms in their cell per atom,  $\Delta S_{VIB}^{Ex} = \Delta S_{VIB}^{Ex}/N_0$  is given by

$$\begin{aligned}
\Delta S_{\text{VIB}}^{\text{Ex}} = & 3/2 k x_A x_B [(L_{AA} - L_{BB})^2 / (L_{AA} \cdot L_{BB}) \\
& + \{4U_{AA}U_{BB} - 2\Omega_{AB}(U_{AA} + U_{BB}) \\
& - (U_{AA} + U_{BB})^2\} / (2U_{AA}U_{BB})] \\
& + 3/2 k x_B x_C [(L_{BB} - L_{CC})^2 / (L_{BB} \cdot L_{CC}) \\
& + \{4U_{BB}U_{CC} - 2\Omega_{BC}(U_{BB} + U_{CC}) \\
& - (U_{BB} + U_{CC})^2\} / (2U_{BB}U_{CC})] \\
& + 3/2 k x_A x_C [(L_{AA} - L_{CC})^2 / (L_{AA} \cdot L_{CC}) \\
& + \{4U_{AA}U_{CC} - 2\Omega_{AC}(U_{AA} + U_{CC}) \\
& - (U_{AA} + U_{CC})^2\} / (2U_{AA}U_{CC})]
\end{aligned} \quad (20)$$

where the following relations were used:

$$\left. \begin{aligned} U_{AB} &= \Omega_{AB} + (U_{AA} + U_{BB})/2 \\ U_{BC} &= \Omega_{BC} + (U_{BB} + U_{CC})/2 \\ U_{AC} &= \Omega_{AC} + (U_{AA} + U_{CC})/2 \end{aligned} \right\} \quad (21)$$

The first order Gibbs energy interaction parameter  $\varepsilon_B^C$ , proposed by Wagner [8], may be written as

$$\begin{aligned}
\varepsilon_B^C &= \{(\partial^2 \Delta G^{\text{Ex}} / \partial x_C \partial x_B)_{x_B \rightarrow 0, x_C \rightarrow 0}\} / k T \\
&= (\eta_B^C - T \sigma_B^C) / k T
\end{aligned} \quad (22)$$

where  $\eta_B^C$  and  $\sigma_B^C$  are the enthalpy and entropy interaction parameters, respectively, and according to Lupis and Elliott [9] are defined as follows:

$$\eta_B^C = (\partial^2 \Delta H_{\text{MIX}} / \partial x_C \partial x_B)_{x_B \rightarrow 0, x_C \rightarrow 0} \quad (23)$$

$$\begin{aligned}
\sigma_B^C &= (\partial^2 \Delta S^{\text{Ex}} / \partial x_C \partial x_B)_{x_B \rightarrow 0, x_C \rightarrow 0} \\
&= \{\partial^2 (\Delta S_{\text{CONF}}^{\text{Ex}} + \Delta S_{\text{VIB}}^{\text{Ex}}) / \partial x_C \partial x_B\}_{x_B \rightarrow 0, x_C \rightarrow 0}
\end{aligned} \quad (24)$$

From Eqs. (13), (15), (20), (23) and (24),  $\eta_B^C$  and  $\sigma_B^C$  can be written as

$$\eta_B^C = \Omega_{BC} - \Omega_{AB} - \Omega_{AC} \quad (25)$$

$$\begin{aligned}
\sigma_B^C &= 3/2 k [(L_{BB} - L_{CC})^2 / (L_{BB}L_{CC}) + \{4U_{BB}U_{CC} \\
&- 2\Omega_{BC}(U_{BB} + U_{CC}) - (U_{BB} + U_{CC})^2\} / (2U_{BB}U_{CC}) \\
&- (L_{AA} - L_{BB})^2 / (L_{AA}L_{BB}) - \{4U_{AA}U_{BB} \\
&- 2\Omega_{AB}(U_{AA} + U_{BB}) - (U_{AA} + U_{BB})^2\} / (2U_{AA}U_{BB}) \\
&- (L_{AA} - L_{CC})^2 / (L_{AA}L_{CC}) - \{4U_{AA}U_{CC} \\
&- 2\Omega_{AC}(U_{AA} + U_{CC}) - (U_{AA} + U_{CC})^2\} / (2U_{AA}U_{CC})]
\end{aligned} \quad (26)$$

From Eqs. (22), (25) and (26), the following relation can be obtained.

$$\varepsilon_B^C = \varepsilon_B^C \quad (27)$$

Further,  $\varepsilon_B^B$  can be expressed as follows:

$$\varepsilon_B^B = (\eta_B^B - T \sigma_B^B) / k T \quad (28)$$

$$\eta_B^B = -2\Omega_{AB} \quad (29)$$

$$\begin{aligned}
\sigma_B^B &= -3k[(L_{AA} - L_{BB})^2 / L_{AA}L_{BB} \\
&+ \{4U_{AA}U_{BB} - 2\Omega_{AB}(U_{AA} + U_{BB}) \\
&- (U_{AA} + U_{BB})^2\} / (2U_{AA}U_{BB})]
\end{aligned} \quad (30)$$

According to the solution model, as applied to binary alloys in our previous work [2 to 5], the relation between  $\varepsilon_B^B$  and the activity coefficient at infinite dilution  $\gamma_B^0$  can be expressed by

$$\varepsilon_B^B = -2 \ln \gamma_B^0 \quad (31)$$

$L_{XX}$  ( $XX = AA, BB$  or  $CC$ ) in Eq. (26) is assumed to be half of the nearest-neighbor distance and is obtained from the following equation [1 to 5]:

$$L_{XX} = 1/2 \cdot (2^{1/2} V_X / N_0)^{1/3} \quad (32)$$

where  $V_X$  is a molar volume of pure  $X$  ( $X = A, B$  or  $C$ ).

$\Omega_{BC}$ ,  $\Omega_{AB}$  and  $\Omega_{AC}$  can be assumed to be equal to the partial enthalpy of mixing in infinite dilution  $\Delta \bar{H}_{C(B)}$  of solute C in solvent B,  $\Delta \bar{H}_{B(A)}$  of solute B and  $\Delta \bar{H}_{C(A)}$  of solute C in solvent A, respectively [2 to 5].

$U_{AA}$ ,  $U_{BB}$  and  $U_{CC}$  in Eq. (26) are calculated from the following equation [4 to 5] when the units of  $\Omega_{BC}$ ,  $\Omega_{AB}$  and  $\Omega_{AC}$  are taken as  $\text{J} \cdot \text{mol}^{-1}$ , and  $k$  in Eqs. (1) to (30) is taken as gas constant  $R/\text{J} \cdot \text{K}^{-1} \cdot \text{mol}^{-1}$ .

$$U_{XX} = -685.3 \cdot (\beta_X)^2 \cdot T_{m,X} / \text{J} \cdot \text{mol}^{-1} \quad (33)$$

where  $T_{m,X}$  is the melting point of element  $X$  and  $\beta_X$  the coefficient to transfer the solid state frequency to that in the liquid at the melting point [10 to 12].

The values of  $\beta_X$  for various elements were obtained from the experimental data on surface tension of pure liquid metals [10]. When the values of  $\beta_X$  are not available, it can be set approximately [10, 12] to 0.5.

The derivation of the above Eq. (33) and the physical meaning of  $\beta_X$  were described in detail in our previous work [1 to 5, 10 to 12].

Consequently,  $\eta_B^C$  and  $\sigma_B^C$  can be obtained from Eqs. (25) to (33), together with the partial enthalpy of mixing in infinite dilution and some fundamental physical properties, i.e.,  $T_{m,X}$ ,  $V_X$  and  $\beta_X$  of the components in the pure state.

### 3 Calculation of the Gibbs Energy Interaction Parameter, the Enthalpy Interaction Parameter and the Entropy Interaction Parameter

As shown in Eqs. (4), (13) and (25),  $\Delta H_{\text{MIX}}$  in ternary alloys according to the present model consists of the summation of the interaction energies between each pair of elements. Extra terms describing the interactions between the three elements in ternary systems, however, are not considered. If each binary in the ternary system shows large interaction energies, i. e. large absolute values of  $\Delta H_{\text{MIX}}$ , it seems inappropriate to apply the present model for the calculation of  $\varepsilon_B^C$  values. The calculation of  $\varepsilon_B^C$ ,  $\eta_B^C$  and  $\sigma_B^C$ , therefore, was carried out for non-ferrous ternary alloys formed from Bi, Cd, In, Pb, Sb, Sn and Zn and also in Fe-Mn base and Fe-Cr base alloys. The components in these systems have similar physical properties and the interaction energies of each pair do not seem to be too great.

The values of  $T_{m,X}$ ,  $V_X$  and  $\beta_X$  for various elements are shown in Table 1 [10, 13]. To evaluate  $\Omega_{BC}$ ,  $\Omega_{AB}$  and  $\Omega_{AC}$  in Eqs. (25) and (26), the values of partial enthalpy of mixing  $\Delta \bar{H}_{C(B)}$  in solvent B, and  $\Delta \bar{H}_{B(A)}$  and  $\Delta \bar{H}_{C(A)}$  in solvent A were calculated using Miedema's semi-empirical method [13], as shown in Table 2.

Table 1. Physical properties of some elements used in the calculation of  $\sigma_B^C$ .  $T_m$ ,  $X$ : Ref. [10],  $V_X$ : Ref. [13] and  $\beta_X$ : Ref. [10].

Elements	$T_m$ , $X$ /K	$V_X$ /cm <sup>3</sup> mol <sup>-1</sup>	$\beta_X$
Bi	544	19.32	0.54
Cd	594	13.00	0.56
Ce	1068	21.62	0.50
Co	1765	6.69	0.48
Cr	2178	7.23	0.50
Cu	1356	7.12	0.46
Fe	1808	7.09	0.48
In	430	15.74	0.68
La	1193	22.54	0.50
Mn	1517	7.35	0.50
Mo	2895	9.39	0.50
Nb	2740	10.81	0.50
Ni	1728	6.60	0.47
Pb	601	18.28	0.55
Sb	904	16.96	0.40
Si	1687	8.61	0.38
Sn	505	16.30	0.64
Ta	3123	10.81	0.50
Ti	1998	10.58	0.50
V	1973	8.36	0.50
W	3655	9.55	0.50
Zn	693	9.17	0.54

Table 2. Partial enthalpy of mixing  $\Delta\bar{H}_{X(Y)}/\text{kJ} \cdot \text{mol}^{-1}$  calculated from Miedema's semi-empirical method [13].

Solvent (Y)	Solute (X)	$\Delta\bar{H}_{X(Y)}$	Solvent (Y)	Solute (X)	$\Delta\bar{H}_{X(Y)}$	Solvent (Y)	Solute (X)	$\Delta\bar{H}_{X(Y)}$
Bi	Cd	4	Bi	In	-5	Bi	Pb	0
Bi	Sb	3	Bi	Sn	5	Bi	Zn	14
Cd	Bi	5	Cd	Pb	7	Cd	Sb	-11
Cd	Sn	-1	Cd	Zn	3	In	Pb	-3
In	Sn	-1	In	Zn	10	Pb	Bi	0
Pb	Cd	5	Pb	In	-3	Pb	Sb	2
Pb	Sn	6	Pb	Zn	16	Sb	Cd	-8
Sb	Pb	2	Sn	Cd	-1	Sn	In	-1
Sn	Pb	7	Sn	Zn	3	Zn	Bi	23
Zn	Cd	4	Zn	In	14	Zn	Pb	25
Zn	Sb	-5	Zn	Sn	5	Fe	Co	-2
Fe	Cr	-6	Fe	Cu	50	Fe	La	25
Fe	Mn	1	Fe	Mo	-9	Fe	Nb	-70
Fe	Ni	-6	Fe	Pb	160	Fe	Si	-75
Fe	Sn	56	Fe	Ta	-67	Fe	Ti	-74
Fe	V	-29	Fe	W	0	Cr	Co	-18
Cr	Cu	49	Cr	Mn	8	Cr	Mo	2
Cr	Ni	-27	Cr	Pb	153	Cr	Si	-87
Cr	Sn	53	Cr	V	-8	Mn	Co	-21
Mn	Cr	9	Mn	La	14	Mn	Mo	22
Mn	Nb	-17	Mn	Ni	-33	Mn	Pb	38
Mn	Si	-120	Mn	Ta	-17	Mn	Ti	-36
Mn	V	-3	Mn	W	28			

Table 3. Calculated results for  $\eta_B^C$ ,  $\sigma_B^C$  and  $\varepsilon_B^C$  in liquid ternary alloys with the experimental values of  $\varepsilon_B^C$ .

No.	Elements A B C	Temp./ K	$\eta_B^C$ / kJ · mol <sup>-1</sup>	$\sigma_B^C$ / J · K <sup>-1</sup> mol <sup>-1</sup>	$\varepsilon_B^C$ / (calc.)	$\varepsilon_B^C$ / (exp.)	Ref.
1	Bi Cd Pb	773	3	0.7	0.4	1.62	14
2	Bi Zn Cd	723	-14	-3.3	-1.9	-0.3	15
3	Bi Zn In	723	5	1.0	0.7	2.2	15
4	Bi Zn Pb	723	11	2.2	1.6	1.4	15
5	Bi Zn Sb	723	-22	-5.2	-3.0	-5.4	15
6	Bi Zn Sn	723	-14	-2.5	-2.0	-0.5	15
7	Cd Bi Pb	773	-12	-2.8	-1.5	-3.2	14
8	Cd Pb Sb	773	6	1.4	0.8	0.0	14
9	Cd Pb Sn	773	0	-0.3	0.0	2.86	14
10	Cd Sn Pb	773	1	-0.1	0.2	2.86	14
11	Cd Zn Pb	805	15	3.1	1.9	0.95	16
12	Cd Zn Sn	805	3	0.8	0.3	-1.10	16
13	In Zn Pb	805	18	3.7	2.2	1.00	16
14	In Zn Sn	805	-4	-0.7	-0.5	-0.63	16
15	Pb Bi Cd	773	-1	-0.1	-0.1	-0.86	14
16	Pb Cd Sn	773	-12	-2.4	-1.6	1.35	14
17	Pb Sb Cd	773	-15	-3.4	-1.9	-1.60	14
18	Pb Zn Bi	805	7	1.6	0.9	-0.70	16
19	Pb Zn Cd	805	-17	-3.9	-2.1	-2.05	16
20	Pb Zn In	805	1	-0.1	0.2	-1.90	16
21	Pb Zn Sn	805	-17	-3.3	-2.1	-4.20	16
22	Sb Cd Pb	773	13	3.5	1.6	2.8	14
23	Sn Cd Pb	773	1	0.5	0.1	0.0	14
24	Sn Cd Zn	973	1	-0.1	0.1	-1.65	14
25	Sn Zn In	805	12	2.2	1.5	0.41	16
26	Sn Zn Pb	805	15	3.1	1.9	1.22	16
27	Fe Mn Co	1843	-20	-1.8	-1.1	-0.9	17
28	Fe Mn Cr	1843	14	0.8	0.8	0.9	17
29	Fe Mn La	1873	-12	-0.9	-0.7	61.6	17
30	Fe Mn Mo	1843	30	1.4	1.8	1.1	17
31	Fe Mn Nb	1843	52	2.9	3.0	2.1	17
32	Fe Mn Ni	1843	-28	-2.6	-1.5	-1.8	17
33	Fe Mn Pb	1823	-123	-16.5	-6.1	-5.2	17
34	Fe Mn Si	1873	-46	-5.3	-2.3	-3.3	17
35	Fe Mn Ta	1843	49	2.3	2.9	0.4	17
36	Fe Mn Ti	1873	37	2.5	2.1	-9.7*	17
37	Fe Mn V	1843	25	1.8	1.4	1.3	17
38	Fe Mn W	1843	27	0.7	1.7	3.1	17
39	Fe Cr Co	1903	-10	-0.8	-0.5	-4.7	17
40	Fe Cr Cu	1873	5	-1.5	0.5	4.1	17
41	Fe Cr Mn	1843	13	0.7	0.8	0.9	17
42	Fe Cr Mo	1873	17	3.1	0.7	0.0	17
43	Fe Cr Ni	1873	-15	-1.5	-0.8	0.0	17
44	Fe Cr Pb	1873	-1	-5.5	0.6	4.4	17
45	Fe Cr Si	1903	-6	-2.0	-0.1	0.0	17
46	Fe Cr Sn	1823	3	-3.2	0.6	3.3	17
47	Fe Cr V	1873	27	2.8	1.4	2.6	17

\* As Ueno et al. [18] pointed out,  $\varepsilon_{\text{Mn}}^{\text{Ti}}(\text{exp.}) = 3.9$ [21].

The calculated results of  $\varepsilon_B^C$ ,  $\eta_B^C$  and  $\sigma_B^C$  in the above systems are shown in Table 3 together with the experimental values of  $\varepsilon_B^C$  [14 to 17]. Figure 2 presents a comparison of the calculated  $\varepsilon_B^C$  with their experimental values. As shown in Table 3 and Fig. 2, most of the calculated  $\varepsilon_B^C$  values have the same sign as those for the experimental values. Since the simple assumptions were

used to extend the model to ternary systems in this work, it is difficult to make a reliable comparison of the calculated and experimental  $\varepsilon_B^C$  results. In addition, the accuracy of the calculated results for  $\varepsilon_B^C$  in this model depends on that of  $\Delta\bar{H}_{X(Y)}$  ( $X = \text{A, B or C}$ ;  $Y = \text{A or B}$ ) calculated from Miedema's semi-empirical method.

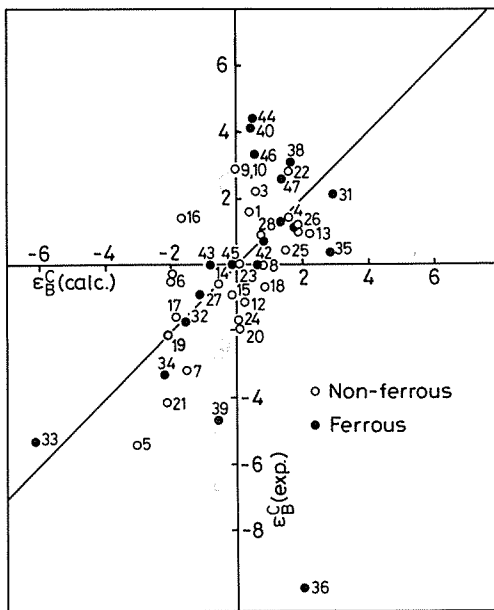


Fig. 2. Comparison of the calculated  $\varepsilon_B^C$  with the experimental values (numbers in the figure correspond to those in Table 3).

Ueno et al. have also calculated  $\varepsilon_B^C$  using Miedema's semi-empirical method on the basis of the pseudopotential formalism coupled with the Gibbs energy of the hard sphere system [18, 19]. They did not, however, refer to the relationship between  $\eta_B^C$  and  $\sigma_B^C$ .

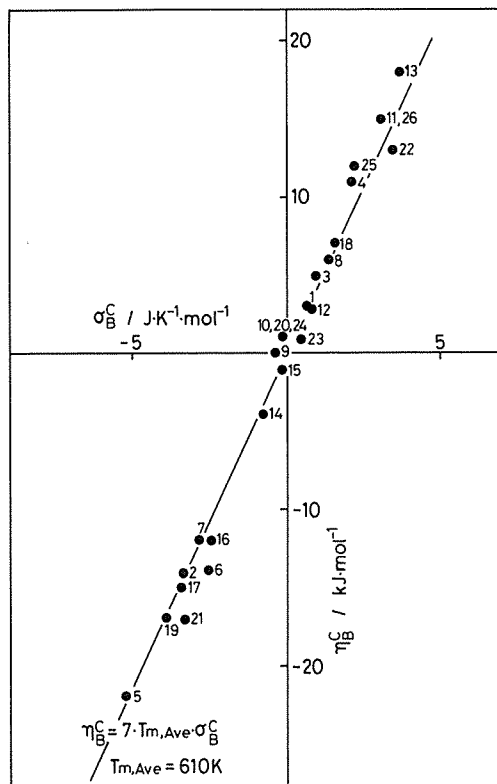


Fig. 3. Relationship between  $\eta_B^C$  and  $\sigma_B^C$  (calculated) for liquid non-ferrous ternary alloys (numbers in the figure correspond to those in Table 3).

#### 4 Relation Between Enthalpy and Entropy Interaction Parameters in Liquid Ternary Alloys

Lupis and Elliott [9] and Richardson [20] have shown that certain correlations exist between  $\eta_B^C$  and  $\sigma_B^C$  in some liquid ternary systems on the basis of the available experimental values. Figures 3 and 4 show the relation between  $\eta_B^C$  and  $\sigma_B^C$  calculated from the present model in non-ferrous alloys and ferrous alloys, respectively. From these figures, there seem to be linear correlations between  $\eta_B^C$  and  $\sigma_B^C$ . From Eqs. (25), (26), (32) and (33), if the components in the ternary alloys have similar physical properties, i.e.

$$\left. \begin{aligned} \beta_A &= \beta_B = \beta_C (= 0.50) \\ V_A &\approx V_B \approx V_C \\ T_{m,A} &\approx T_{m,B} \approx T_{m,C} (= T_{m,Ave}) \end{aligned} \right\} \quad (34)$$

the following approximate equation applies:

$$\eta_B^C \approx 7.0 \cdot T_{m,Ave} \cdot \sigma_B^C \quad (35)$$

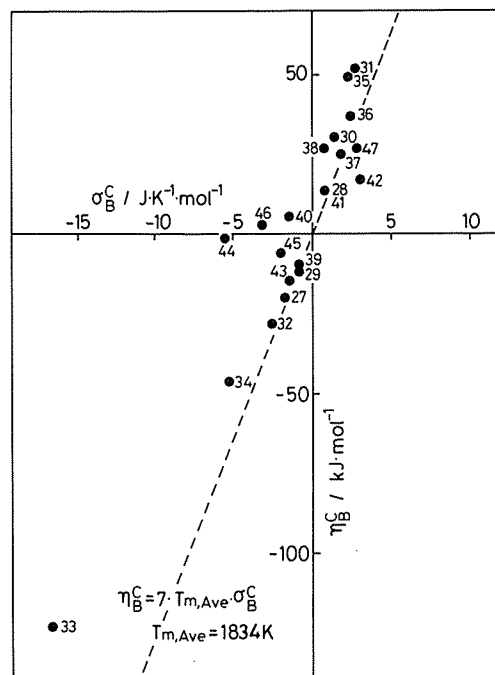


Fig. 4. Relationship between  $\eta_B^C$  and  $\sigma_B^C$  (calculated) for liquid ferrous ternary alloys (numbers in the figure correspond to those in Table 3).

where  $T_{m,Ave}$  is the arithmetic average of  $T_{m,A}$ ,  $T_{m,B}$  and  $T_{m,C}$ .

The above equation implies that the alloy, for which the components have the higher melting points, will show a larger value of the ratio  $\eta_B^C/\sigma_B^C$ . The relation in Eq. (35) with the average value of the melting points of Bi, Cd, In, Pb, Sb, Sn and Zn ( $T_{m,Ave} = 610$  K) is shown in Fig. 3, where the approximation in Eq. (35) satisfies the relation between  $\eta_B^C$  and  $\sigma_B^C$  for the alloys formed by the above metals. The dotted line in Fig. 4 indicates the relation in Eq. (35) with the average value of the melting point of Fe, Mn and Cr ( $T_{m,Ave} = 1834$  K). As shown in this figure, when the melting point of the third element C is much different from those of Fe, Mn and Cr, their points (e.g., No. 33 for Fe–Mn–Pb, No. 44 for Fe–Cr–Pb and so on) are located away from the line. Hence, if the second or third element

in  $\varepsilon_B^C$  is a gaseous element such as oxygen or nitrogen, another relationship between  $\eta_B^C$  and  $\sigma_B^C$  instead of Eq. (35) should be derived because  $U_{XX}$  can not be expressed in terms of the melting points of those elements as in Eq. (33).

## 5 Concluding Remarks

In the present work, a previously described solution model based on the free volume theory was applied to ternary alloys to calculate the interaction parameter  $\varepsilon_B^C$ , as well as the enthalpy and entropy interaction parameters,  $\eta_B^C$  and  $\sigma_B^C$ , in some non-ferrous and ferrous alloys. The values of  $\varepsilon_B^C$ ,  $\eta_B^C$  and  $\sigma_B^C$  can be evaluated from the partial enthalpy of mixing  $\Delta\bar{H}_{X(Y)}$  obtained by Miedema's semi-empirical method and some physical properties of pure components. The relationship between  $\eta_B^C$  and  $\sigma_B^C$  can be expressed approximately as a linear relation dependent upon the melting points of the components.

## Literature

1. Tanaka, T.; Gokcen, N. A.; Morita, Z.: *Z. Metallkd.* 81 (1990) 49.
2. Tanaka, T.; Gokcen, N. A.; Morita, Z.: *Z. Metallkd.* 81 (1990) 349.
3. Tanaka, T.; Gokcen, N. A.; Morita, Z.; Spencer, P. J.: *Anales de Fisica-Serie B* (Proceedings of the Discussion Meeting on Thermodynamics of Alloys, Barcelona, Spain) Vol. 86 (1990) 104.
4. Tanaka, T.; Gokcen, N. A.; Neuschütz, D.; Spencer, P. J.; Morita, Z.: *Steel Research* 62 (1991) 385.
5. Tanaka, T.; Imai, N.; Kiyose, A.; Iida, T.; Morita, Z.: *Z. Metallkd.* 82 (1991) 836.
6. Shimoji, M.; Niwa, K.: *Acta Metall.* 5 (1957) 496.
7. Gokcen, N. A.: *Statistical Thermodynamics of Alloys*, Plenum Press, New York (1986).
8. Wagner, C.: *Thermodynamics of Alloys*, Addison-Wesley, Reading, MA (1952) 51.
9. Lupis, C. H. P.; Elliott, J. F.: *Acta Metall.* 15 (1967) 265.
10. Iida, T.; Guthrie, R. I. L.: *The Physical Properties of Liquid Metals*, Clarendon Press, Oxford (1988) 6, 17, 97 and 100.
11. Iida, T.; Kasama, A.; Misawa, M.; Morita, Z.: *J. Japan Inst. Metals*, 38 (1974) 177.
12. Kasama, A.; Iida, T.; Morita, Z.: *J. Japan Inst. Metals* 40 (1976) 1030.
13. Niessen, A. K.; de Boer, F. R.; Boom, R.; de Châtel, P. F.; Mattens, W. C. M.; Miedema, A. R.: *CALPHAD* 7 (1983) 51.
14. Dealy, J. M.; Pehlke, R. D.: *Trans. Met. Soc. AIME* 227 (1963) 88.
15. Gluck, J. V.; Pehlke, R. D.: *Trans. Met. Soc. AIME* 239 (1967) 36.
16. Moser, Z.: *Metall. Trans. B6B* (1975) 103.
17. *Steelmaking Data Sourcebook*. The Japan Society for the Promotion of Science, The 19th Committee on Steelmaking, Gordon and Breach Science Pub., New York (1988) 273.
18. Ueno, S.; Waseda, Y.; Jacob, K. T.; Tamaki, S.: *Steel Research* 59 (1988) 474.
19. Ueno, S.; Waseda, Y.; Chang, Y. A.: *Z. Metallkd.* 79 (1988) 435.
20. Richardson, F. D.: *Physical Chemistry of Melts in Metallurgy*, Vol. I, Academic Press, New York (1974) 190.
21. Buzek, Z.: *Hutn. Aktuality Recnik*. 20 (1979) and in: Final Report on "Thermodynamic Data for Steelmaking" Commission of the European Communities, Luxembourg, No. 7820 (1982) 298.

(Received February 24, 1992)