



Title	Enhancement of Au Dissolution by Microorganisms Using an Accelerating Cathode Reaction
Author(s)	Kita, Yoshito; Nishikawa, Hiroshi; Ike, Michihiko et al.
Citation	Metallurgical and Materials Transactions B. 2009, 40(1), p. 39-44
Version Type	VoR
URL	https://hdl.handle.net/11094/2893
rights	
Note	

The University of Osaka Institutional Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

Enhancement of Au Dissolution by Microorganisms Using an Accelerating Cathode Reaction

YOSHITO KITA, HIROSHI NISHIKAWA, MICHIIHIKO IKE,
and TADASHI TAKEMOTO

A *Chromobacterium violaceum* (*C. violaceum*) strain that produces cyanide was used to dissolve Au. In this bacterial Au dissolution process, decreased dissolved oxygen concentration in the bacterial medium significantly inhibits Au dissolution. Although aeration is effective in increasing the level of dissolved oxygen in the bacterial medium, it is not effective in increasing Au dissolution during the growth phase of the bacteria because of the latter's high respiratory consumption of oxygen. The present study investigated the utility of H_2O_2 , rather than aeration, for increasing dissolved oxygen concentrations in bacterial growth medium. It was anticipated that the stronger oxidation reagent would increase Au dissolution by accelerating the cathode reaction during the bacterial growth phase. In fact, the addition of H_2O_2 to the bacterial culture increased dissolved oxygen concentrations in the growth phase and also drastically increased the dissolution rate of Au. Electrochemical measurements indicated that H_2O_2 addition to the bacterial medium accelerated the cathode reaction and thus enhanced Au dissolution by this biological process.

DOI: 10.1007/s11663-008-9177-z




© The Minerals, Metals & Materials Society and ASM International 2008

I. INTRODUCTION

IN electronic assembly processes, Au is frequently used for surface plating and bonding wires due to its excellent bonding characteristics. At the same time, the amount of Au used in recent high density surface mount boards decreases due to advanced thin plating and joining technologies. Gold is a precious metal and is highly valued for its physicochemical properties; thus, it is desirable to recover Au from industrial waste.^[1] At present, metallic scraps containing Au are generally treated by hydrometallurgical methods such as aqua regia or cyanidation. While excessive use of cyanide for the dissolution of Au is associated with environmental risk, biological Au dissolution methods produce little cyanide and, when coupled with subsequent detoxification,^[2,3] are particularly environmentally friendly processes.

Chromobacterium violaceum (*C. violaceum*) is a mesophilic, motile, Gram-negative, facultative anaerobe.^[4] Strains of this microorganism produce cyanide^[5] and can subsequently detoxify the cyanide using β -cyanoalanine synthase when grown in minimal medium.^[6–8] Therefore, this strain can potentially be used in ecologically-friendly Au recovery processes.^[9,10]

The Au dissolution in cyanide solution consists of an anode Reaction [1] and a cathode Reaction [2]. These reactions are summarized by Elsner's Eq. [3]:^[11]



The rate of Au dissolution depends on a number of factors, including cyanide concentration, Au surface area,^[12,13] mixing, solution conditions (temperature and pH), interference from other materials, and dissolved oxygen concentration.^[14,15] Electrochemically, cyanide and oxygen concentrations are important factors affecting the dissolution of Au,^[16–18] and aeration of the bacterial suspension effectively increases the Au dissolution rate.^[10] However, during the growth phase, when *C. violaceum* rapidly consumes dissolved oxygen for bacterial respiration, Au dissolution is inhibited due to suppression of the cathode reaction arising from insufficient dissolved oxygen.

The aim of this study was to investigate the effect of H_2O_2 as an efficient source of oxygen on the Au dissolution rate during the growth phase of *C. violaceum*.

II. MATERIALS AND METHODS

A. Organism and Culture Conditions

Chromobacterium violaceum NBRC 12614 was grown in flasks containing YP medium (polypeptone 10 g,

YOSHITO KITA, Graduate Student, is with Graduate School of Engineering, Osaka University, Ibaraki, Osaka 567-0047, Japan. Contact e-mail: kitayokitayo@gmail.com HIROSHI NISHIKAWA, Associate Professor, and TADASHI TAKEMOTO, Professor, are with Joining and Welding Research Institute, Osaka University, Ibaraki, Osaka 567-0047, Japan. MICHIIHIKO IKE, Professor, is with Department of Environmental Engineering, Osaka University, Suita, Osaka 565-0871, Japan.

Manuscript submitted November 5, 2007.

Article published online December 10, 2008.

yeast extract 2 g, $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$ 1 g, and distilled water 1 L) at 30 °C with agitation at 110 rpm.

B. Au Dissolution from Powder

For the Au dissolution test, 0.5 mol Au powder (superficial area, 0.4 m^2/g ; average particle diameter, 1.1 μm ; and tap density, 6.4 g/cm^3) was added to a 500-mL conical flask containing 300 mL YP medium inoculated with 3.0 mL actively growing *C. violaceum* culture. To accelerate cyanide production by *C. violaceum*, 30 mmol/L glycine was added to the medium.^[9] In order to increase the dissolved oxygen concentration, either 1.0 mL H_2O_2 solution was added to the culture every 5 minutes or aseptic air was blown into the flask at 100 mL/min. During the dissolution test, the culture was incubated at 30 °C and mixed at 110 rpm.

C. Electrochemical Measurements

In order to investigate the electrochemical behavior of Au, the rest potential of Au in the culture medium was measured using a potentiostat and a function generator. The Au plate (purity 99.99 pct), Pt wire, and Ag/AgCl were used as a working electrode, a counter electrode, and a standard electrode, respectively. The Au plate and Pt wire surfaces were polished using emery paper and finished with 1- μm diamond powder. The working electrodes were encapsulated in epoxy resin except for a 1.0 cm^2 surface area at one side. The solution was stirred and maintained at 30 °C. Figure 1 presents a schematic diagram of the electrochemical experiment.

D. Analysis

Bacterial growth was monitored by plate counts on YP agar medium (YP medium with agar, 15 g). Viable suspended cells were counted using the drop plate method with serial dilution on YP medium. Plates were incubated for 24 hours at 37 °C.

Total cyanide concentration was analyzed colorimetrically at 520 nm using the picric acid colorimetric method. The Au concentration was analyzed by atomic absorption analysis. The dissolved oxygen concentration was measured with a dissolved oxygen sensor connected to a handheld dissolved oxygen meter.

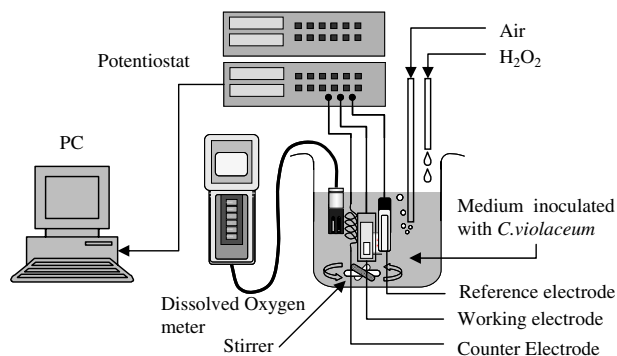


Fig. 1—Schematic diagram of the electrochemical experiment.

III. RESULTS AND DISCUSSION

A. Effects of H_2O_2 Addition on Dissolved Oxygen Concentration during the Growth of *C. violaceum*

Figure 2(a) shows the change in the *C. violaceum* cell population, while Figure 2(b) shows the cyanide and dissolved oxygen concentrations during the growth of the bacteria for up to 120 hours. The *C. violaceum* cell population rapidly increased from 2.0×10^7 to 2.0×10^9 cells/mL during the first 24 hours, after which the population stabilized, while the cyanide concentration rapidly increased from 0 to 0.55 mmol/L in the first 24 hours, peaked (0.7 mmol/L) at 48 hours, and then decreased. Two phases are evident from these results: *C. violaceum* rapidly produces cyanide in the growth phase and gradually decreases cyanide production in stationary phase.

In contrast, dissolved oxygen concentration rapidly decreased in the growth phase (0 to 48 hours) and remained low (0.05 mmol/L) in the stationary phase. Based on the dissolved oxygen concentration, it is clear that *C. violaceum* consumes dissolved oxygen for bacterial respiration during the growth and stationary

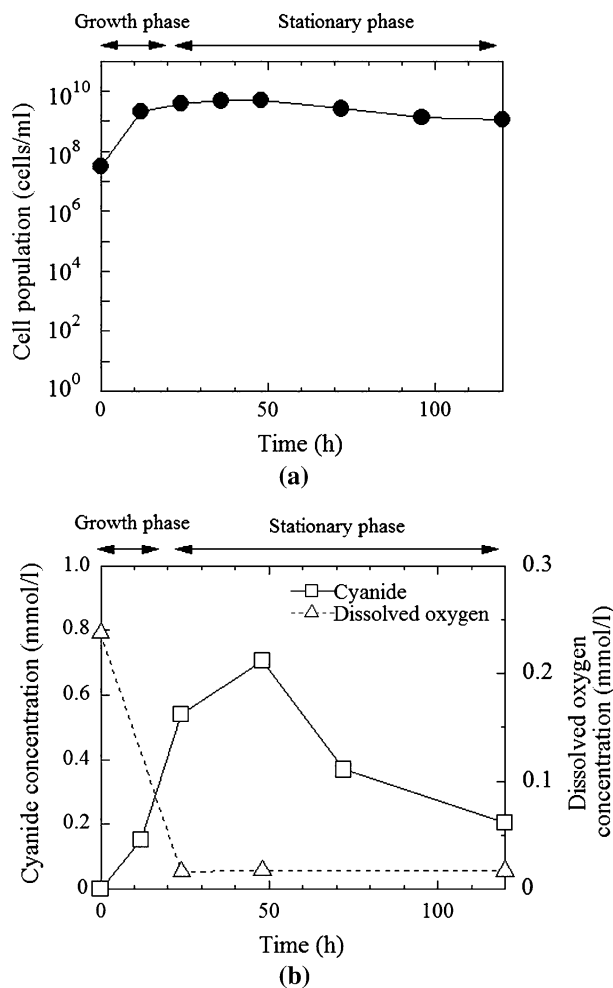


Fig. 2—Cyanide production by *C. violaceum*: (a) cell population of *C. violaceum* (●) in the culture; and (b) cyanide concentration (□) and dissolved oxygen concentration (Δ) in the culture medium.

phases.^[19] This decrease inhibits the cathode reaction and may decrease the Au dissolution rate. Aeration increases both dissolved oxygen concentration and the Au dissolution rate during the stationary phase,^[10] but does not increase dissolved oxygen concentration during the growth phase when *C. violaceum* rapidly consumes dissolved oxygen. The Au dissolution might be increased by increasing dissolved oxygen during the growth phase, when *C. violaceum* can produce significant cyanide.

H₂O₂ is an efficient oxygen source.^[20] Figure 3 shows the change in dissolved oxygen concentration of a *C. violaceum* culture incubated for 24 hours (from Figure 2) after H₂O₂ addition. Dissolved oxygen concentration increased after H₂O₂ addition, peaking after about 0.05 hours; it then decreased from 0.15 to 0.20 hours after addition. Figure 4 depicts the maximum dissolved oxygen concentration derived from Figure 3. As H₂O₂ concentration increased from 0 to 0.0018 pct, dissolved oxygen concentration increased almost linearly, while the oxygen content remained almost constant at higher H₂O₂ concentration. The bacterial culture frothed when more than 0.01 pct H₂O₂ was added.

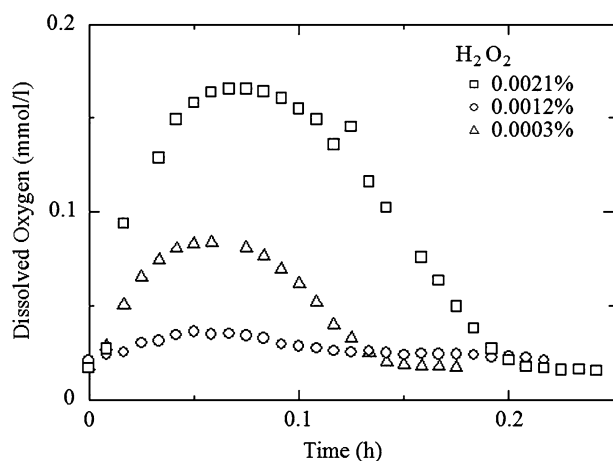


Fig. 3—Changes in dissolved oxygen concentration in *C. violaceum* cultures following incubation for 24 h (from Fig. 2), after the addition of H₂O₂: 0.0003 pct (○), 0.0012 pct (△), and 0.0021 pct (□).

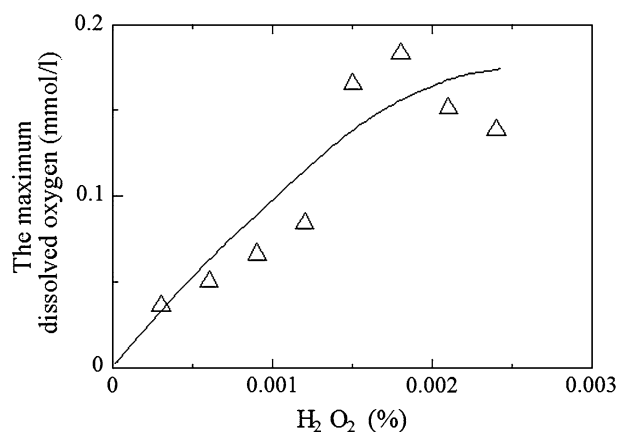


Fig. 4—Maximum dissolved oxygen concentration of the cultures, as calculated from Fig. 3.

The addition of H₂O₂ increased dissolved oxygen concentration even during the growth phase, although the dissolved oxygen level seemed to saturate at 0.23 mmol/L (30 °C). The addition of H₂O₂ can increase dissolved oxygen levels for about 0.15 hours (Figure 3); accordingly, the addition of H₂O₂ every 0.08 hour maintained higher dissolved oxygen concentration.

B. H₂O₂ Tolerance of *C. violaceum*

H₂O₂ is an excellent oxygen source and also acts as an antimicrobial agent.^[21] The H₂O₂ tolerance of *C. violaceum* was investigated by determining the number of bacteria following H₂O₂ addition to the culture. Figure 5 shows the *C. violaceum* cell population in the 24-hour cultures (from Figure 2) after adding H₂O₂ and incubating for 10 minutes. The cell populations were maintained above 10⁹ cells/mL, indicating that *C. violaceum* tolerates H₂O₂ below 0.01 pct H₂O₂, while more than 0.1 pct H₂O₂ is clearly toxic. In this experiment, H₂O₂ tolerance was based on a previous report.^[10]

H₂O₂ at a concentration of 0.0021 pct can increase dissolved oxygen concentration, as shown in Figure 4, without damaging the *C. violaceum* population, because the bacteria can tolerate H₂O₂ up to 0.1 pct. The addition of H₂O₂ appears to be a useful oxygen source for increasing bacterial Au dissolution rates by increasing the dissolved oxygen concentration (cathode reaction) in bacterial cultures.

C. Effects of H₂O₂ on Bacterial Au Dissolution

Figure 6 shows the cyanide concentration (Figure 6(a)), dissolved oxygen concentration (Figure 6(b)), and Au concentration (Figure 6(c)) in *C. violaceum* cultures with added H₂O₂, with and without aeration. The cyanide concentration increased almost linearly over 27 hours, reaching a concentration of 2.3 mmol/L. The addition of H₂O₂ increased the dissolved oxygen concentration above 0.1 mmol/L throughout the experiment, while aeration increased dissolved oxygen concentration to 0.1 mmol/L only after 27 hours. Without the addition of

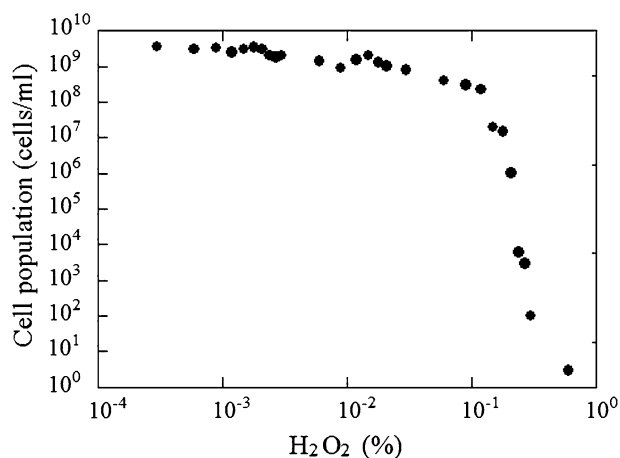


Fig. 5—*C. violaceum* cell population in 24-h cultures (Fig. 2) after the addition of H₂O₂ and incubation for 10 min.

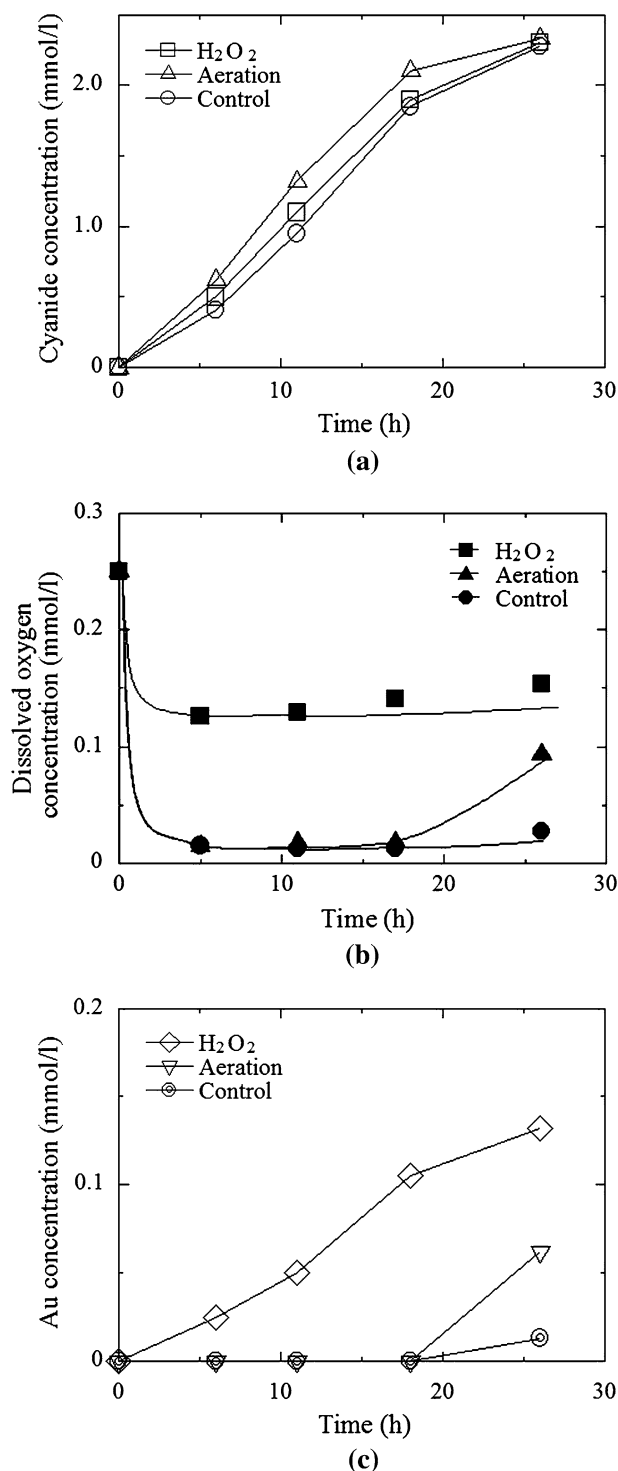


Fig. 6—Gold dissolution in cultures with added Au powder and portionwise addition of hydrogen peroxide, with and without aeration. (a) Cyanide concentration in the culture medium with H_2O_2 (\square), with (Δ) and without (\circ) aeration. (b) Dissolved oxygen concentration in the culture medium with H_2O_2 (\blacksquare), with (\blacktriangle) and without (\bullet) aeration. (c) Au concentration in the culture medium with H_2O_2 (\diamond), with (∇) and without (\odot) aeration.

H_2O_2 or aeration, dissolved oxygen concentration was consistently less than 0.04 mmol/L. The addition of H_2O_2 accelerated Au dissolution, resulting in 0.13 mmol/L dissolved Au after 27 hours, while concentrations of only

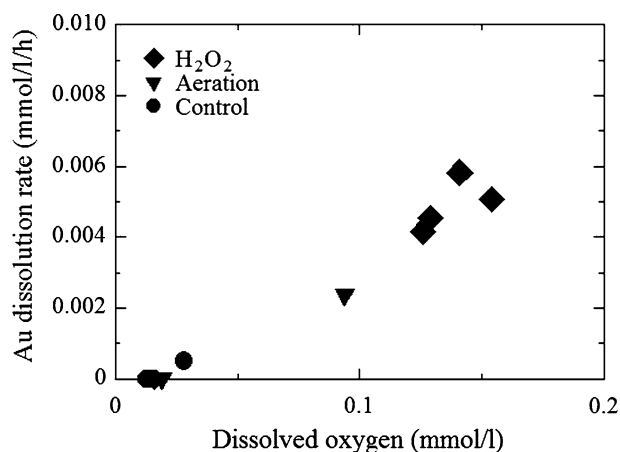


Fig. 7—Effects of dissolved oxygen concentration on the Au dissolution rate (Fig. 5(c)).

0.06 and 0.02 mmol/L dissolved Au were achieved with and without aeration after 27 hours, respectively.

Figure 7 plots the Au dissolution rate (taken from Figure 6(c)) and dissolved oxygen concentration (taken from Figure 6(b)) in bacterial cultures without aeration, with aeration, and upon addition of H_2O_2 . As the plots show a linear relationship, it is clear that increased dissolved oxygen enhances the Au dissolution rate. As indicated in Figure 6, the highest dissolution rate was obtained in H_2O_2 -treated cultures with maximum dissolved oxygen. H_2O_2 addition was effective in enhancing Au dissolution by accelerating the cathode reaction by increasing the dissolved oxygen level in bacterial cultures. Accordingly, the low Au dissolution rate observed during the growth phase is due to the process being severely suppressed by the lack of dissolved oxygen.

D. Electrochemical Measurement

Figure 8(a) shows the changes in the resting potential of Au plate in H_2O_2 -added *C. violaceum* cultures incubated for 24 hours. Figure 8(b) plots the resting potential of Au plate (from Figure 8(a)) as a function of the dissolved oxygen concentration in H_2O_2 -added *C. violaceum* cultures (shown in Figure 3). All data lie on a straight line irrespective of H_2O_2 concentration. This type of change in resting potential is called Nernstian-type change^[22,23] and indicates that the reaction is controlled by only the cathode reaction. In fact, the cyanide concentration of the culture was constant before and after H_2O_2 addition.

Figure 9 details the changes in the resting potential and the current density of Au plate in the *C. violaceum* culture. The Au dissolution increases with increasing charge current density. To enhance Au dissolution, both the anode and cathode reactions must be accelerated by increasing cyanide (line shift from e to d) and dissolved oxygen (line shift from a to c) concentrations. During the growth phase, the anode reaction is accelerated (line d) but the cathode reaction is inhibited (line a) due to consumption of oxygen by bacterial respiration, while *C. violaceum* can produce high concentrations of cyanide

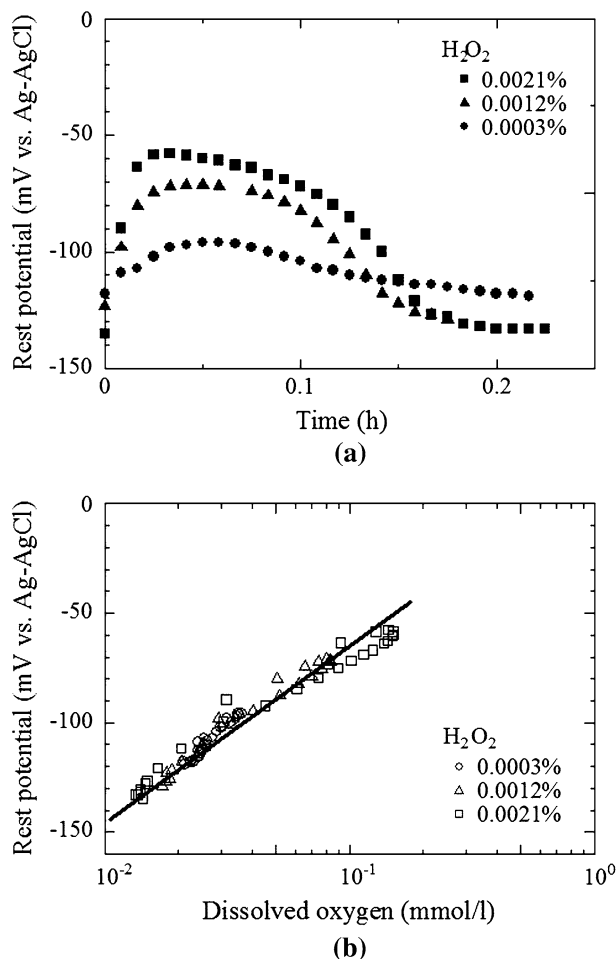


Fig. 8—(a) Rest potential of Au plate in the culture medium in which *C. violaceum* was incubated for 24 h (Fig. 3(a)) after addition of 0.0003 pct (●), 0.0012 pct (▲), and 0.0021 pct (□) hydrogen peroxide. (b) Effects of dissolved oxygen concentration on resting potential (Fig. 7(a)).

despite the low concentration of dissolved oxygen. Accordingly, the electrochemical reaction during the growth phase can be expressed by the point M. In contrast, during the stationary phase, cyanide concentration decreases (line e) and dissolved oxygen concentration remains constant (line a), while *C. violaceum* decomposes cyanide and consumes dissolved oxygen by bacterial respiration. Aeration did not increase dissolved oxygen concentration during the growth phase due to rapid consumption by bacterial respiration. The reaction of the stationary phase was maintained at point M', but the increased dissolved oxygen concentration shifts the variation point from M' to P. Accordingly, the Au dissolution rate increased during the stationary phase compared with that of the growth phase, as shown in Figure 6(c). The addition of H_2O_2 increased dissolved oxygen concentration even during the growth phase, resulting in increased Au dissolution rate, as shown in Figures 6(b) and (c). The increase in the resting potential of Au plate in the bacterial culture by the addition of H_2O_2 in Figure 8(b) represents the increase in the resting potential from point M to N in Figure 9. Therefore, the present study clarified that H_2O_2 is an effective oxygen

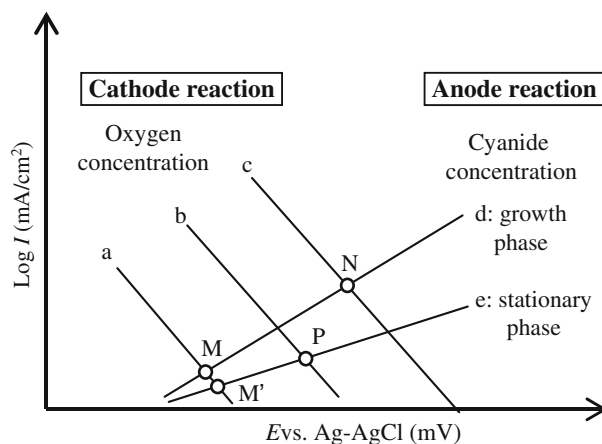


Fig. 9—Change in the resting potential of Au on biological gold leaching. Lines a, b, and c indicate the cathode curves for the control, upon aeration, and upon addition of H_2O_2 to the bacterial cultures, respectively. Lines d and e indicate the anodic curves for the growth and stationary phases, respectively.

source and that bacterial dissolution of Au during the growth phase is controlled by the cathode reaction.

IV. CONCLUSIONS

Chromobacterium violaceum produces cyanide and was used to dissolve Au. To increase Au dissolution during the growth phase, when *C. violaceum* rapidly consumes dissolved oxygen by respiration, the effects of aeration and addition of H_2O_2 to the bacterial culture on the Au dissolution rate were examined. The resting potential in the bacterial culture was measured to investigate the cathode reaction and the effect of increasing dissolved oxygen concentration on Au dissolution. Based on the results presented in this article, the following conclusions can be drawn.

1. During the growth phase, *C. violaceum* produces a higher concentration of cyanide and rapidly consumes dissolved oxygen by bacterial respiration.
2. Addition of H_2O_2 to the bacterial culture increases dissolved oxygen concentration even during the growth phase and increases the Au dissolution rate, while aeration does not increase the dissolved oxygen concentration during the growth phase due to rapid bacterial respiration.
3. *C. violaceum* tolerates H_2O_2 up to 0.01 pct, and this concentration is effective in increasing the Au dissolution rate during the growth phase.
4. The electrochemical study clarified that the Au dissolution reaction in bacterial cultures is controlled by the cathode reaction due to severe oxygen shortage arising from bacterial respiration during the growth phase.

REFERENCES

1. T. Fujita and W.T. Yen: *Symp. on Actions for Environmental Concern in Electronics Assembly*, Tokyo and Osaka (2 days), Japan, 2001, pp. 118–27. Available at: <http://www.soc.nii.ac.jp/jws/research/micro/aecea/aecea%207.html> (the site is Japanese only).

2. D. Norman and R. Raftery: *Wash. Geol.*, 1995, vol. 23 (1), pp. 30–41.
3. G. Olson: *FEMS Microbiol. Lett.*, 1994, vol. 119, pp. 1–6.
4. M. Moss and C. Ryall: *The Prokaryotes*, 2nd ed., Springer-Verlag, New York, NY, 1981, pp. 1356–64.
5. R. Michaels and W. Corpe: *J. Bacteriol.*, 1965, vol. 89 (1), pp. 106–12.
6. A.M. Macadam and C.J. Knowles: *Biochem. Biophys. Acta*, 1984, vol. 786, pp. 123–32.
7. P.B. Rodgers: *J. Gen. Microbiol.*, 1978, vol. 108, pp. 261–67.
8. P.B. Rodgers: *J. Gen. Microbiol.*, 1982, vol. 128, pp. 2983–89.
9. M.A. Faramarzia, M. Stagarsa, E. Pensinib, W. Krebsb, and H. Brandl: *J. Biotech.*, 2004, vol. 113 (1–3), pp. 321–26.
10. Y. Kita, H. Nishikawa, and T. Takemoto: *J. Biotechnol.*, 2006, vol. 124, pp. 545–51.
11. H. Hedley and H. Tabachnick: *Mineral Dressing Notes*, American Cyanamid Co., 1958, no. 23.
12. D.H. Rubisov, V.G. Papangelakis, and P.D. Kondos: *Can. Inst. Min. Metall.*, 1996, vol. 35 (4), pp. 353–61.
13. P. Ling, V.G. Papangelakis, S.A. Argyropoulos, and P.D. Kondos: *Can. Metall. Q.*, 1996, vol. 35 (3), pp. 225–34.
14. L.R.P. de Andrade Lima and D. Hodouin: *Hydrometallurgy*, 2005, vol. 79, pp. 121–37.
15. K. Haque: *CIM Bull.*, 1992, vol. 85 (963), pp. 31–38.
16. A.R. Heath and J.A. Rumball: *Min. Eng.*, 1998, vol. 11, pp. 999–1010.
17. D.K. Peter and F.G. Wesley: *Can. Metall. Q.*, 1995, vol. 35, pp. 39–45.
18. M.E. Wadsworth: *Int. J. Miner. Process.*, 1999, vol. 58, pp. 351–68.
19. S. Foucher, F. Battaglia-Brunet, P. d'Hugues, M. Clarens, J.J. Godon, and D. Morin: *Hydrometallurgy*, 2003, vol. 71 (1–2), pp. 5–12.
20. L. Guzman, M. Segarra, J.M. Chimenos, M.A. Fernandez, and F. Espiell: *Hydrometallurgy*, 1999, vol. 52, pp. 21–35.
21. G. Cerny: *Packag. Technol. Sci.*, 1992, vol. 5, pp. 77–81.
22. N. Kallay, T. Preocanin, and T. Ivsic: *J. Coll. Interface Sci.*, 2007, vol. 309, pp. 21–27.
23. A.K. Singh, A.K. Jain, and S. Mehtab: *Anal. Chem. Acta*, 2007, vol. 597, pp. 322–30.