

Title	Ultrasonic pole figure for the texture of aluminum alloy
Author(s)	Hirao, M.; Hara, N.
Citation	Applied Physics Letters. 50(20) P.1411-P.1412
Issue Date	1987-05-18
Text Version	publisher
URL	<a href="http://hdl.handle.net/11094/2991">http://hdl.handle.net/11094/2991</a>
DOI	
rights	
Note	

*Osaka University Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

Osaka University

## Ultrasonic pole figure for the texture of an aluminum alloy

M. Hirao and N. Hara

Citation: *Appl. Phys. Lett.* **50**, 1411 (1987); doi: 10.1063/1.97837

View online: <http://dx.doi.org/10.1063/1.97837>

View Table of Contents: <http://apl.aip.org/resource/1/APPLAB/v50/i20>

Published by the [American Institute of Physics](http://www.aip.org/).

---

### Related Articles

Simultaneous self-collimation of fundamental and second-harmonic in sonic crystals

*Appl. Phys. Lett.* **99**, 151905 (2011)

Three-dimensional acoustic wavefront imaging in anisotropic systems by picosecond acoustics

*J. Appl. Phys.* **109**, 033507 (2011)

Acoustic reflectivity goniometry of bounded ultrasonic pulses: Experimental verification of numerical models

*J. Appl. Phys.* **104**, 064914 (2008)

Rayleigh wave interaction with surface-breaking cracks

*J. Appl. Phys.* **101**, 064906 (2007)

Ultrasonic attenuation in a chain crystal containing resonantly scattering defects

*Low Temp. Phys.* **32**, 270 (2006)

---

### Additional information on *Appl. Phys. Lett.*

Journal Homepage: <http://apl.aip.org/>

Journal Information: [http://apl.aip.org/about/about\\_the\\_journal](http://apl.aip.org/about/about_the_journal)

Top downloads: [http://apl.aip.org/features/most\\_downloaded](http://apl.aip.org/features/most_downloaded)

Information for Authors: <http://apl.aip.org/authors>

### ADVERTISEMENT

The logo for AIP Advances features the text 'AIP Advances' in a blue and green font. Above the text is a decorative graphic of several orange and yellow circles of varying sizes, arranged in a curved path that suggests motion or a signal. The background of the advertisement is a light green color with a darker green vertical stripe on the right side.

*Submit Now*

**Explore AIP's new  
open-access journal**

- **Article-level metrics  
now available**
- **Join the conversation!  
Rate & comment on articles**

# Ultrasonic pole figure for the texture of aluminum alloy

M. Hirao and N. Hara

Faculty of Engineering Science, Osaka University, Toyonaka, Osaka 560, Japan

(Received 5 February 1987; accepted for publication 25 March 1987)

An approximate method is proposed to calculate the pole figure diagrams based on the elastic anisotropy measured by ultrasonic velocity experiments. An example is taken from the surface texture of rolled plates of aluminum alloy 7075-T651, for which the angular dependence of the Rayleigh wave is measured in the rolling plane and analyzed to obtain the expansion coefficients of orientation distribution function. The ultrasonic pole figures are favorably compared with the conventional x-ray pole figures, both demonstrating a single texture centered over (001)[110] orientation.

When a polycrystalline metal plastically deforms, the crystallites are rotated with the crystal slip and their certain crystallographic orientation tends to be partially aligned depending on the flow geometry and magnitude. This partial alignment is called preferred orientation or texture. Most polycrystalline materials as a whole exhibit weak elastic anisotropy due to the texture. The relationship between the texture and the elastic anisotropy has been established by introducing the orientation distribution function (ODF) which gives the probability of crystallite orientation with respect to the sample axes.<sup>1</sup> The texture slightly modifies the second-order elastic constants through three independent ODF coefficients,  $w_{4m0}$  ( $m = 0, 2, 4$ ), in the case of cubic metals. Therefore, it is now possible to infer the texture from the measurements of anisotropy in the ultrasonic velocities.<sup>2,3</sup> The ultrasonic method is basically incapable of such detailed texture characterization as the x-ray and neutron diffraction methods can do, but it makes a nondestructive and easy inspection possible.

This letter focuses on the surface texture of rolled plates of aluminum alloy 7075-T651. The surface texture can be most conveniently examined using the Rayleigh wave, which penetrates into the depth about a wavelength from the surface. Sayers<sup>4</sup> and Delsanto *et al.*<sup>5,6</sup> derived the formula relating the propagation velocity  $V_r$  and the ODF coefficients in the first-order approximation. When the Rayleigh wave propagates at an angle  $\theta$  to the rolling direction in the plate surface,  $V_r$  varies as

$$V_r(\theta) - V_{r0} = \frac{c}{\rho V_{r0}} (r_0 w_{400} + r_2 w_{420} \cos 2\theta + r_4 w_{440} \cos 4\theta), \quad (1)$$

where  $V_{r0}$  is the velocity in the isotropic case ( $w_{4m0} = 0$ ),  $\rho$  the density, and  $c$  the anisotropy factor of the crystal. The coefficients  $r_i$  depend only on the Poisson ratio: for aluminum,  $r_0 = -1.29$ ,  $r_2 = 2.45$ , and  $r_4 = 0.39$ . It is seen then that the  $\cos 2\theta$  term has the largest influence on the variation of  $V_r$ . This is the case for most solids.

A sing-around experiment was conducted for  $V_r$ 's angular variation. Both ends of an acrylic bar were cut to the critical angle for the Rayleigh wave generation and detection, where two piezoelectric transducers (PZT's) were mounted. The center frequency was 5 MHz and the gauge

distance was 131 mm. The bar was rotated around its center at every  $5^\circ$  by a stepping motor operated with a personal computer, which was also used for data acquisition and calculation. Four test plates are sized  $200 \times 300 \text{ mm}^2$  and of thickness ranging from 25.5 to 12.7 mm (TP 71 to 74).

Typical results of the measurements are shown in Fig. 1 for a quadrant of each plate. All the data were analyzed to obtain the coefficients of constant,  $\cos 2\theta$ , and  $\cos 4\theta$  components. The curve, which is reconstructed using these three components, is drawn in the figure together with the experimental results. The good agreement with the plots indicates that the measured angular variation of  $V_r$  can be well interpreted with formula (1). The ODF's coefficients are then determined from the Fourier coefficients as  $w_{420} = -0.0010$  and  $w_{440} = -0.0051$  for TP 71. These values were reproducible within 0.00011 for  $w_{420}$  and 0.00055 for  $w_{440}$ .

We need  $w_{400}$  and the higher order coefficients of ODF to calculate the pole figures, but they cannot be determined from the ultrasonic experiments.<sup>1-3</sup> We here propose a procedure for approximating  $w_{400}$  and the higher order coefficients, which is applicable for a single texture. The previous work<sup>2</sup> revealed that the surface texture of 7075-T651 aluminum rolled plates is best described by an ideal orientation, (001)[110]. The delta-function representation of ODF<sup>7</sup> for (001)[110] texture gives

$$w_{400} = 0.0313, \quad w_{420} = 0, \quad w_{440} = -0.0184, \quad \text{and} \\ w_{600} = 0.0081, \quad w_{620} = 0, \quad w_{640} = 0.0151, \quad w_{660} = 0. \quad (2)$$

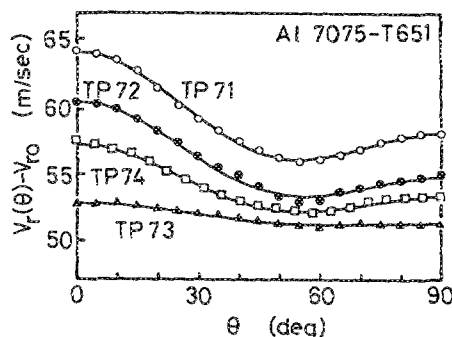


FIG. 1. Raw data and fitted curves for angular dependence of Rayleigh wave velocity for rolled aluminum alloy 7075-T651. Angle  $\theta$  is measured from the rolling direction.

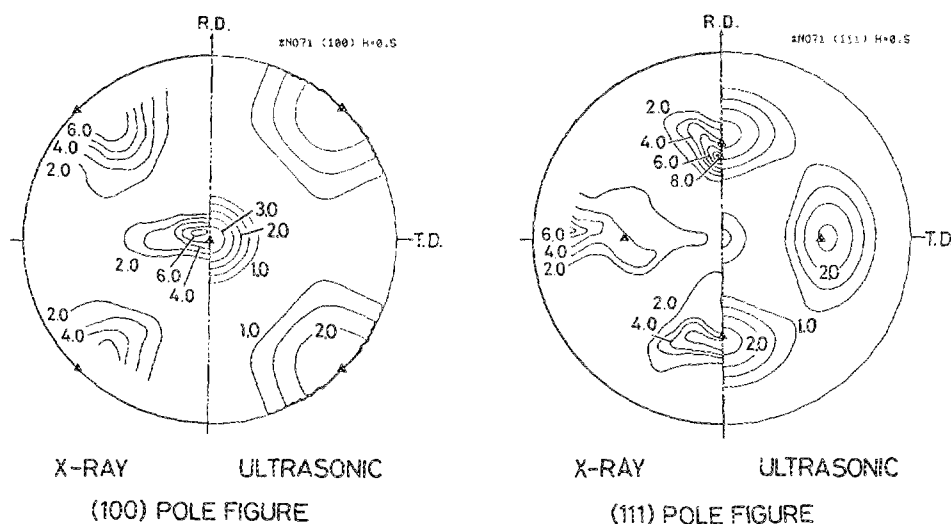


FIG. 2. Comparison of ultrasonic pole figures to x-ray pole figures (TP 71).  $\blacktriangle$ , (001)[110]. The ultrasonic pole figures [ $4\pi q(\zeta, \eta)$  of Eq. (3)] involve terms with the fourth- and sixth-order ODF coefficients.

These ODF coefficients apply exactly to the polycrystalline metals with all the crystallites aligned in (001)[110] orientation. We assume that the ratio of measured  $w_{440}$  to thus determined  $w_{440}$  indicates the "intensity" of that texture. By multiplying the  $w$ 's in Eq. (2) with this intensity, we may

obtain the approximation for the ODF coefficients that cannot be measured using ultrasonics. They are  $w_{400} = 0.0094$ ,  $w_{600} = 0.0024$ ,  $w_{640} = 0.0045$ , and  $w_{620} = w_{660} = 0$  for TP 71, for example. The ultrasonic pole figure is calculated by substituting them in addition to measured  $w_{420}$  and  $w_{440}$  into

$$q(\zeta, \eta) = 1/4\pi + S_4 [P_4^0(\zeta)w_{400} + P_4^2(\zeta)w_{420} \cos 2\eta + P_4^4(\zeta)w_{440} \cos 4\eta] + S_6 [P_6^0(\zeta)w_{600} + P_6^2(\zeta)w_{620} \cos 2\eta + P_6^4(\zeta)w_{640} \cos 4\eta + P_6^6(\zeta)w_{660} \cos 6\eta]. \quad (3)$$

where  $P_l^m(\zeta)$  denotes the normalized associated Legendre function of  $\zeta = \cos \chi$ ,  $\chi$  and  $\eta$  being, respectively, the polar and azimuthal angles with respect to the samples axes.  $w_{420}$  is zero in Eq. (2) but we use the measured  $w_{420}$  in Eq. (3). The factors  $S_4$  and  $S_6$  take the following values:

$S_4 = S_6 = 2\pi$  for (100) pole figure

$S_4 = -\pi/2$  and  $S_6 = -13\pi/4$  for (110) pole figure

$S_4 = -4\pi/3$  and  $S_6 = 32\pi/9$  for (111) pole figure.

In Fig. 2 the (100) and (111) ultrasonic pole figures are compared with those measured by the x-ray diffractometer (Schulz reflection method). Favorable correspondence suggests that the ultrasonic pole figure would be a useful texture indicator.

The angular variation of the surface skimming SH wave has been separately measured with the same test plates for evaluating  $w_{440}$ .<sup>2</sup> The experiments were made using 2 MHz PZT elements. The difference of  $w_{440}$  measured by Rayleigh

wave and by SH wave is not negligible, but as small as that observed by Clark *et al.*<sup>8</sup> or less. We also found that this difference tends to increase as the plate thickness decreases so far as the four plates used are concerned. This observation suggests that the texture inhomogeneity through thickness would be the major cause of the difference in the values of  $w_{440}$ .

<sup>1</sup>C. M. Sayers, *J. Phys. D* **15**, 2157 (1982).

<sup>2</sup>M. Hirao, K. Aoki, and H. Fukuoka, *J. Acoust. Soc. Am.* (in press).

<sup>3</sup>S. S. Lee, J. F. Smith, and R. B. Thompson, Proceedings of the Symposium on Inter-Relationship of Metallurgical Structure and Formability, to be published from AIME.

<sup>4</sup>C. M. Sayers, *Proc. R. Soc. London Ser. A* **400**, 175 (1985).

<sup>5</sup>P. P. Delsanto and A. V. Clark, Jr., *J. Acoust. Soc. Am.* (in press).

<sup>6</sup>P. P. Delsanto, R. B. Mignogna, and A. V. Clark, Jr., Review of Progress in Quantitative NDE (to be published).

<sup>7</sup>P. R. Morris, *Int. J. Engr. Sci.* **8**, 49 (1970).

<sup>8</sup>A. V. Clark, Jr., A. Govada, R. B. Thompson, J. F. Smith, G. V. Blessing, P. P. Delsanto, and R. B. Mignogna, Review of Progress of Quantitative NDE (to be published).