

Title	Effect of spin-orbit impurity scattering on the Knight shift in BCS superconductors : Reanalysis of Anderson's classic paper
Author(s)	Miyake, K. ; Asayama, K.
Citation	Physical Review B. 62(17) P.11363-P.11364
Issue Date	2000-11-01
Text Version	publisher
URL	http://hdl.handle.net/11094/3234
DOI	
rights	Miyake, K., Asayama, K., Physical Review B, 62, 17, 11363-1364, 2000-11-01. "Copyright (2000) by the American Physical Society."
Note	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

Osaka University

Effect of spin-orbit impurity scattering on the Knight shift in BCS superconductors: Reanalysis of Anderson's classic paper

K. Miyake and K. Asayama

Division of Materials Physics, Department of Physical Science, Graduate School of Engineering Science, Osaka University, Toyonaka, Osaka 560-8531, Japan

(Received 16 June 2000)

We present the result of a numerical reanalysis of the classic paper of Anderson discussing the effect of spin-orbit scattering on the Knight shift in BCS conventional superconductors. The numerical evaluation of Anderson's relation between the Knight shift and the scattering rates improves on the approximate numerical factors given by Anderson.

The aim of this Brief Report is very simple. We have reanalyzed numerically the formula for the effect of impurity scattering with spin-orbit coupling on the Knight shift given by Anderson in the classic paper of this field,¹ and realized that the numerical calculations performed about four decades ago might be replaced by an updated version.

Skipping the derivations, we present the formula for the spin susceptibility given by Eq. (8) in Ref. 1:

$$\frac{\chi_s}{\chi_n} = \frac{\int d\epsilon \int d\epsilon' f((\epsilon - \epsilon')\tau\hbar^{-1}) [u(\epsilon)v(\epsilon') - v(\epsilon)u(\epsilon')]^2 (E + E')^{-1}}{\int d\epsilon \int d\epsilon' \lim_{\Delta \rightarrow 0} f((\epsilon - \epsilon')\tau\hbar^{-1}) [u(\epsilon)v(\epsilon') - v(\epsilon)u(\epsilon')]^2 (E + E')^{-1}}, \quad (1)$$

where τ is the lifetime of the quasiparticle due to spin-orbit scattering from impurities or the boundary of the system, the coefficients u and v are defined as

$$u(\epsilon) = \frac{1}{\sqrt{2}} \left(1 + \frac{\epsilon}{E} \right)^{1/2}, \quad (2)$$

$$v(\epsilon) = \frac{1}{\sqrt{2}} \left(1 - \frac{\epsilon}{E} \right)^{1/2}, \quad (3)$$

where ϵ is the energy level of a one-particle state in the normal state measured from the chemical potential, and the corresponding one-particle excitation energies E and E' in the superconducting state are defined in terms of the superconducting gap Δ as usual:

$$E = \sqrt{\epsilon^2 + \Delta^2} \quad \text{and} \quad E' = \sqrt{\epsilon'^2 + \Delta^2}. \quad (4)$$

The relaxation function f in Eq. (1) is assumed to be given by the Lorentzian form

$$f(x) = \frac{1}{1 + x^2}. \quad (5)$$

In the above expressions, ϵ_0 in Ref. 1 has been replaced by Δ , a much more familiar notation now.

Using the definitions (2), (3), and (4), the coherence factor $[u(\epsilon)v(\epsilon') - v(\epsilon)u(\epsilon')]^2$ is calculated in the standard way:

$$[u(\epsilon)v(\epsilon') - v(\epsilon)u(\epsilon')]^2 = \frac{EE' - \epsilon\epsilon' - \Delta^2}{EE'}. \quad (6)$$

Then, the expression for χ_s/χ_n is given in the following form:

$$\frac{\chi_s}{\chi_n} = \frac{1}{2\pi} \int_{-\infty}^{+\infty} dx \int_{-\infty}^{+\infty} dx' \frac{1}{1 + (x - x')^2} \frac{\sqrt{x^2 + (\Delta\tau\hbar^{-1})^2} \sqrt{x'^2 + (\Delta\tau\hbar^{-1})^2} - xx' - (\Delta\tau\hbar^{-1})^2}{\sqrt{x^2 + (\Delta\tau\hbar^{-1})^2} \sqrt{x'^2 + (\Delta\tau\hbar^{-1})^2} [\sqrt{x^2 + (\Delta\tau\hbar^{-1})^2} + \sqrt{x'^2 + (\Delta\tau\hbar^{-1})^2}]}, \quad (7)$$

where $x = \epsilon\tau\hbar^{-1}$ and $x' = \epsilon'\tau\hbar^{-1}$. It is verified easily by analytic calculations that the double integration of Eq. (7) results in 2π if $\Delta\tau\hbar^{-1} = 0$, giving $\chi_s/\chi_n = 1$ as expected.

We have performed the double integration of Eq. (7) numerically by means of the trapezoidal rule dividing each region $-1000 < x(x') < -1$, $-1 < x(x') < 1$, and $1 < x(x')$

< 1000 by 10 000 meshes with equal width in each region. The result is shown in Fig. 1 in which the squares represent χ_s/χ_n for $\Delta\tau\hbar^{-1} < 1$ and the circles that for $\Delta\tau\hbar^{-1} > 1$, respectively. It is remarked that these numerically obtained points can be fitted well by a rather simple expression as seen in Fig. 1:

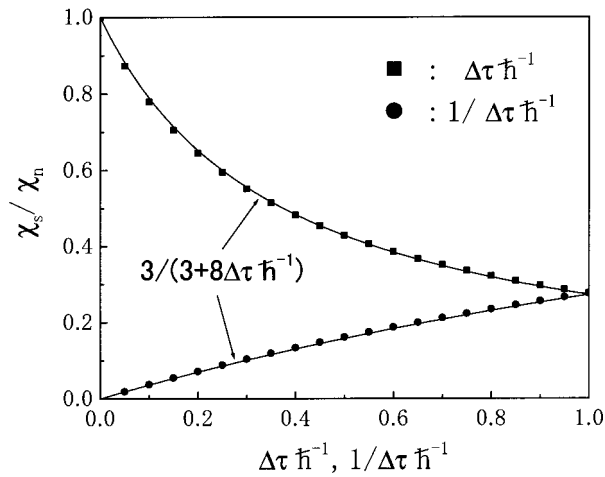


FIG. 1. Knight shift vs impurity scattering rates associated with spin-orbit coupling.

$$\frac{\chi_s}{\chi_n} \approx \frac{3}{3 + 8\Delta\tau\hbar^{-1}}. \quad (8)$$

This behaves in the two limits $\Delta\tau\hbar^{-1} \ll 1$ and $\Delta\tau\hbar^{-1} \gg 1$ as follows:

$$\frac{\chi_s}{\chi_n} \approx \begin{cases} 1 - \frac{8}{3}\Delta\tau\hbar^{-1}, & \Delta\tau\hbar^{-1} \ll 1, \\ \frac{3}{8}(\Delta\tau\hbar^{-1})^{-1}, & \Delta\tau\hbar^{-1} \gg 1. \end{cases} \quad (9)$$

The numerical coefficients in these limiting forms are considerably different from Eqs. (9) and (10) of Ref. 1 in which those are given as

$$\frac{\chi_s}{\chi_n} \approx \begin{cases} 1 - 2\Delta\tau\hbar^{-1}, & \Delta\tau\hbar^{-1} \ll 1, \\ \frac{1}{6}(\Delta\tau\hbar^{-1})^{-1}, & \Delta\tau\hbar^{-1} \gg 1. \end{cases} \quad (10)$$

In conclusion, we have reanalyzed the formula of Anderson for the Knight shift of BCS superconductors subject to spin-orbit scattering due to impurities, and obtained a technically exact result (8) which may give a new clue for analysis of the Knight shift experiments of BCS superconductors.

One of the authors (K.M.) acknowledges J. Flouquet and his colleagues for hospitality at CEA-Grenoble where the last stage of this work was performed. This work was supported in part by a Grant-in-Aid for COE Research (10CE2004) of Monbusho, the Ministry of Education, Science, Sports and Culture of Japan.

¹P.W. Anderson, Phys. Rev. Lett. 3, 325 (1959).