

Title	Effect of Beam Oscillation on Electron Beam Melting
Author(s)	Tomie, Michio; Abe, Nobuyuki; Hano, Motomu et al.
Citation	Transactions of JWRI. 1989, 18(2), p. 303-304
Version Type	VoR
URL	<a href="https://doi.org/10.18910/5350">https://doi.org/10.18910/5350</a>
rights	
Note	

*Osaka University Knowledge Archive : OUKA*

<https://ir.library.osaka-u.ac.jp/>

Osaka University

# Effect of Beam Oscillation on Electron Beam Melting†

Michio TOMIE\*, Nobuyuki ABE\*, Motomu HANO\*\* and Teteumi SHIRABE\*\*

KEY WORDS : (Beam Oscillation) (Electron Beam) (Melting)

As superior properties of the electron beam heat source, it is well known that the scanning path of beam can be controlled at high speed and in high accuracy by use of electromagnetic deflection coil, and this has become an effective means of material surface treatment.

In this report, the authors tried to check the effect of beam oscillation on the depth of melting and melted surface conditions by using a prototype of beam oscillation pattern input system.

For irradiation of beam, an electron beam welding apparatus with 30 kW power was used. Figure 1 shows a schematic diagram of the test system in which a beam oscillation pattern is to be put in the computer at discretion and location of beam irradiated on the surface of specimen is moved at various set speeds by magnetic field of deflecting coil. As specimen, aluminium alloy having low melting point was used, which size was  $\phi 30$  mm x 30 mm, and oscillation pattern is as shown in Fig. 2. Beam oscillation parameters are radial wave pattern, radial scanning frequency  $f_R$  and rotational frequency  $f_D$ . Radial beam moving speed is controlled by changing radial wave pattern and frequency  $f_R$ . In this report, rotational frequency  $f_D$  was fixed at 0.1 Hz.

Radial beam moving speed was changed continuously

in radial movement of beam with such three type wave patterns as shown in Fig. 3 to thereby change density distribution of energy applied on the specimen to check melting profiles. Beam irradiation conditions were as follows: acceleration voltage  $V_b = 70$  kV, beam current  $I_b = 20$  mA,  $a_b = 1.0$ , radial frequency  $f_R = 10$  Hz, rotational frequency  $f_D = 0.1$  Hz, beam rotation was one cycle. The specimen was cut off at  $180^\circ$  from the point where beam was started to view the melting profiles on that section. As shown in Fig. 3, Wave Pattern 1 in which radial beam moving speed was constant has uniform melting profile, but Wave Pattern 2 in which beam resided for a time when it moved to two-thirds from the center of specimen shows deeper melting at such location. While, Wave Pattern 3 in which beam moving speed was decreased as beam moved to the periphery shows that melting becomes deeper at such outer areas. Thus, beam moving speed corresponds well to the profile of melting, and so it may be possible to control the melting depth freely by

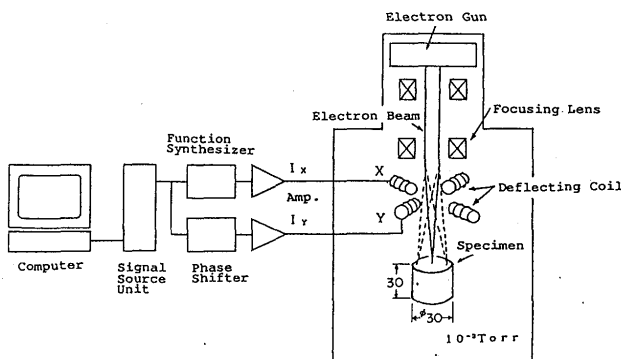


Fig. 1 Schematic Diagram of Test System.

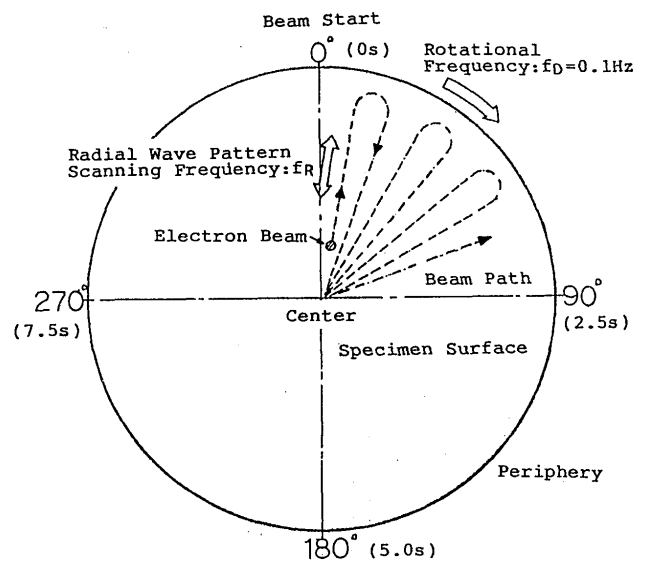


Fig. 2 Beam Oscillation Pattern on the Surface of Specimen.

† Received on October 31, 1989

\* Associate Professor

\*\* Ube Industries, Ltd.

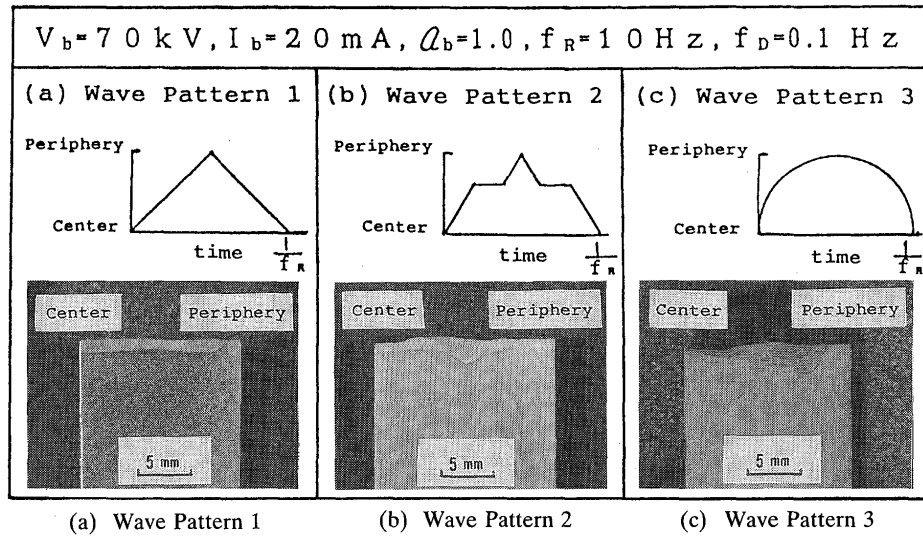


Fig. 3 Relation between Radial Wave Pattern and Melting Profile.

inputting proper wave pattern.

On Wave Pattern 1, which had uniform melting profile, radial frequency  $f_R$  changed to 5 Hz, 10 Hz, and 20 Hz, when melting surfaces were observed. When frequency  $f_R$  was 5 Hz and 10 Hz, the melting surface was substantially flat and smooth, but when it was 20 Hz, the melting surface became disturbed significantly.

On Wave Pattern 1, the beam current was changed at frequency  $f_R = 10 \text{ Hz}$  to determine the melting depth. As shown in Fig. 4, the melting depth was almost unchanged with angles at beam current  $I_b = 30 \text{ mA}$  and less, while the depth became greater as the angle was increased at 40 mA and over. This is considered because the preheat effect by heat transfer becomes noticeable as the beam current is increased and, as a result, the melting depth becomes greater.

The oscillation pattern input system constructed as prototype for testing was found to be able to control the melting depth and melting surface conditions with adequate input oscillation pattern.

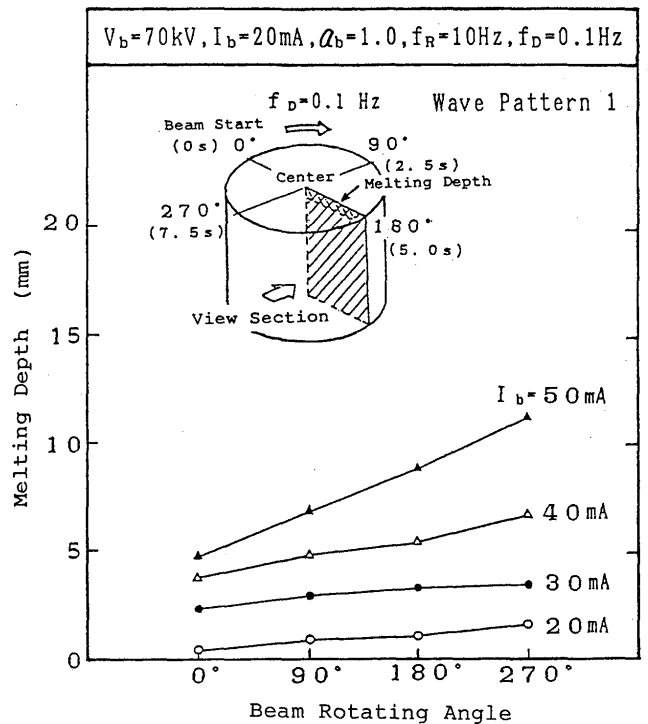


Fig. 4 Relation between Beam Rotating Angle and Melting Depth.