

Title	Ultrasonic Brazing of Alumina to Copper Using Zn-Al-Cu Fillers(Materials, Metallurgy & Weldability)
Author(s)	Naka, Masaaki; Maeda, Michimasa
Citation	Transactions of JWRI. 1991, 20(1), p. 91-96
Version Type	VoR
URL	https://doi.org/10.18910/6364
rights	
Note	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

Osaka University

Ultrasonic Brazing of Alumina to Copper Using Zn-Al-Cu Fillers†

Masaaki NAKA* and Michimasa MAEDA**

Abstract

Ultrasonic Brazing was applied to join to copper using Zn-Al-Cu filler metals containing Al plus Cu content up to 30 mass% where the ratio of Al/Cu is fixed as 3/2. The intensity of ultrasound was 1 kW and 18 kHz. The joining mechanism was investigated by measuring the joining strength and analyzing the microstructure at interface of the joint.

First, Al_2O_3 was metallized by applying ultrasound in Zn-Al-Cu filler bath. Then, the metallized Al_2O_3 was brazed with Cu using the same fillers. The increase in application time of ultrasound and metallizing temperature raises the joining strength of Al_2O_3 /Zn-Al-Cu/Cu joint. The joining strength of Al_2O_3 /Cu joint exhibits the maximum at Al+Cu content of 20 mass% in Zn-Al filler, and lowers with further addition of Al+Cu content.

The application of ultrasound during brazing accelerates the removal of bubbles and the reaction at the interface between alumina and filler metal. This gives rise to wetting of Zn-Al-Cu filler against alumina, and increasing the joining strength of Al_2O_3 /Cu joint.

KEY WORDS: (Ceramic-Metal Joining) (Ceramics) (Alumina) (Copper) (Ultrasonic Brazing) (Joining) (Brazing) (Zinc) (Filler Metal)

1. Introduction

Ceramics are becoming increasing important in engineering application, but their fabrication into useful components frequently requires techniques of joining ceramics to metals. The brazing methods of ceramics to metals are divided into the heat-resistant meals method¹⁾, active filler metals method²⁾, molten aluminum method³⁻⁵⁾, oxide utilizing method^{6,7)}. The thermal stress arisen from the difference of thermal expansion between ceramic and metal affords detrimental effects in ceramic/metal joint after joining. Soft metals which are inserted between ceramics and metals are often used to relax the thermal stress in joints. Although the decrease in joining temperature also reduces the thermal stress in ceramic/metal joints, the wettability of brazing fillers is simultaneously impaired. We have tried hitherto to improve the wettability of fillers by applying the ultrasonic wave to ceramics^{8,9)}.

This work reports, in successive from the previous one^{8,9)}, to improve the brazeability of Zn-Al-Cu filler metals during joining of alumina to copper by applying the ultrasound.

2. Experimental

Materials used were 99.62 mass% Al_2O_3 containing 0.1 mass% SiO_2 and others and tough pitch copper containing 0.03 mass% O. The size of materials was 6 mm in diameter and 4 mm in thickness as shown in Fig. 1. Table 1 gives a series of composition for Zn-Al-Cu filler metals containing the sum of Al plus Cu content up to 30 mass% where the ratio of Al/Cu is fixed as 3/2. Figure 2 shows the process of ultrasonic brazing of ceramics to metal in Zn-Al-Cu filler bath. Alumina were first metallized by applying the ultrasound in Zn-Al-Cu filler bath. The intensity of ultrasound was 1 kW and 18 kHz. The brazing temperature and applying time of ultrasound were 673 to 773 K and 0 to 90 s, respectively. After metallizing alumina, alumina was lapped with copper which was coated with the same filler metal by applying the ultrasound in 3 s.

The joining strength of Al_2O_3 /Cu joints brazed with

Table 1 Chemical composition of Zn-Al-Cu alloys used.

Zn-Al-Cu	Al(mass%)	Cu(mass%)	Zn(mass%)	Liquidus temperature (K)
Zn-6Al-4Cu	6	4	bal.	650
Zn-12Al-8Cu	12	8	bal.	663
Zn-18Al-12Cu	18	12	bal.	675

† Received on May 7, 1991

* Associate Professor

** Associate Professor, Osaka Sangyo University

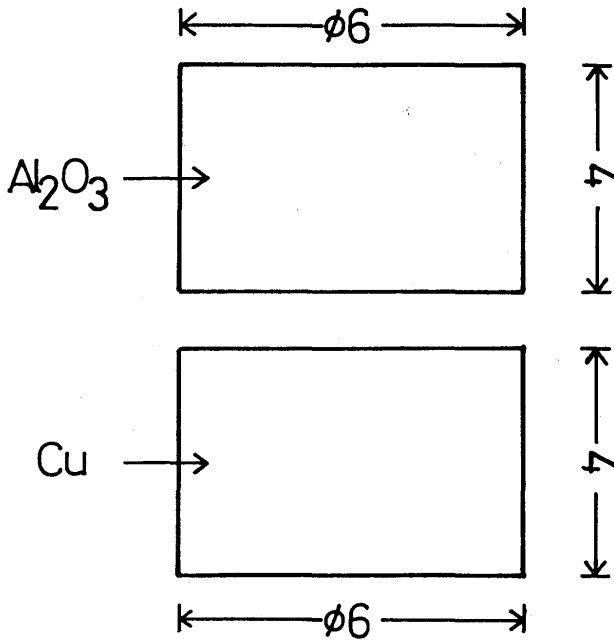


Fig. 1 Specimen size.

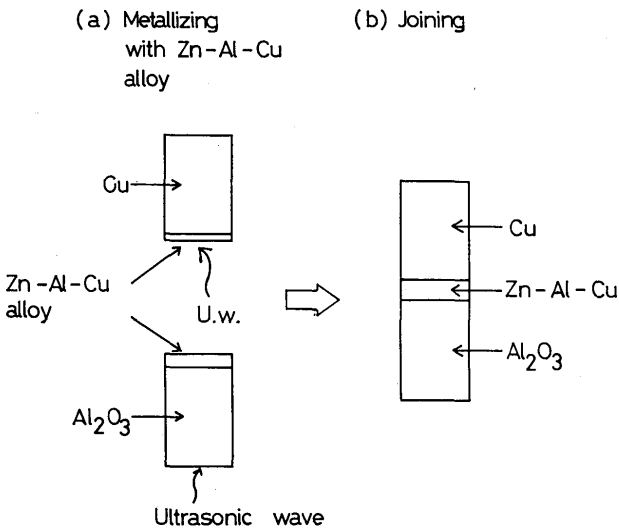


Fig. 2 Process of ultrasonic brazing of ceramics to metal.

Zn-Al filler was evaluated by fracture shear loading using a cross head speed of 1.67×10^{-2} mm/s, and the microstructure was analysed by scanning electron microscopy and EDX microanalysis.

3. Results and Discussion

3.1 Joining strength of Al_2O_3 /Cu joint formed by ultrasonic brazing

Figure 3 shows the change in joining strength of Al_2O_3 /Zn-6Al-4Cu/Cu joint with application time of ultrasound

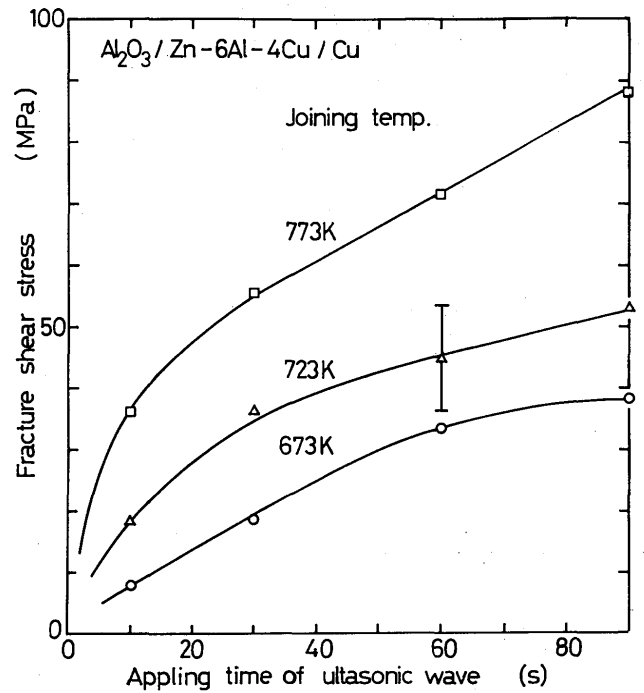


Fig. 3 Change in joining strength of Al_2O_3 /Cu joint using Zn-6Al-4Cu filler with application time of ultrasound.

at joining temperatures from 673 to 773 K. The application of ultrasound during brazing improves the strength of Al_2O_3 /Cu joint at all joining temperatures. For instance, the strength of the joint increases up to 88 MPa at 90 s with increasing the application time of ultrasound at joining temperature of 773 K, although the joint without applying ultrasound doesn't be joined soundly. The ultrasonic wave accelerates the motion of molten alloys in the filler bath and removes bubbles at the alumina-filler interface. Thus, the ultrasound accelerates the wetting of alloys against alumina. This results in the improvement of joining strength of Al_2O_3 /Cu joints.

The similar effects of ultrasound are seen in Al_2O_3 /Cu joints using other Zn-12Al-8Cu and Zn-18Al-12Cu filler metals as shown in Figs. 4 and 5. The longer time duration of applying ultrasound over 60 sec represents the higher strength of joint with Zn-12Al-8Cu filler than that of joint with Zn-6Al-4Cu filler. The Zn-18Al-12Cu filler with large amounts of alloying elements of Al and Cu reaches the lower strength of Al_2O_3 /Cu joint, compared with other fillers.

The increase in joining temperature raises the joining strength at a constant applying time of ultrasound. Figure 6 represents the change in joining strength of Al_2O_3 /Cu joint using Zn-6Al-4Cu filler with joining temperature at the constant applying time of 60 s. The strength of joint changes from 34 MPa at 673 K to 71 MPa at 773 K at brazing condition of 60 s. The increase in bath temperature makes the spread of ultrasound on ceramics easy.

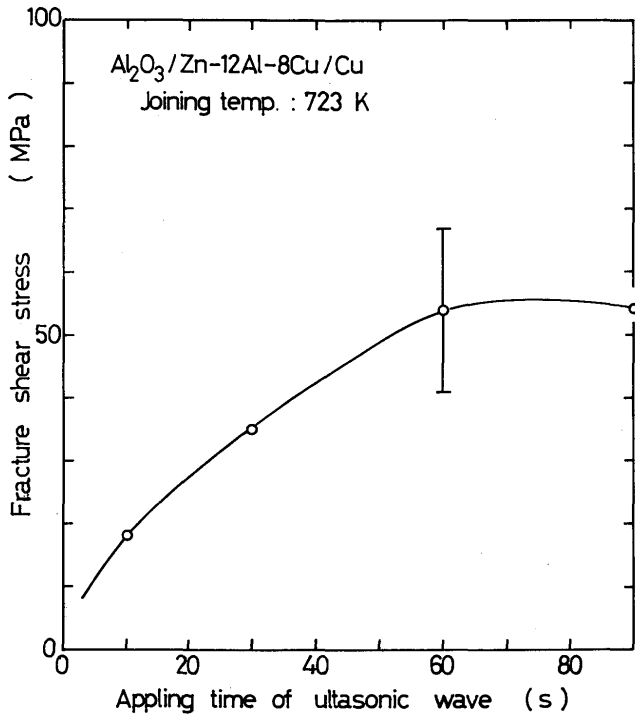


Fig. 4 Change in joining strength of Al₂O₃/Cu joint using Zn-12Al-8Cu filler at joining temperature of 723 K with application time of ultrasound.

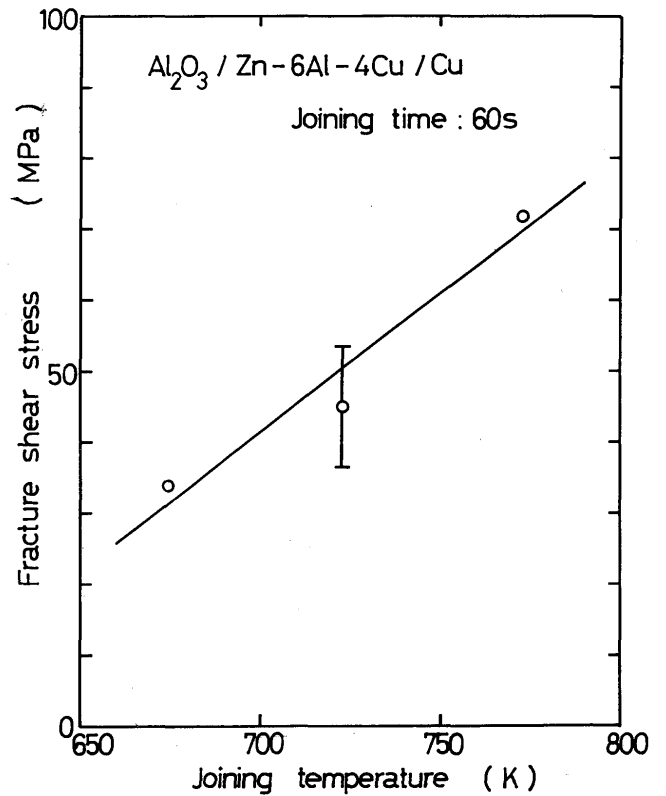


Fig. 6 Change in strength of Al₂O₃/Cu joint using Zn-6Al-4Cu filler with joining temperature at application time of 60 s.

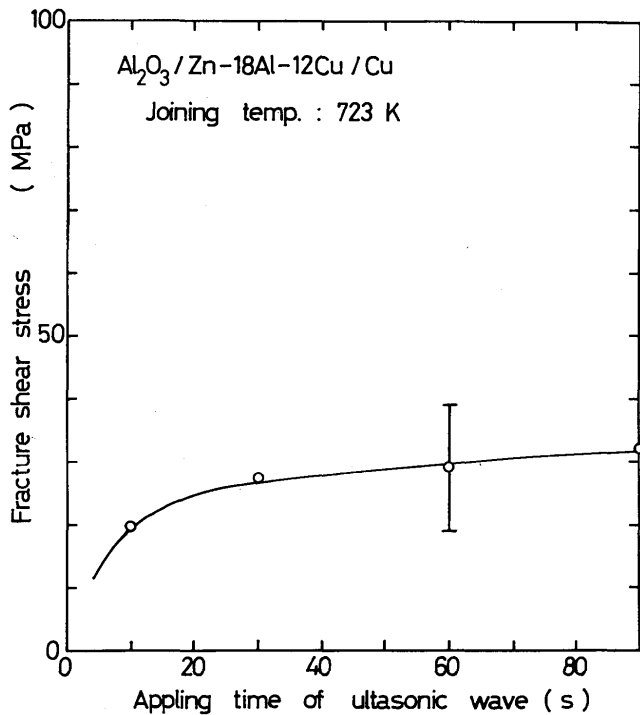


Fig. 5 Change in joining strength of Al₂O₃/Cu joint using Zn-18Al-12Cu filler with application time of ultrasound at joining temperature of 723 K.

The change in joining strength of Al₂O₃/Cu joint with Al plus Cu content in Zn-Al-Cu filler at joining condition of 723 K and 60 s is shown in Fig. 7 where the ratio of Al/Cu is fixed as 6/4. The joining strength of Al₂O₃/Cu joint increases with increasing Zn plus Cu content in the filler from 12 MPa at 0 mass% Al, and exhibits the maximum value of 54.5 MPa at 20 mass% Al+Cu. With further adding Al+Cu content, the strength lowers to 29.5 MPa at 30 mass% Al + Cu through the maximum value. Included in the figure for comparison are the values of Al₂O₃/Cu joints with Zn and Zn-Al fillers⁹⁾. The mixing of Al and Cu provides the higher strength, compared with that of joint containing Al as alloying element.

The increase in joining strength of Al₂O₃/Cu joint is arisen from two factors. First, the wetting of molten Zn-Al-Cu filler against Al₂O₃ is improved by an addition of aluminum in the initial stage up to Al + Cu content of 20 mass%. MacDonald³⁾ and Naka et al⁵⁾ have indicated that the molten aluminum definitely wets Al₂O₃. The aluminum in Zn-Al filler dissolves or reacts with Al₂O₃. This leads to accelerate the wetting of the filler against Al₂O₃. Secondly, the mechanical properties of Zn-Al-Cu fillers are improved by mixing Al plus Cu into Zn. This also raises the joining strength of Al₂O₃/Cu joint.

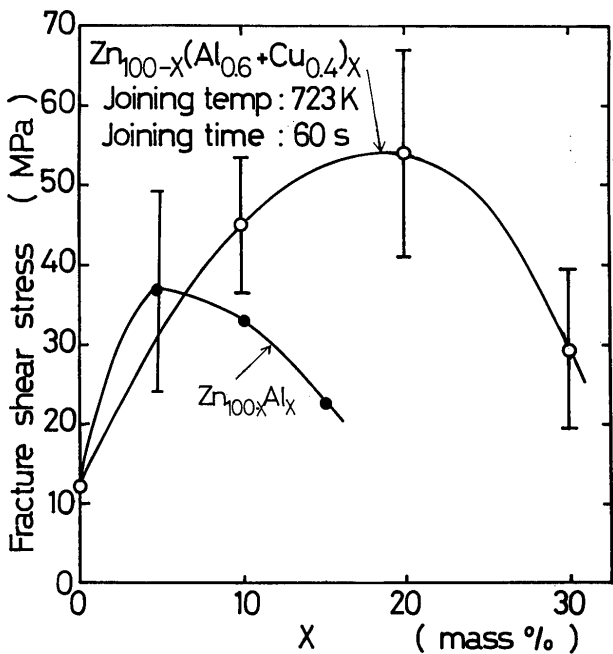


Fig. 7 Change in strength of Al₂O₃/Cu joint brazed at 723 K for 60 s with alloying content X in Zn-Al-Cu or Zn-Al filler.

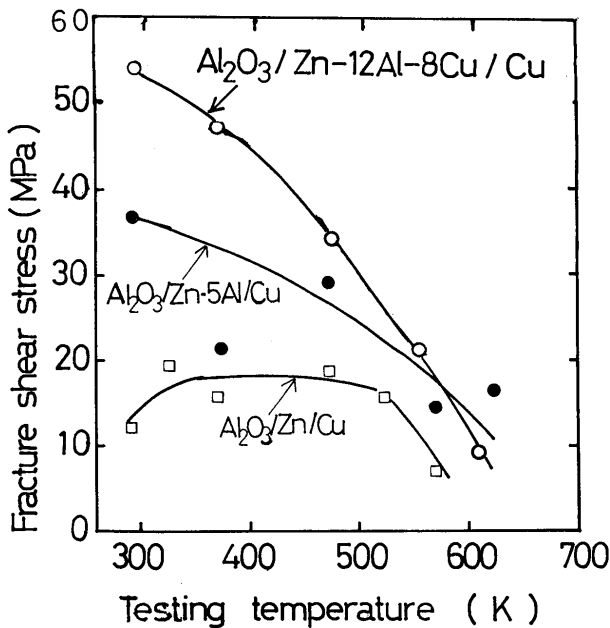


Fig. 8 Change in strength of Al₂O₃/Cu joint Zn-12Al-8Cu filler brazed at 723 K for 60 s with testing temperature.

However, the mixing of excess amounts of Al plus Cu raises the viscosity of molten Zn-Al fillers. The ultrasonic wave can't be effectively applied to Al₂O₃ in such viscous molten fillers. Then, the high viscosity of the filler results in lowering the joining strength of Al₂O₃/Cu joint.

Figure 8 shows the joining strength of Al₂O₃/Cu joint using Zn-12Zn-8Cu filler brazed at 723 K for 60 s at testing

temperatures from room temperature to 623 K. Al₂O₃/Cu joint with Zn filler maintains the joining strength up to 373 K, though the joining strength rises a little with increasing testing temperature from room temperature. With further increasing testing temperature the joining strength of the joint lowers monotonously. Included in the figure for comparison are values of joints with Zn and Zn-5Al fillers. The joint with Zn-Al-Cu filler represents the higher strength at elevated temperatures up to 550 K, compared with the joint with Zn or Zn-5Al filler. The mixing effect of Al and Cu operates at the higher temperatures.

The fracture of Al₂O₃/Cu joint with Zn-12Al-8Cu filler takes place in the interface between filler and alumina at room temperature in Fig. 9. The alumina fracture surface of joint with Zn-12Al-8Cu filler show partly the adhesion of

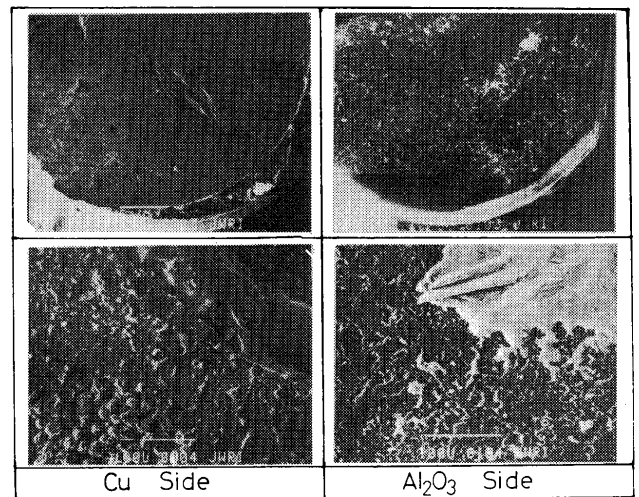


Fig. 9 Fracture surface of Al₂O₃/Cu joint using Zn-12Al-8Cu fractured at room temperature.

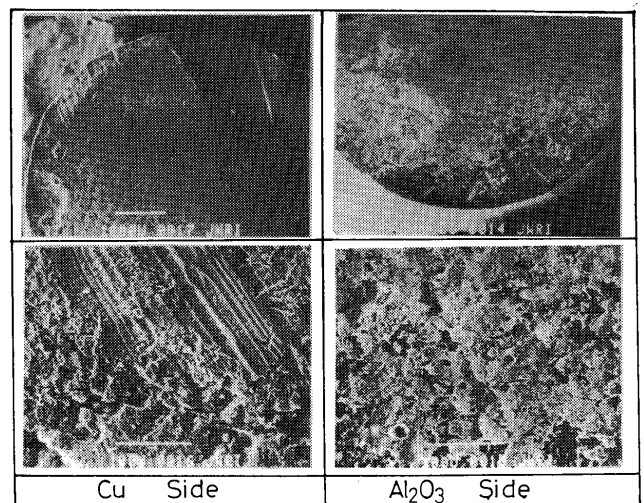


Fig. 10 Fracture surface of Al₂O₃/Cu joint using Zn-12Al-8Cu fractured at 543 K.

the filler on Al₂O₃. Fig. 10 represents the fracture surface of Al₂O₃/Cu joint with Zn-12Al-8Cu filler at testing temperature of 543 K. The ductile shearing takes place at the filler. These observations of fracture surface of joint demonstrate that the decrease in strength of Zn-12Al-8Cu fillers at high testing temperature is attributable to the decrease in the joining strength of Al₂O₃/Cu joints.

4. Joining microstructure at interface of Al₂O₃/Cu joint

Figure 11 represents the microstructure (a), interfaces of Al₂O₃/filler(b) and filler/Cu(c) of Al₂O₃/Cu joint with Zn-6Al-4Cu filler brazed at 673 K for 60 s. The filler, which is accelerated by applying the ultrasound, well joins with Al₂O₃ without defects as shown in Fig. 11(b). The two intermediate phases are formed at the interface between the filler and copper material in Fig.11 (c). The chemical compositions of intermediate phases at filler/Cu interface of the joint with Zn-6Al-4Cu filler brazed at 673 K for 60 s are shown in Table 2. The phase I adjacent to the filler in Fig. 11(c) is identified as ε phase which is the same in Cu-Zn system¹⁰. The phase II adjacent to copper material is also identified as γ phase in Cu-Zn system. The aluminum stabilizes the Zn rich intermediates by dissolving into the phases in the table.

Figure 12 shows the microstructure(a) and interfaces of Al₂O₃/filler(b) and filler/Cu(c) of Al₂O₃/Cu joint with Zn-12Al-8Cu filler brazed at 723 K for 60 s. The filler also well wets the Al₂O₃. At the interface between the filler and Cu the two intermediate phases are formed in Fig. 12(c), and the chemical composition of the two phases are represented in Table 3. The phase I adjacent to the filler

Table 2 Chemical composition of intermediate phases in Al₂O₃/Cu joint using Zn-6Al-4Cu filler brazed at 673 K for 60 s.

	Zn	Cu	Al
	(at%)		
Phase I	75.94	20.94	3.12
Phase II	50.68	41.44	7.88

Table 3 Chemical composition of intermediate phases in Al₂O₃/Cu joint using Zn-12Al-8Cu filler brazed at 723 K for 60 s.

	Zn	Cu	Al
	(at%)		
Phase I	67.45	24.05	8.50
Phase II	41.97	31.20	26.83

and phase II adjacent to copper are identified as γ phase in Cu-Zn system and τ' in Al-Cu-Zn system¹²). The intermediate phases in the joint with Zn-12Al-8Cu filler containing less amounts of zinc are formed, compared with the phases in the joint with Zn-6Al-4Cu filler.

5. Conclusions

The joining on Al₂O₃ to Cu with Zn-Al-Cu filler metals containing the sum of Al plus Cu content up to 30 mass% where the ratio of Al/Cu is fixed as 3/2 was conducted by ultrasonic brazing at brazing condition of 673–773 K and 0-90 s. The intensity of ultrasound used was 1 kW and 18 kHz. The joining mechanism of the ultrasonic brazing was investigated by measuring the joint strength and observing the microstructure of the interface of the Al₂O₃/Cu joint.

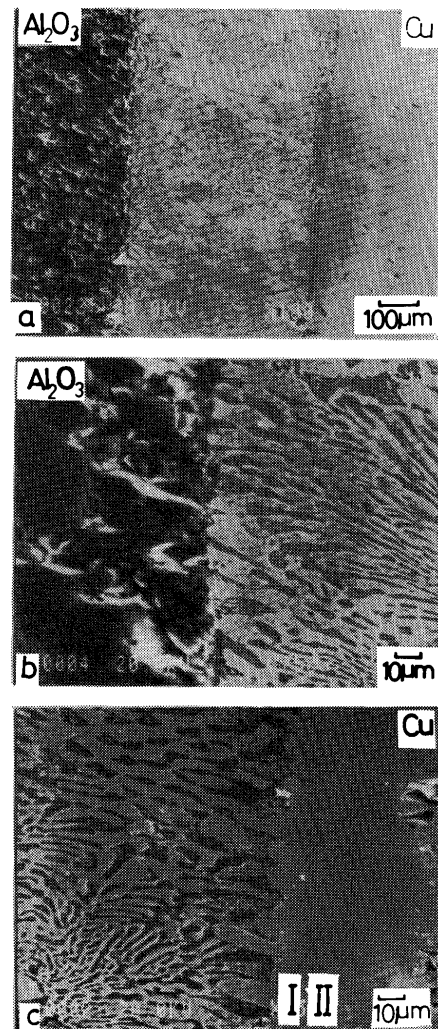


Fig. 11 Microstructure(a), interfaces of Al₂O₃/filler(b) and filler/Cu (c) in Al₂O₃/Cu joint with Zn-6Al-4Cu filler brazed at 673 K for 60 s.

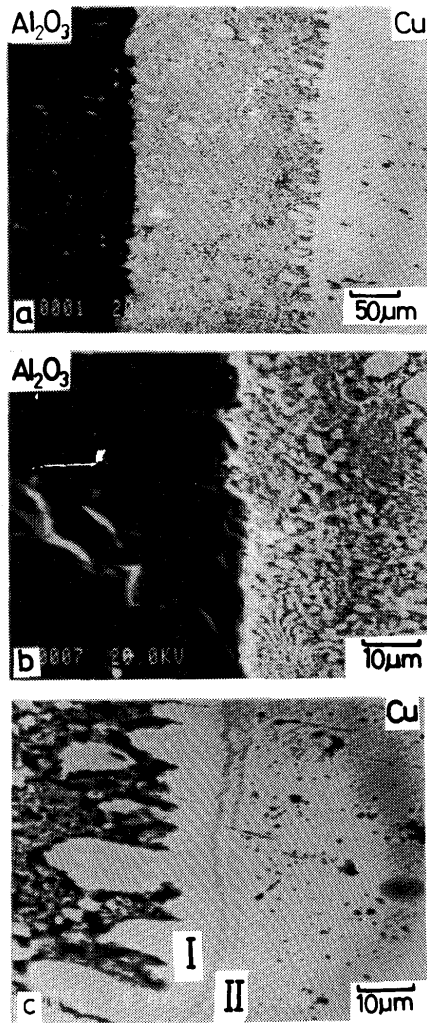


Fig. 12 Microstructure(a), interfaces of Al_2O_3 /filler(b) and filler/Cu (c) in Al_2O_3 /Cu joint with Zn-12Al-8Cu filler brazed at 723 K for 60 s.

The increase in applying time and brazing temperature raises the joining strength of Al_2O_3 /Cu joints with Zn-Al-Cu filler. The ultrasonic wave activates the motion of

molten alloys in the Zn-Al fillers, and accelerates the wetting of alloys against Al_2O_3 . This leads to the increase in joining strength of the joint.

The addition of Al plus Cu to Zn filler up to 20 mass% improves the wettability and mechanical properties of the filler against Al_2O_3 . This results in the superior strength of Al_2O_3 /Cu joints brazed with Zn-Al-Cu filler under applying the ultrasound.

While the Zn-Al-Cu fillers directly join with Al_2O_3 , the fillers form the intermediate phases between the fillers and copper.

References

- 1) J. R. Flopd: J. Am. Ceram. Soc., 42(1963), 65.
- 2) W. M. Armstrong, A. C. D. Chaklader and J. F. Clark: J. Am. Ceram. Soc., 45(1962), 115.
- 3) J. E. McDonald and J. G. Eberhart: Trans. AIME., 233(1965), 512.
- 4) T. Izeki and M. G. Nicholas: J. Mater. Sci., 14(1979), 687.
- 5) M. Naka, M. Kubo and I. Okamoto: J. Mater. Sci., 22(1987), 4417.
- 6) J. E. Burgess, C. A. Neugebauer and G. F. Flanagan: J. Electrochem. Soc., 122(1975), 688.
- 7) M. Naka and I. Okamoto: Quaternary J. Japan Weld. Soc., 5(1986), 113.
- 8) M. Naka and I. Okamoto: Metal-Ceramic Joints, MRS, 1989, p61.
- 9) M. Naka and M. Maeda and I. Okamoto: Trans. JWRI., 18(1989), No.2, 81.
- 10) M. Hansen, Constitution of Binary Alloys, McGraw-Hill Book Co., 1958, p649.
- 11) Y. A. Chang, J. P. Neumann, A. Mikula and D. Goldberg: Phase diagram and Thermodynamic Properties of Ternary Copper-Metal Systems, Inter. Copper Assoc. Inc., 1979, p253.