



Title	Synthesis of $\text{Si}_1\text{N}_2\text{O}$ -SiC Composites from Desert Sand(Materials, Metallurgy & Weldability)
Author(s)	Radwan, Mohamed; Miyamoto, Yoshinari
Citation	Transactions of JWRI. 2002, 31(1), p. 37-40
Version Type	VoR
URL	https://doi.org/10.18910/7446
rights	
Note	

The University of Osaka Institutional Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

Synthesis of $\text{Si}_2\text{N}_2\text{O}$ -SiC Composites from Desert Sand[†]

RADWAN Mohamed* and MIYAMOTO Yoshinari**

Abstract

$\text{Si}_2\text{N}_2\text{O}$ -SiC composite powders in various compositions were synthesized by the nitriding combustion of the mixtures of natural desert sand, reclaimed silicon and graphite. Qualitative and quantitative analysis of the composites' phases were made from the x-ray diffraction patterns. Their sintering behavior was observed by densification at 1600 °C for 2 minutes using the new spark plasma sintering technique.

KEY WORDS: (Combustion synthesis) (SHS) ($\text{Si}_2\text{N}_2\text{O}$) (SiC) (Composite) (Sand)


1. Introduction

Desert sand is a unique natural raw material because it is abundant, cheap and pure in the earth's crust. This fact attracted us to investigate the synthesis of useful materials that can result from its combustion in nitrogen gas. The combustion synthesis¹⁾ method is an advanced process used successfully for preparation of a variety of refractories and ceramics such as borides, nitrides, carbides, and silicides²⁻⁴⁾. It depends on the strong exothermic heat formation from the chemical reaction which propagates spontaneously and rapidly through the reactants converting them into a product. Simple equipment, high-energy efficiency, and high synthesis rate are its main advantages.

From natural sand, we prepared powders of $\text{Si}_2\text{N}_2\text{O}$ -SiC and $\text{Si}_2\text{N}_2\text{O}$ - Si_3N_4 composites besides the monolithic $\text{Si}_2\text{N}_2\text{O}$. This paper reports the results of the combustion synthesis of the $\text{Si}_2\text{N}_2\text{O}$ -SiC composite powders.

2. Experimental Procedure

Untreated desert sand (99.7 % purity) from Egypt, reclaimed silicon (94 % purity) from Toho Zinc Co. Ltd., Japan, and graphite (99.7 % purity) were used as the raw materials. The starting compositions were determined by the following chemical equation:



The mixing ratios X and Y used and the nominal product compositions (in molar ratios) are given in Table 1. The starting mixtures preparation and the combustion synthesis were the same as described in our previous report⁵⁾.

Qualitative and quantitative phase determination in the synthesized powders was performed by X-ray powder diffraction analysis with $\text{Cu-K}\alpha$ radiation.

The sintering experiments were carried out at constant conditions (1600 °C sintering temperature in 400 °C/min heating rate and 2 minutes holding time under 30 MPa sintering pressure) using Dr. Sinter[®] Model 1050 SPS apparatus (Sumitomo Coal Mining Company, Ltd., Japan). The additive of $\text{CaO-Al}_2\text{O}_3$ (5 wt%) was used as a sintering-aid.

Table 1 Mixing ratios of starting reactants and nominal composition of the products.

<i>Y</i>	<i>X</i>	<i>Calculated composition</i>	<i>Si₂ON₂</i> (wt%)	<i>SiC</i> (wt%)
0.25	0.075	$3\text{Si}_2\text{ON}_2 + \text{SiC}$	88.2	11.8
0.33	0.075	$2\text{Si}_2\text{ON}_2 + \text{SiC}$	83.3	16.7
0.5	0.075	$\text{Si}_2\text{ON}_2 + \text{SiC}$	71.4	28.6
0.67	0.075	$\text{Si}_2\text{ON}_2 + 2\text{SiC}$	55.6	44.4

Transactions of JWRI is published by Joining and Welding Research Institute of Osaka University, Ibaraki, Osaka 567-0047, Japan

3. Results and Discussion

The change in the formation enthalpy of the synthesis reaction at various Y ratios is shown in Fig. 1. Increasing the SiC content in the composite products tends to decrease the exothermicity of the starting reactants. This trend was reflected on their corresponding temperature profiles, Fig. 2, which were measured during the combustion by using a thermocouple placed halfway in the burden. The combustion temperature was decreased from 1868 °C to 1600 °C when the SiC content was increased from 19.7 wt% to 57.6 wt%. But, starting

mixtures with Y greater than 0.67 failed to sustain reaction in the self-propagation mode. Among the reasons are the low exothermicity of these mixtures and the high volume of graphite in the reactants which may prevent good contacts between Si particles and N_2 . The thermodynamic calculations suggest that in such mixtures, the principal reaction is the nitriding of Si and the heat released by this reaction can promote further reactions of $\text{Si}_2\text{N}_2\text{O}$ and SiC formation.

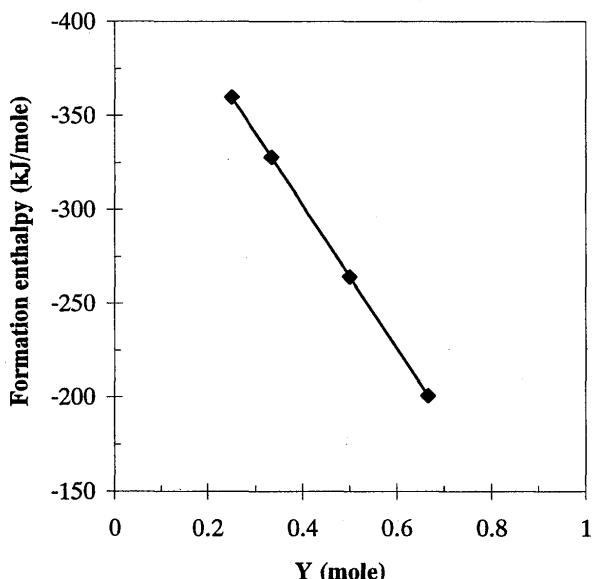


Fig. 1 Formation enthalpy of $\text{Si}_2\text{N}_2\text{O}-\text{SiC}$ synthesis reactions at different mixing ratios.

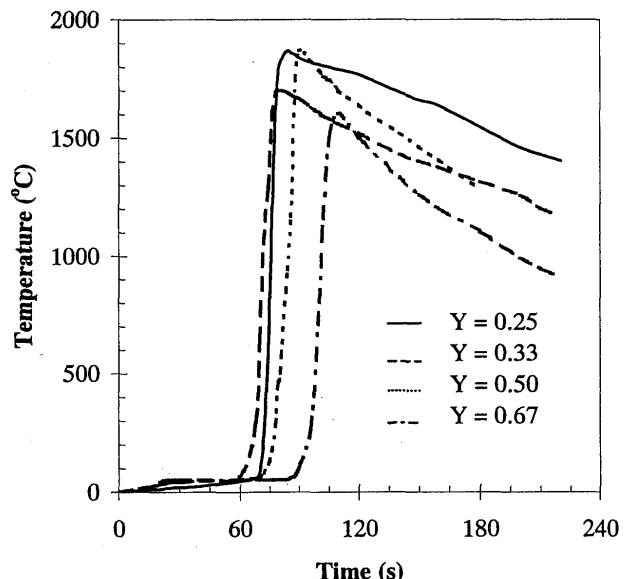


Fig. 2 Temperature profiles of $\text{Si}_2\text{N}_2\text{O}-\text{SiC}$ composite synthesis reactions.

Figure 3 shows the change in the $\text{Si}_2\text{N}_2\text{O}$ and SiC contents in the synthesized composite powders determined from their x-ray diffraction patterns. From the XRD analyses of synthetic $\text{Si}_2\text{N}_2\text{O}-\text{SiC}$ composites with known compositions, we found that the amount of each phase could be calculated from the intensities of their main peaks. Figure 3 shows that composites with SiC contents up to 57.6 wt% were synthesized. The measured contents differ from the calculated ones which may be due to the vaporization of $\text{Si}_2\text{N}_2\text{O}$ during the high-temperature combustion reaction. Since these

reactions were reproducible, it is possible to control the composition of the resultant composite.

The results of measuring densities, hardness, and fracture toughness of the sintered powders are shown in Figs. 4 and 5. The increase of SiC content in the composite hindered achieving the full densification. This is because of the covalent nature of the hard SiC and usually SiC is densified at much higher temperatures. However, the Vickers hardness increased significantly as can be predicted. Since these results are still preliminary, we expect to improve the densities and both the hardness and toughness of the sintered composites in the near future.

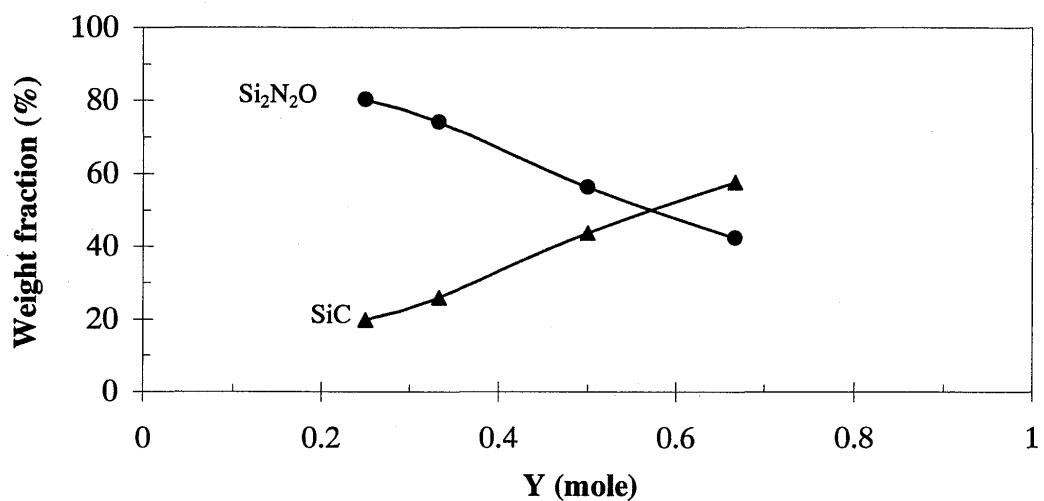


Fig. 3 Change of composition in the synthesized $\text{Si}_2\text{N}_2\text{O}$ - SiC composites.

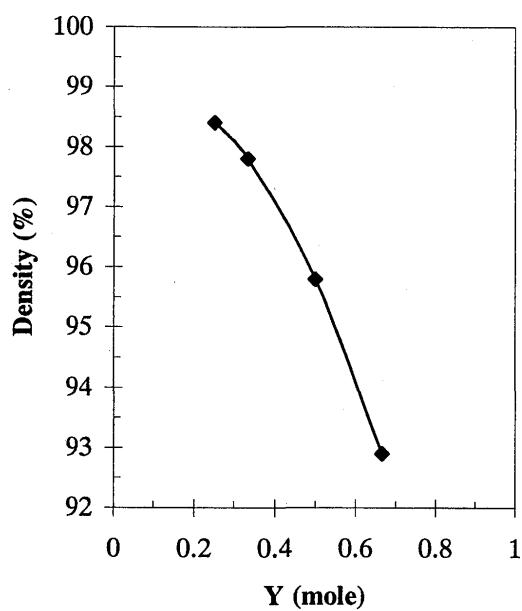


Fig. 4 Change of the density of the sintered $\text{Si}_2\text{N}_2\text{O}$ - SiC composites.

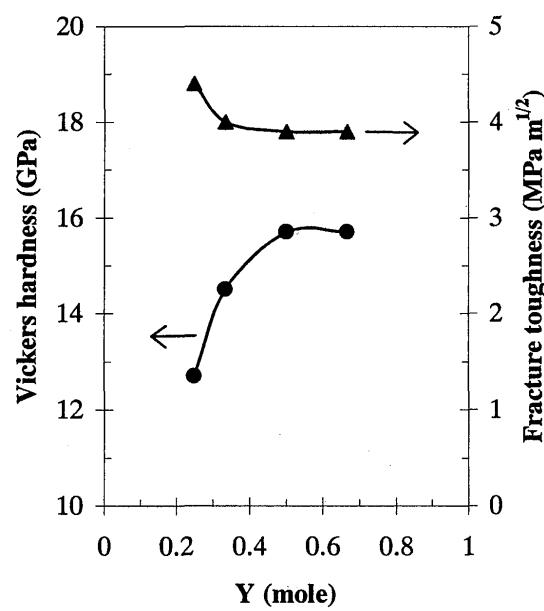


Fig. 5 Vickers hardness and fracture toughness of the sintered $\text{Si}_2\text{N}_2\text{O}$ - SiC composites.

4. Summary

Desert sand is cheap, natural, abundant ore in high purity form and can be considered as a valuable starting material for the synthesis of many Si-based ceramics using the nitriding combustion synthesis method. This research reports the results of nitriding combustion of desert sand to $\text{Si}_2\text{N}_2\text{O}-\text{SiC}$ composite powders. Composites with SiC contents up to 57.6 wt% were prepared.

Acknowledgement

M. Radwan wishes to thank the Missions Department at the Ministry of Higher Education of Egypt for the financial support of his study in JWRI.

References

- 1) A. G. Merzhanov and I. P. Borovinskaya: Dokl. Akad. Nauk SSSR, **204** (1972), 366.
- 2) J. F. Crider: Ceram. Eng. Sci. Proc., **3** (1982), 519.
- 3) Y. Miyamoto: Int. J. of Self-Propag. High-Temp. Syn., **8** (1999), 375.
- 4) A. G. Merzhanov: J. of Materials Processing Technology, **56** (1996), 222.
- 5) M. Radwan and Y. Miyamoto: In Proceedings of The 40th Symposium on Basic Science of Ceramics, Osaka University, Japan, January 22-23 (2002), 570.