



Title	Optical properties of di-substituted acetylene polymers
Author(s)	Tada, Kazuya; Hidayat, Rahmat; Hirohata, Masaharu et al.
Citation	Proceedings of SPIE – The International Society for Optical Engineering. 1997, 3145, p. 171–178
Version Type	VoR
URL	https://hdl.handle.net/11094/76946
rights	
Note	

The University of Osaka Institutional Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

Optical Properties of Di-substituted Acetylene Polymers

Kazuya Tada, Rahmat Hidayat, Masaharu Hirohata, Hirotake Kajii, Satoshi Tatsuhara, Akihiko Fujii, Masanori Ozaki, Masahiro Teraguchi*, Toshio Masuda* and Katsumi Yoshino

Department of Electronic Engineering, Osaka University, 2-1 Yamada-Oka, Suita, Osaka 565, Japan

* Division of Polymer Chemistry, Kyoto University, Yoshida-Honmachi, Sakyo, Kyoto 606, Japan

ABSTRACT

Optical properties and electronic energy structures of di-substituted acetylene polymers have been studied. Strong blue and green photoluminescence and electroluminescence have been observed in the poly(diphenylacetylene) (PDPA) derivatives and poly(1-alkyl-2-phenylacetylene) (PAPA) derivatives, contrary to *trans*-polyacetylene, in which only very weak photoluminescence are observed at infrared region. The dependence of optical properties of the di-substituted polyacetylene derivatives such as photoluminescence intensity and electroluminescence efficiency on the molecular structure of substituents and the change of optical properties upon electrochemical doping and their interpretation by soliton model have also been discussed. Spectral narrowing in photoluminescence of some di-substituted polyacetylenes have also been studied.

1. INTRODUCTION

Recently, conducting polymers with extensive π -conjugation in their main chain have attracted much attentions as materials for electronic and optoelectronic devices such as electroluminescent devices ¹⁻³⁾ and photocells, ⁴⁻⁷⁾ because of their high quantum electron/photon conversion efficiency and advantages for fabrication of thin films with large area. They have attracted much attentions from not only such practical viewpoints but also fundamental viewpoints because they exhibits numerous unique phenomena such as drastic changes in electrical, optical and magnetic properties upon doping.

Polyacetylene is a conducting polymer with most simple backbone structure and many studies were carried out on the characteristics of this polymer. ⁸⁾ Although practical applications of polyacetylene and their derivatives such as an electrode of a secondary battery were attempted but they have not been successful. On the other hand, we proposed for the first time to apply a *trans*-polyacetylene derivative, perfluoroalkylated poly(diphenylacetylene) to electroluminescent devices, and also demonstrated strong green photoluminescence. ⁹⁾

In the early stage of study of polyacetylene, Lauchlan *et al.* reported the absence of photoluminescence in *trans*-polyacetylene and interpreted the result based on the soliton model. ¹⁰⁾ The lack of the proposals of electroluminescent device with *trans*-polyacetylene derivatives before us may be partly due to a speculation associated with this interpretation that efficient luminescence will not be expected in any *trans*-polyacetylene derivatives.

However, we ¹¹⁾ and Fitchen ¹²⁾ have observed weak photoluminescence at infrared region in *trans*-polyacetylene, suggesting that not the soliton dynamics but the relative position of 1^1B_u and 2^1A_g metastable states in energy is important to interpret the luminescence of this polymer. That is, in *trans*-polyacetylene, the metastable 1^1B_u state is higher than 2^1A_g state in energy, resulting in the weak photoluminescence. The substituents may influence on the energy levels of 2^1A_g and 1^1B_u states.

In this article, we report optical properties and electronic energy structures of di-substituted acetylene polymers.

2. EXPERIMENTAL

Various di-substituted acetylene polymers such as poly(1-phenyl-2-*p*-*n*-butyl phenyl acetylene) (PDPA-*n*Bu), poly(1-phenyl-2-*p*-*tert*-butylphenyl acetylene) (PDPA-*t*Bu), poly(1-phenyl-2-*p*-adamantylphenyl acetylene) (PDPA-Ad), poly(1-phenyl-2-*p*-trimethylsilylphenyl acetylene) (PDPA-SiMe₃), poly(1-phenyl-2-*p*-tri(isopropyl)silyl phenylacetylene) (PDPA-Si*i*Pr₃), poly(1-phenyl-2-*p*-triphenylsilylphenyl acetylene) (PDPA-SiPh₃), poly(1-phenyl-2-*m*-trimethylsilylphenyl acetylene) (PDPA-*m*SiMe₃), poly(1-phenyl-2-*p*-phenoxyphenyl acetylene) (PDPA-OPh), poly(1-methyl-2-phenyl acetylene) (PMePA), poly(1-ethyl-2-phenyl acetylene) (PEtPA), poly(1-*n*-hexyl-2-phenyl acetylene) (PHxPA) and poly(1-methyl-2-naphthyl acetylene) (PMeNA) were studied here. The molecular structures of these polymers are shown in Fig. 1. The synthesis of these di-substituted acetylene polymers are described elsewhere.¹³⁾ These polymers are soluble in common organic solvents such as chloroform.

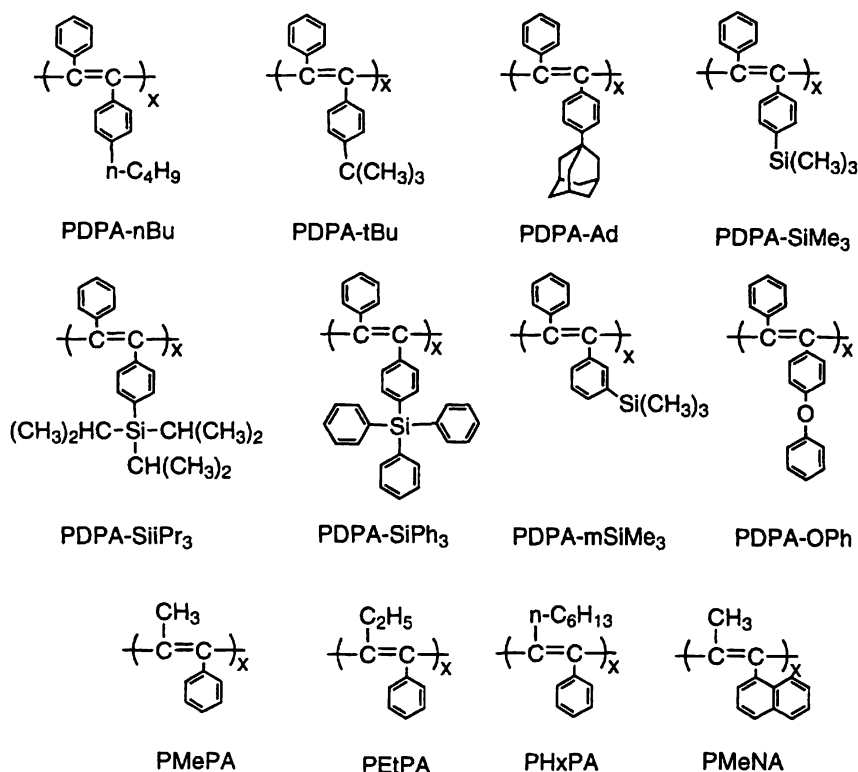


Fig. 1 Molecular structures of di-substituted acetylene polymers studied here.

Thin films were prepared by spin coating or casting a chloroform solution containing the conducting polymer on appropriate substrates such as quartz plates or In-Sn oxide (ITO) coated quartz plates (transparent electrodes).

Optical absorption and photoluminescence spectra were measured using spectrophotometer (HP 8452 or Hitachi 330) and fluorescence spectrophotometer (Hitachi F2000), respectively.

Electrochemical measurements such as cyclic voltammetry were carried out using potentiostat (Hokuto-Denko HA501) and function generator (Hokuto-Denko HB104) in a dry-box filled with Ar gas. Used three-electrode electrochemical cell was filled with acetonitrile containing tetrabutylammonium tetrafluoroborate (TBABF₄) as supporting salt, and had a casted film on ITO-coated glass, an Ag wire and a Pt plate as working electrode (WE), reference electrode (RE) and counter electrode (CE), respectively.

ESR study was carried out with Bruker ESP-300. Spin density was measured using DPPH as the reference.

The electroluminescent devices were fabricated by depositing a Mg-In alloy onto a spin coated polymer films on the ITO-coated glass plates or ITO-coated quartz substrates. The emission area were approximately 6 mm². Electroluminescent characteristics were studied either under vacuum as room temperature or in liquid N₂ by a method described elsewhere.^{2,3,9)}

The emission spectra at strong excitation were measured using a spectrophotometer (Hamamatsu Photonics PMA-11) upon irradiation of laser pulse with 10 ns in width and 355 nm in wavelength produced by THG of a Nd:YAG laser light.

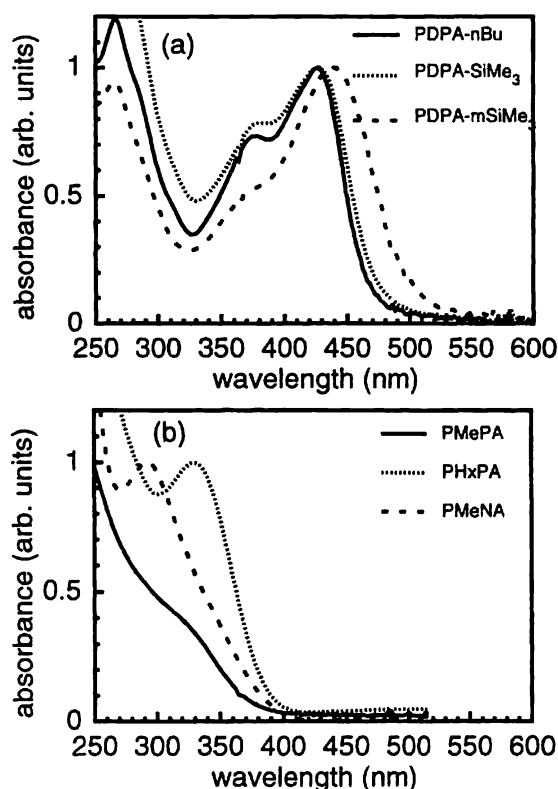


Fig. 2 Optical absorption spectra of poly(diphenylacetylene) derivatives (a) and poly(1-alkyl-2-phenyl acetylene) derivatives.

3. RESULTS AND DISCUSSION

Optical absorption spectra of poly(diphenylacetylene) (PDPA) derivatives and poly(1-alkyl-2-phenyl acetylene) (PAPA) derivatives are shown in Figs. 2(a) and (b), respectively. It is clearly indicated that PDPA derivatives such as PDPA-nBu, PDPA-SiMe₃ and PDPA-mSiMe₃ have the absorption edge at longer wavelength than PAPA derivatives such as PMePA, PHxPA and PMeNA.

The band-gap energies of these polymers can be evaluated from Fig. 2 using $(\alpha h\nu)^2 - h\nu$ plot where α , h are the absorbance at frequency ν and the Planck's constant, respectively, and are summarized in Table 1. The energies of highest occupied molecular orbital (HOMO) corresponding to the valence band top evaluated from cyclic voltammetry using Ag wire as a reference electrode are also listed in this table.

The band-gap energies of various PDPA derivatives with side group at *para*-position are almost the same regardless of the molecular structure of the side group. However, it should be noted that the position of the side group influences a little to the band gap energy. That is, the band gap energy of PDPA-mSiMe₃ having the same substituent with PDPA-SiMe₃ at different position (*meta*-position) is 2.57 eV and significantly smaller than that of PDPA-SiMe₃ (2.70 eV). The band-gap energy of perfluoroalkyl poly(diphenylacetylene) (PFDPDA) previously reported is 2.7 eV and also coincide with those of PDPA derivatives studied here.

The molecular structures of the substituents in poly(1-alkyl-2-phenylacetylene) derivatives should influence the electronic energy structure. The energy of HOMO of poly(1-alkyl-2-phenyl acetylene)s becomes lower with increasing alkyl chain length, and that of PMePA is higher than that of PMeNA.

Table 1. HOMO level, band gap, PL and EL peaks and Stokes shift value of di-substituted acetylene polymers.

Polymer	Band gap (eV)	HOMO vs vacuum level (eV)	PL peak (eV)	EL peak (eV)	Stokes shift (eV)
PDPA-nBu	2.73	-5.6	2.38	2.40	0.35
PDPA-tBu	2.71	-5.7	2.36	2.43	0.35
PDPA-Ad	2.67	-5.6	2.31	2.25	0.36
PDPA-SiMe ₃	2.70	-5.75	2.36	2.40	0.34
PDPA-SiPr ₃	2.74	-5.9	2.38	2.35	0.36
PDPA-SiPh ₃	2.71	-5.9	2.34	2.38	0.37
PDPA-mSiMe ₃	2.57	-5.75	2.29	2.23	0.28
PDPA-OPh	2.66	-5.7	2.30	2.25	0.36
PMePA	3.42	-5.9	2.63	2.58	0.79
PEtPA	3.35	-6.0	2.66	2.70	0.69
PHxPA	3.35	-6.1	2.70	2.76	0.65
PMeNA	3.40	-6.1	2.61	2.48	0.79

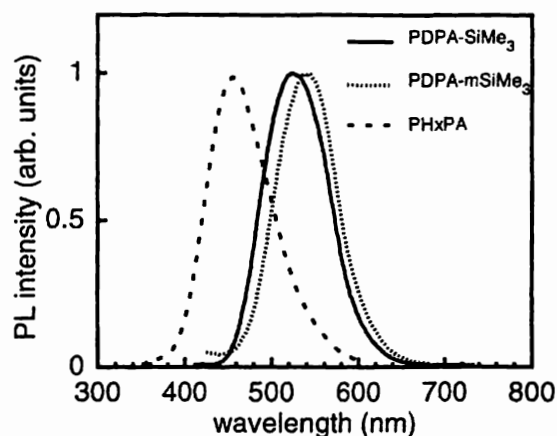


Fig. 3 Photoluminescence spectra of PDPA-SiMe₃, PDPA-mSiMe₃ and PHxPA.

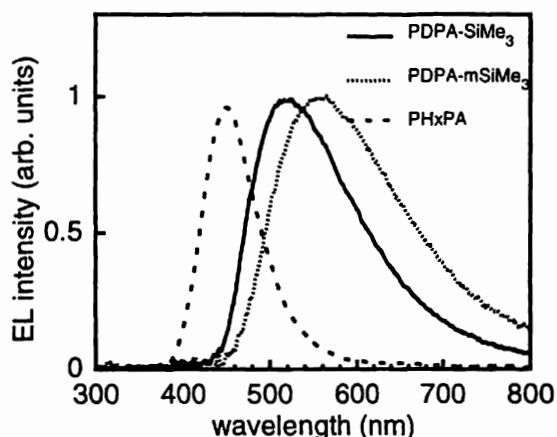


Fig. 4 Electroluminescence spectra of PDPA-SiMe₃, PDPA-mSiMe₃ and PHxPA.

Figure 3 shows the photoluminescence spectra of the di-substituted acetylene polymers such as PDPA-SiMe₃, PDPA-mSiMe₃ and PHxPA. PDPA derivatives with various substituents show strong green photoluminescence with the peak at almost the same photon energy. Strong blue or blue-green photoluminescences are observed in PAPA derivatives and the peak energy of them are blue-shifted with increasing alkyl chain length. Stokes shift, which is the difference between the band gap energy and the photoluminescence peak energy, of the di-substituted polyacetylenes are summarized also in Table 1 as well as photoluminescence peak energies. All of these polymers show relatively large Stokes shift as observed in *trans*-polyacetylene, reflecting their backbone structure.

Electroluminescence spectra of the device with the di-substituted acetylene polymers are shown in Fig. 4. The electroluminescence spectra of the polymers almost coincide with their photoluminescence spectra. The electroluminescence peak energy of the polymers are summarized also in Table 1, and almost coincide with photoluminescence peak energy.

Unique dependence of the intensities on the molecular structure of the side groups were found in both the electroluminescence and photoluminescence of the di-substituted polyacetylenes. Figure 5 shows the photoluminescence intensity and the relative electroluminescence efficiency of the PDPA derivatives with substituent containing Si atom. Among *para*-substituted PDPA

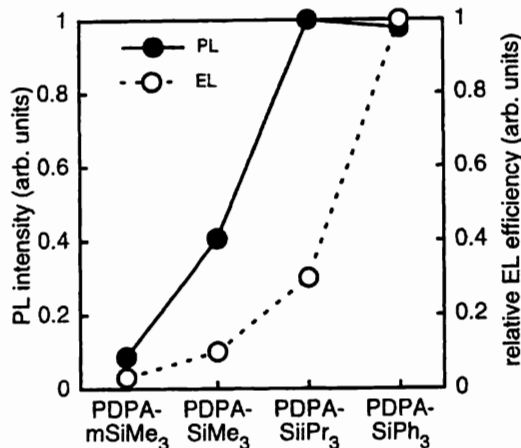


Fig. 5 Photoluminescence intensity and relative electroluminescence efficiency of the poly(diphenylacetylene) derivatives with substituent containing Si atom.

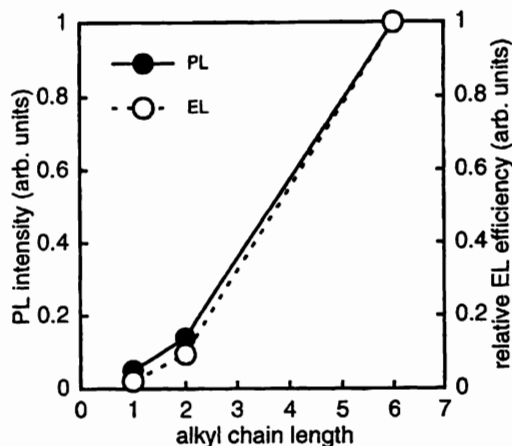


Fig. 6. Dependence of Photoluminescence intensity and relative electroluminescence efficiency of poly(1-alkyl-2-phenyl acetylene)s on alkyl chain length.

derivatives, PDPA-SiPh₃ and PDPA-SiPr₃ show stronger photoluminescence and electroluminescence than PDPA-SiMe₃ with smaller substituents. This can be tentatively understood in terms of steric hindrance between substituents. That is, in PDPA derivatives with larger substituents, more efficient confinement of the exciton or exciton-polaron in the main chain should take place due to larger steric hindrance between substituents, resulting in stronger luminescence. The photoluminescence intensity and electroluminescence intensity of PDPA-mSiMe₃ are significantly smaller than those of PDPA-SiMe₃, suggesting that the position of the substituent also affects the exciton confinement nature.

The photoluminescence intensity and electroluminescence efficiency of poly(1-alkyl-2-phenyl acetylene)s increase with increasing alkyl chain length, as shown in Fig. 6. This can also be tentatively interpreted in terms of exciton confinement effect due to steric hindrance between the alkyl side chain and the polymer main chain.

It is important to check whether the solitons exist or not in these fluorescent di-substituted polyacetylenes. Upon electrochemical BF₄⁻ doping (p-type doping) to some di-substituted polyacetylenes such as PDPA-nBu, we have observed evolution of optical absorption at the photon energy near the half of the band-gap energy as well as the suppression of the inter-band absorption,

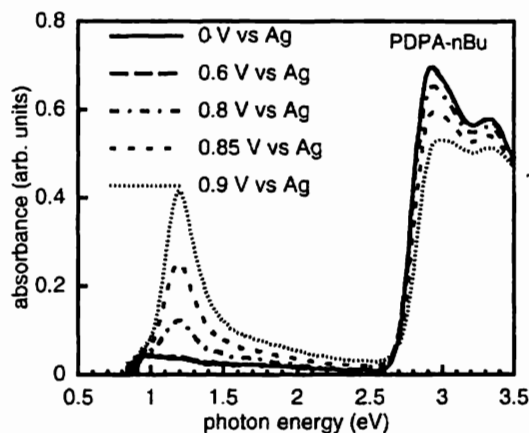


Fig. 7. Change of optical absorption spectra of PDPA-nBu upon electrochemical BF_4^- doping.

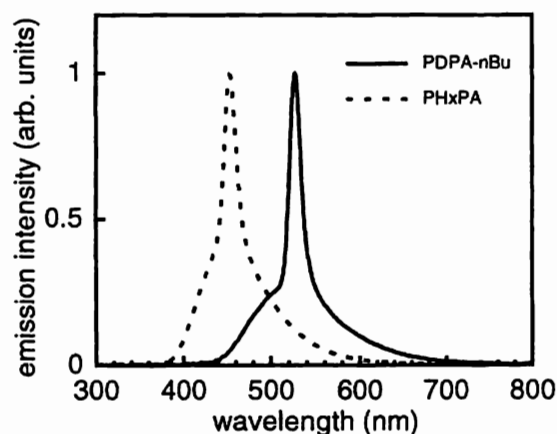


Fig. 8. Emission spectra of PDPA-nBu and PHxPA at strong excitation.

which is similar phenomenon observed in *trans*-polyacetylene,¹⁴⁾ as shown in Fig. 7. Moreover, until certain doping level, while significant evolution of the absorption at the half-band-gap energy takes place, significant increase of spin density was not observed, indicating the creation of spinless charged species or solitons in the di-substituted acetylene polymers.

Upon highly intense excitation, spectral narrowing of the photoluminescence¹⁵⁻¹⁷⁾ was observed in some di-substituted polyacetylenes due to stimulated emission. The emission spectra of PDPA-nBu and PHxPA at strong excitation are shown in Fig. 8.

4. SUMMARY

The experimental results are summarized as follows.

- (1) Strong blue and green photoluminescence and electroluminescence were observed in various di-substituted acetylene polymers. Poly(1-alkyl-2-phenyl acetylene) derivatives show blue or blue-green luminescence depending on substituents and poly(diphenylacetylene) derivatives show green luminescence.
- (2) The photoluminescence intensity and electroluminescence efficiency in the di-substituted acetylene polymers are strongly

dependent on the molecular structure of the substituents. This was explained in terms of change in exciton confinement due to steric hindrance effect.

- (3) Creation of solitons in the di-substituted acetylene polymers were confirmed by checking the change of optical absorption spectrum and spin density upon electrochemical doping.
- (4) Spectral narrowing was observed in photoluminescence of some di-substituted acetylene polymers such as PDPA-nBu and PHxPA by strong excitation.

ACKNOWLEDGMENT

This work was financially supported by the Research for the Future Program of the Japan Society of the Promotion of Science (Project No. JSPS-RFTF96P00206)

REFERENCES

1. J. H. Burroughes, D. D. C. Bradley, A. R. Brown, R. N. Marks, K. Mackay, R. H. Friend, P. L. Burns and A. B. Holmes: *Nature* **347** (1990) 539.
2. Y. Ohmori, M. Uchida, K. Muro and K. Yoshino: *Jpn. J. Appl. Phys.* **30** (1991) L1938.
3. Y. Ohmori, M. Uchida, K. Muro and K. Yoshino: *Jpn. J. Appl. Phys.* **30** (1991) L1941.
4. G. Yu, K. Pakbaz and A. J. Heeger: *Appl. Phys. Lett.* **64** (1994) 3422.
5. A. A. Zakhidov and K. Yoshino: *J. Soc. Electrical Mater. Eng.* **4** (1995) 43.
6. J. J. M. Halls, C. A. Walsh, N. C. Greenham, E. A. Marseglla, R. H. Friend, S. C. Moratti and A. B. Holmes: *Nature* **376** (1995) 498.
7. K. Tada, M. Onoda, A. A. Zakhidov and K. Yoshino: *Jpn. J. Appl. Phys.* **36** (1997) L306.
8. A. J. Heeger, S. Kivelson, J. R. Schrieffer and W. P. Su: *Rev. Mod. Phys.* **60** (1988) 781.
9. K. Tada, H. Sawada, J. Kyokane and K. Yoshino: *Jpn. J. Appl. Phys.* **34** (1995) L1083.
10. L. Lauchlan, S. Etemad, T. C. Chung, A. J. Heeger and A. G. MacDiarmid: *Phys. Rev. B* **24** (1981) 3701.
11. K. Yoshino, S. Hayashi, Y. Inuishi, K. Hattori and Y. Watanabe: *Solid State Commun.* **46** (1983) 583.
12. D. B. Fitchen: *Synth. Metals* **9** (1984) 341.
13. H. Shirakawa, T. Masuda and T. Takeda: *The Chemistry of Triple-Bonded Functional Groups*, ed. S. Patai (John Wiley & Sons, 1994) Chap.17, p. 945.
14. T. C. Chung, F. Moraes, J. D. Flood and A. J. Heeger: *Phys. Rev. B* **29** (1984) 2341.
15. N. Tessler, G. J. Denton and R. H. Friend: *Nature* **382** (1996) 695.
16. F. Hide, M. A. Diaz-Garcia, B. J. Schwartz, M. R. Anderson, Q. Pei and A. J. Heeger: *Science* **273** (1996) 1833.
17. S. V. Frolov, W. Gellermann, M. Ozaki, K. Yoshino and Z. V. Vardeny: *Phys. Rev. Lett.* **78** (1997) 729.