

Title	An Approach to Viscosity Calculations of Molten Iron and Its Dilute Binary Alloys
Author(s)	Okamoto, Ikuo; Iida, Takamichi; Kihara, Hiroshi
Citation	Transactions of JWRI. 1974, 3(1), p. 27-31
Version Type	VoR
URL	https://doi.org/10.18910/7786
rights	
Note	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

Osaka University

An Approach to Viscosity Calculations of Molten Iron and Its Dilute Binary Alloys[†]

Ikuo OKAMOTO*, Takamich IIDA** and Hiroshi KIHARA***

Abstract

Accurate theoretical values of viscosities are not available at present. Therefore, in this paper we propose an approach to viscosity calculations of liquid metals and dilute binary alloys.

Using the expression for liquid metals which has been derived by one of the authors, the calculated value of viscosity for molten iron at 1600°C is equal to 4.7 cP.

From the expression and experimental data, we present an attempt to calculate viscosities of dilute binary alloys from simple parameters. That is, viscosities of dilute iron-based binary alloys are approximately proportional to the square root of the product of atomic weight and melting point (°K), $(MT_m)^{1/2}$ of alloying elements.

Viscosities of molten iron due to one atomic percent of various alloying elements at 1600°C are expressed as follows:

$$\eta_{\text{Fe-dil}} \approx \eta_{\text{Fe}} + K[(MT_m)_X^{1/2} - (MT_m)_{\text{Fe}}^{1/2}]$$

where, $K \approx 3.5 \times 10^{-5}$ (from experimental data).

We have obtained same relation for liquid mercury and its dilute amalgams as well.

Consequently, if the value K is obtained experimentally, the approximate values for viscosities of dilute alloys can be estimated.

1. Introduction

Viscosity of liquid metals and alloys is of interest as a physical quantity in non-equilibrium state as well as diffusion and thermal conduction. It is so not only from practical aspects but from the fundamental point of view. In particular, viscosity of dilute alloys is quite important as the data which are used for practical operations and the clue for theoretical treatment of the viscosity of liquid alloys. Especially, experimental and theoretical studies on the viscosity of molten iron and its dilute alloys are desired. Nevertheless, few systematic studies have been made on this subject.^{1), 2)}

Born and Green³⁾, and Kirkwood and coworkers⁴⁾ have derived the expressions of viscosity of liquid as a function of intermolecular forces (potential) and pair correlation function based on statistical mechanical theory. At the present stage of statistical mechanics in regard to liquid, however, little is known about the molecular forces between same or foreign molecules (atoms), and furthermore the mathematical treatment of their expressions is considerably complicated. It is, therefore, very difficult to apply these expressions in practice.

Though the strictness of physical treatments is sacrificed to a certain extent, it would be useful that viscosities of many liquid metals and dilute alloys can be estimated by simple expressions, from the partial

standpoint.

In this paper, at first, the viscosity of pure molten iron at 1600°C was calculated from the expression which has been derived previously by one of the authors, and compared the values observed experimentally by a number of workers. Then, using the expression, an approach to viscosity calculations of dilute binary alloys has been proposed, and an expression for viscosities of molten iron with one atomic percent of various alloying elements at 1600°C was obtained with simple physical quantities.

2. Viscosity Calculation of Pure Molten Iron

Recently, we have discussed viscosity of liquid metals and have derived an expression within the following assumptions. All atoms in liquid state are regarded as equivalent harmonic oscillators with the same frequency and momentum is transferred between the nearest neighbour atoms in adjacent layers. The expression⁵⁾ is given by:

$$\eta = \frac{4}{3} \nu P(T) m \rho^2 \int_0^a g(r) r^4 dr \quad (1)$$

and

$$P(T) = 1 - \int_{T \geq \alpha T_b} \sqrt{\frac{3}{8\pi}} \exp\left(-\frac{3}{8} \left(\frac{\alpha T_b}{T} - 1\right)^2\right) d\left(\frac{\alpha T_b}{T} - 1\right) \quad (2)$$

[†] Received on Dec. 20, 1973

* Associate Professor

** Research Instructor

*** Director and Professor

where, ν vibrational frequency of an atom in liquid state.

$P(T)$: factor representing the probability which an atom in a state of vibration can stay at any position, that is, the life time of vibration.

m : atomic mass

ρ : average number of atoms per unit volume (number density)

$g(r)$: radial distribution function (pair correlation function)

a : upper of the first peak in $g(r)$

T_b : boiling point ($^{\circ}\text{K}$)

α : factor concerned with the energy needed to be able to move freely from a vibrating state to another site by translational motion (at the melting point, $\alpha \approx 1 \sim 1.5$)

Now, we will calculate the viscosity of pure molten iron at 1600°C . At present, the characteristic frequency of vibration of liquid state is not estimated theoretically, therefore, to first approximation, Lindemann's formular⁶ is used. The formular is:

$$\nu_m = C \sqrt{\frac{T_m}{MV_m}} \quad (3)$$

where, ν_m is the fundamental frequency in solid state at the melting point, c is constant ($2.8 \times 10^{12} \sim 3.1 \times 10^{12}$), T_m is the melting point ($^{\circ}\text{K}$), M the atomic weight and V_m the volume of a gram-atom at temperature T_m .

The calculated value of ν_m from the equation (3) is equal to $7.95 \times 10^{12} \text{ (sec}^{-1}\text{)}$. Value for the density of molten iron at 1600°C is from Lucas⁷: $6.94 \text{ (g.cm}^{-3}\text{)}$. Atomic mass, m , is equal to $9.28 \times 10^{-23} \text{ (g)}$, and number density, is equal to $7.48 \times 10^{22} \text{ (number)}$. The integration concerned with radial distribution function: $\int_0^a g(r)r^4 dr$ could be done by following assumption. In our phenomenological theory, the radial distribution function is introduced as a measure to estimate the number of atoms participating in the momentum transfer between the nearest neighbour atoms (the coordination numbers of atoms). By considering nearest neighbour interactions, this concept is useful in making a first order approximation to the macroscopic behaviour of liquid such as viscosity. But it is not yet well-defined how the area under the first peak of atomic radial distribution function is designated. In present work, the coordination numbers of atoms have been estimated by the method as shown in Fig. 1. That is, a corresponds to the first minimum on the right hand side of the first peak in $g(r)$. This method is considered the best mathematical one. The result of the integration is equal to $9.72 \times 10^{-39} \text{ (cm}^5\text{)}$. The observed value for the radial

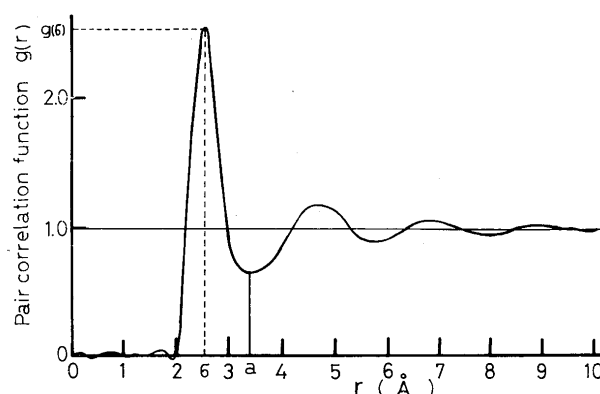


Fig. 1. Pair correlation function of molten iron at 1620°C (see Ref. 8).

distribution function of molten iron at 1620°C is from Waseda and Suzuki⁸.

When the vibrating frequency of atoms is estimated from the Lindemann's formular, $p(T) < 1$ is resonable, because the strength of the interaction between atoms in solid state is stronger than in liquid state. When the vibrational frequency of atoms in liquid is calculated by the Lindemann's formular, $P(T)$ is equal to $0.8 \sim 1$ for alkali metals, tin, lead and other metals. That is, if the frequency of atoms is determined from the Lindemann's formular and $P(T)$ is equal to $0.8 \sim 1$, the calculated values of viscosity of liquid metals at the melting point are in good agreement with experimental data.

Now, when $P(T)$ is equal to 0.9 for molten iron at the melting point, 1.4 is obtained for the factor α from the equation (2), and $P(T)$ is equal to 0.88 at 1600°C . From those results, the calculated value of viscosity for molten iron at 1600°C is equal to 4.7 cP. The calculated value is equal to 5.3cP, when $P(T)$ is equal to 1 at 1600°C , and 4.3cP when $P(T)$ is equal to 0.8, respectively. Viscosity of molten iron as determined by a number of workers and the calculated values are shown in Fig. 2.

3. An Approach to Viscosity Calculations of Dilute Binary Alloys

From experimental data, for the majority of liquid metals, the integral term in the equation (1) can be expressed approximately in the following form:

$$\int_0^a g(r)r^4 dr \approx 0.35g(\sigma)\sigma^5 \quad (4)$$

where, σ is the average interatomic distance. Furthermore, using a relationship $\rho \sim 1/\sigma^3$, the equation (1) is approximated by:

$$\eta \approx 0.47\nu P(T)mg(\sigma) \cdot \frac{1}{\sigma} \quad (5)$$

and, using the Lindemann's formular for ν , we have

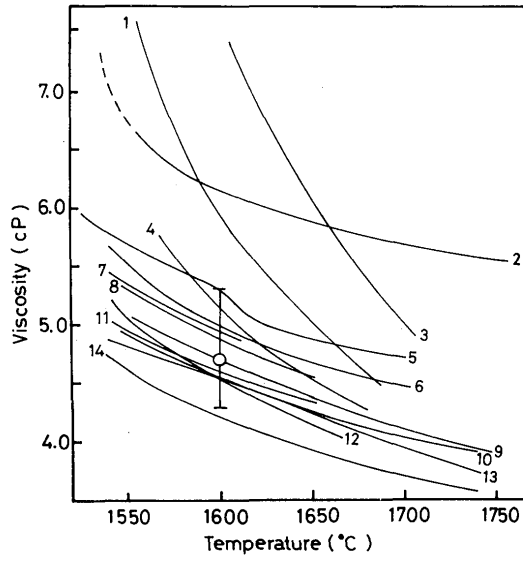


Fig. 2. Viscosity of molten iron as determined by a number of workers and calculated value using the equation (1)
 (1: vatolin et. al, 2: Barfield et al, 3: Samarin, 4: Wen Li-Shin
 5: Adachi, Morita et al, 6: Saito and Nakanishi, 7: Froberg,
 8: Schenck et al, 9: Saito et al, 10: Cavalier, 11: Narita and
 Onoe, 12: Kawai and Tuji, 13: Lucas, 14: Thile, Φ: calculated value).

$$\eta \approx \frac{0.47 C M T_m^{\frac{1}{2}} P(T) g(\sigma)}{N M^{\frac{1}{2}} V^{\frac{1}{2}} \sigma}$$

$$= j \left\{ \frac{P(T) g(\sigma)}{V^{\frac{1}{2}}} \right\} (M T_m)^{\frac{1}{2}} \quad (6)$$

where, N is the Avogadro's number

$$j = \frac{0.47c}{N^{\frac{1}{2}}}, \quad \sigma \approx \left(\frac{V}{N} \right)^{\frac{1}{3}}$$

(Though j is equal to 2×10^{-4} from the equation (6), experimental values of viscosity for many liquid metals agree well with the calculated values, when j is equal to 2.5×10^{-4}).

It is needless to say that viscosity is the dynamic physical quantity in non-equilibrium state, therefore, the thermodynamics deduced from the equilibrium state cannot, obviously, be applied. However, if the idea of partial molar quantity of thermodynamics is allowed to use as an analogy in numerical treatment for discussing viscosity of liquid binary alloys, the viscosity of A-B binary liquid alloys which consists of n_A at % of A-atom and n_B at % of B-atom may be expressed in the following form:

$$\eta_{A-B} = \frac{1}{100} (n_A \eta_A^* + n_B \eta_B^*) \quad (7)$$

where,

$$\eta_A^* \equiv \left(- \frac{\partial \eta_{A-B}}{\partial n_A} \right)_{n_B, T, P}; \quad \eta_B^* \equiv \left(- \frac{\partial \eta_{A-B}}{\partial n_B} \right)_{n_A, T, P}$$

Using the relationship $n_A + n_B = 100$, we have

$$\eta_{A-B} \equiv \eta_A^* + \frac{n_B}{100} (\eta_B^* - \eta_A^*) \quad (8)$$

Now, let us consider the case that the concentration of B-atom is extremely dilute. In such case, the state of A-atom in the dilute solution may be regarded as almost the same as that in the pure liquid which consists only of A-atom. Then, we obtain

$$\eta_A^* \approx \eta_A \quad (9)$$

where, η_A is viscosity of pure liquid metals which consists only of A-atoms. Therefore, substituting η_A for η_A^* in the equation (8) yields the following expression for the viscosity of dilute binary alloys.

$$\eta_{A-B} = \eta_A + \frac{n_B}{100} (\eta_B^* - \eta_A) \quad (10)$$

Now, let us consider the physical meanings of the expression (10). If B^* is used to designate the atom in liquid consists of B-atoms that are completely surrounded by A-atoms and have the interaction with them, η_B^* in the equation (10) is considered to be the viscosity of pure liquid which consists only of B^* -atom, and is also given as the intercept at $n_A = 0$ of the tangent to the curve of η_{A-B} at the infinite dilute concentration of the component B as shown in Fig. 3.

Then, we may apply the above idea to the viscosity of liquid binary alloys. As far as the binary alloys containing several atomic percentages of solute can be approximately regarded as dilute solution, the viscosity of dilute binary alloys, thus, is given from the equation (10) as follows:

$$\eta_{M-X} \approx \eta_M + \frac{n_X}{100} (\eta_X^* - \eta_M) \quad (11)$$

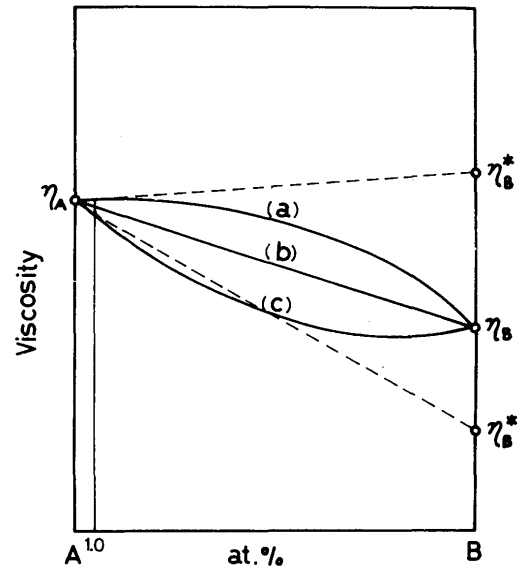


Fig. 3. Schematic diagram illustrating partial viscosity in dilute A-B binary solution. (--- Ideal dilute solution)

where, the subscripts M-X, M and X represent the dilute alloy, the base metal and the alloying elements respectively. Using our present expression (6), further the above equation may be rewritten in the following expression:

$$\eta_{M-X} \approx \eta_M + j n_X \left\{ \frac{P(T)g(\sigma)}{V^{1/2}} (MT_m)^{1/2} \right\}_{X^*} - \left\{ \frac{P(T)g(\sigma)}{V^{1/2}} (MT_m)^{1/2} \right\}_M \quad (12)$$

where, the subscript X^* represents the alloying elements whose atoms are completely surrounded by the base metal atoms.

In the equation (12), of the terms represented by the subscript X^* , $P(T)$, which is a function of boiling point, does not largely depend on it, and $g(\sigma)$ and $V^{1/2}$ may be supposed to be close to the value of base metal rather than that of alloying element by assuming their state described above. On the other hand, the values of M and T_m would not probably be so different from that of the alloying element, even if the alloying element is placed on that state. (T_m in this paper refers to interatomic bond strength).

Thus, assuming inherent characteristic of alloying element can be expressed by the term $(MT_m)^{1/2}$, the term denoted by the subscript X^* is approximately represented as follows:

$$\left\{ \frac{P(T)g(\sigma)}{V^{1/2}} (MT_m)^{1/2} \right\}_{X^*} \approx \left\{ \frac{P(T)g(\sigma)}{V^{1/2}} \right\}_M (MT_m)^{1/2}_X \quad (13)$$

However, as presently it is very difficult to treat strictly the above-mentioned relation from the theoretical point of view, we take this problem into consideration on the basis of experimental results. For an example, viscosities of iron-based dilute binary alloys (1 at %: at 1600°C⁹⁾) which were determined by a number of workers, are plotted as a function of $(MT_m)^{1/2}$ in Fig. 4. Though discrepancies exist between observations of different workers, it is considered from the experimental results shown in Fig. 4 that the relation in the expression (13) can be expected to hold in these iron-based dilute alloy systems. Now, viscosities of molten iron and its alloys have been measured by the oscillational vessel method. This method of measuring viscosity has many practical advantages at elevated temperature, but there are mathematical difficulties in making the calculations, and a precise technique for viscosity measurements of liquid metal and alloys at high temperature has not been well established. Furthermore, the viscosity-standard liquid for liquid metals has not yet established. From these reasons, it is understandable that discrepancies exist between the data which have been reported.

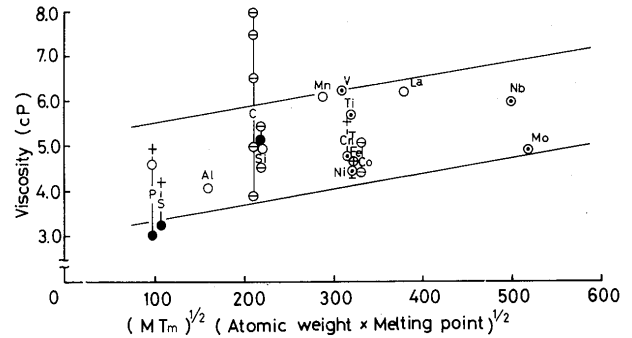


Fig. 4. Change in the viscosity of molten iron due to one atomic percent of various alloying elements at 1600°C.
(⊕: calculated value, ○: Romanov and Kochegarov, ⊙: Narita and Onoe, ●: Suzuki and Maekawa, +: Vostryakov, vatolin and Yesin, ⊖: others)

Then the observed values by Romanov and Kochegarov^{9),10)} and Suzuki and Maekawa⁹⁾ are shown in Fig. 5. As shown in Fig. 5, it is obvious that the relation in the expression (13) can be expected to hold approximately in this case. In addition, the above relation is found to hold also for the viscosities of mercury-based dilute binary alloys²⁾ as shown in Fig. 6. (The viscosities of mercury and its dilute binary alloys have been determined by the capillary method.) From these results, we consider that the equation (13) holds on viscosities of other metal-based dilute binary alloys as well. Consequently, using the equation (13), viscosity of dilute binary alloys can be expressed as follows:

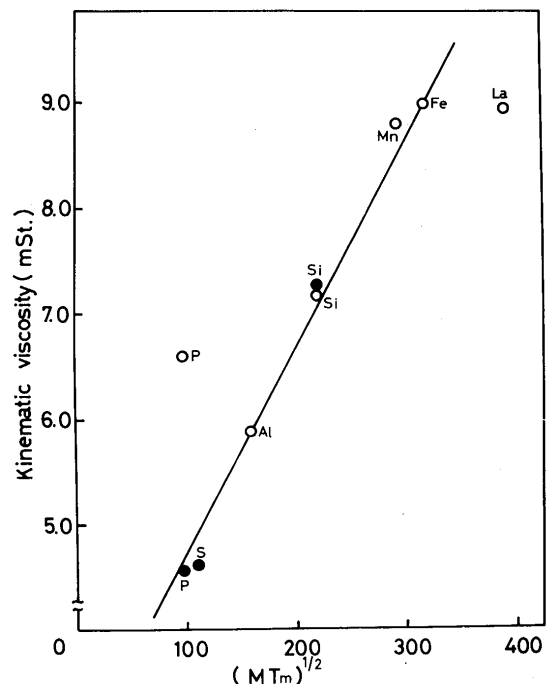


Fig. 5. Change in the kinematic viscosity of molten iron due to one atomic percent of various alloying elements at 1600°C.
(○: Romanov and Kochegarov, ●: Suzuki and Maekawa)

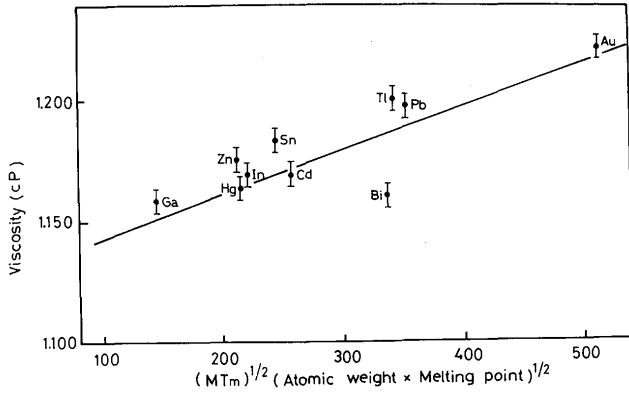


Fig. 6. Change in the viscosity of mercury with one atomic percent of various alloying metals at 140°C (see Ref. 2).

$$\eta_{M-X} \approx \eta_M + jn_X \left\{ \frac{P(T)g(\sigma)}{V^{2/3}} \left\{ (MT_m)_X^{1/2} - (MT_m)_M^{1/2} \right\} \right\} \quad (14)$$

and putting,

$$jn_X \frac{P(T)g(\sigma)}{V^{2/3}} \equiv K$$

we have

$$\eta_{M-X} \approx \eta_M + K \left\{ (MT_m)_X^{1/2} - (MT_m)_M^{1/2} \right\} \quad (15)$$

Viscosities of molten iron due to one atomic percent of various alloying elements at 1600°C are expressed from Fig. 4 as follows:

$$\eta_{Fe-die} \approx \eta_{Fe} + 3.5 \times 10^{-5} \left\{ (MT_m)_X^{1/2} - 317 \right\} \quad (16)$$

Accordingly, the expression represented by the equation (15) may be considered to hold not only on the viscosities of iron or mercury-based dilute binary alloys, but on viscosities of other metal-based dilute alloys, and if the value K in the equation (15) is determined from few experimental data for certain base metals, viscosities of those metal-based dilute binary alloys can be evaluated by the use of equation (15).

4. Conclusion

Using the expression for mono-atomic liquid metals which has been derived by one of the authors previously, the viscosity of molten iron at 1600°C was calculated.

A consideration was made on viscosity of dilute binary alloys, and the obtained results may be summarized as follows.

An equation for viscosities of dilute binary alloys could be expressed in the terms of the square root of the product of atomic weight and melting point of alloying elements as a parameter.

Consequently, if the value K in the equation (15) is determined experimentally or theoretically for certain base metals, viscosities of those metal based dilute binary alloys can be estimated easily by use of the equation (15).

References

- 1) Y. Okajima and M. Shimoji; Trans. JIM., 13 (1972), 255.
- 2) T. Iida, A. Kasama, Z. Morita, I. Okamoto and S. Tokumoto; J. Japan Inst. Metals., 37-8 (1973), 841., (in Japanese)
- 3) M. Born and H. S. Green; Proc. Roy. Soc. A. 190 (1947), 455.
- 4) J. G. Kirkwood, E. P. Buff and M. S. Green; J. Chem. Phys., 17 (1949), 988.
- 5) H. Kihara, I. Okamoto and T. Iida; Trans. JWRI. 1 (1972), 33.
- 6) F. A. Lindemann; Phys. Z., 11 (1910), 609.
- 7) L. D. Lucas; Compt. Rend., 250 (1960), 1850.
- 8) Y. Waseda and K. Suzuki; Phys. Stat. Sol., 39 (1970), 669.
- 9) The Iron Steel Inst. Japan (Spec. Rep); No. 12 (1972), 32. (in Japanese)
- 10) A. A. Romanov and V. G. Kochegarov; Fizika Metall., 18 (1964), 869.