

Title	High-speed fabrication of clear transparent cellulose nanopaper by applying humidity-controlled multi-stage drying method
Author(s)	Li, Chenyang; Kasuga, Takaaki; Uetani, Kojiro et al.
Citation	Nanomaterials. 2020, 10(11), p. 2194
Version Type	VoR
URL	https://hdl.handle.net/11094/78433
rights	© 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is licensed under a Creative Commons Attribution 4.0 International License.
Note	

## The University of Osaka Institutional Knowledge Archive : OUKA

https://ir.library.osaka-u.ac.jp/

The University of Osaka





## High-Speed Fabrication of Clear Transparent Cellulose Nanopaper by Applying Humidity-Controlled Multi-Stage Drying Method

Chenyang Li<sup>1</sup>, Takaaki Kasuga<sup>1</sup>, Kojiro Uetani<sup>1</sup>, Hirotaka Koga<sup>1</sup> and Masaya Nogi<sup>1,\*</sup>

- <sup>1</sup> The Institute of Scientific and Industrial Research, Osaka University, 8-1 Mihogaoka, Ibaraki, Osaka 567-0047, Japan; lichenyang@eco.sanken.osaka-u.ac.jp (C.L.); tkasuga@eco.sanken.osaka-u.ac.jp (T.K.); uetani@eco.sanken.osaka-u.ac.jp (K.U.); hkoga@eco.sanken.osaka-u.ac.jp (H.K.)
- \* Correspondence: nogi@eco.sanken.osaka-u.ac.jp; Tel.: +81-6-6879-8441 (M.N.)

**Table S1.** Drying time, transit concentration (the dispersion transit from constant drying rate period to falling drying rate period), and haze of obtained cellulose nanopaper. The drying times listed include the total drying time, constant-drying-rate-period time, and falling-drying-rate-period time. The relative humidity and temperature were constant in all the periods under all the conditions.

Relative Temperature humidity (°C)	Temperature	Total drying time (h)	Constant drying rate period		Falling drying rate period		Transit	Haze
	(°C)		Period time (h)	Ratio (%)	Period time (h)	Ratio (%)	concentration (wt %)	(%)
RH 35%	45	12.8	9.3	73	3.5	27	2.45	1.00
RH 35%	55	8	5.7	71	2.3	29	2.32	1.02
RH 35%	65	6.3	4.8	76	1.5	24	2.52	1.00
RH 35%	75	5.3	3.7	70	1.6	30	2.46	0.96
RH 35%	85	4.5	3.3	73	1.2	27	2.38	0.99


Relative Temperature humidity (°C)	Temperature	Total	Constant drying rate period		Falling drying rate period		Transit	Haze
	drying time (h)	Period	Ratio	Period	Ratio	concentration (wt %)	(%)	
		( )	time (h)	(%)	time (h)	(%)		
RH 45%	45	14.6	11.6	79	3.0	21	3.96	0.94
RH 45%	55	11.7	8.4	72	3.3	28	3.72	0.85
RH 45%	65	7.6	5.9	78	1.5	22	3.34	0.91
RH 45%	75	5.8	4.7	81	1.6	19	3.97	0.98
RH 45%	85	5	3.9	78	1.2	22	4.35	0.95

Relative Temperature humidity (°C)	Temperature	Total drying time (h)	Constant drying rate period		Falling drying rate period		Transit concentration	Haze
	(°C)		Period	Ratio	Period	Ratio	(wt %)	(%)
		time (ii)	time (h)	(%)	time (h)	(%)	(₩1 /0)	
RH 55%	45	16.3	13.9	85	2.4	15	4.27	0.75
RH 55%	55	12.1	10.4	86	1.7	14	4.08	0.76
RH 55%	65	8.6	6.8	79	1.8	21	4.07	0.78
RH 55%	75	7.1	5.8	82	1.3	18	3.46	0.93
RH 55%	85	4.5	3.3	73	1.2	27	2.38	0.91

Relative	Temperature	Constant drying	Falling drying	Transit	Haze
humidity	(°C)	rate period	rate period	concentration	(%)

		Total drying time (h)	Period time (h)	Ratio (%)	Period time (h)	Ratio (%)	(wt %)	
RH 65%	45	18.9	15.9	84	3.0	16	4.6	0.82
RH 65%	55	14.5	12.7	88	1.8	12	4.75	0.78
RH 65%	65	12.9	11.0	85	1.9	15	4.72	0.73
RH 65%	75	9.7	7.9	81	1.8	19	4.06	0.88
RH 65%	85	8	6.5	81	1.5	19	4.61	0.74

Relative	Relative Temperature humidity (°C)	Total	Constant drying rate period		Falling drying rate period		Transit	Haze
humidity		drying time (h)	Period time (h)	Ratio (%)	Period time (h)	Ratio (%)	concentration (wt %)	(%)
RH 75%	45	25.2	23.7	94	1.5	6	9.33	0.61
RH 75%	55	20.4	18.9	93	1.5	7	8.72	0.67
RH 75%	65	17.5	15.3	87	2.2	13	6.98	0.64
RH 75%	75	12.8	11.5	90	1.3	10	7.28	0.72
RH 75%	85	11.3	10.1	89	1.2	11	7.82	0.67

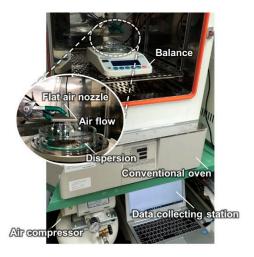

**Figure S1**. The air-flow system used to control the humidity in the conventional oven. The air-flow system was a flat air nozzle with 13 orifices of 9 mm diameter connected to an air compressor. The system softly blew air (air flow rate: 0.4-0.5 L/min) toward the dispersion to remove the saturated water vapor at the water/air interface. When the air-flow system was blowing, the RH directly above the water/air interface was reduced, thus increasing the evaporation rate.




Figure S2. X-ray diffraction profiles of nanopaper dried under different conditions. During the drying process, the temperature was  $55\,^{\circ}$ C for the entire period, and the RH was 55% during the constant-drying-rate period and 15%, 55%, or 85% during the falling-drying-rate period.