



Title	Formation of Cr ₃ C ₂ /Ni-Cr Alloy Layer by an Electron Beam Cladding Method and Evaluation of the Layer Properties
Author(s)	Abe, Nobuyuki; Tsukamoto, Masahiro; Miyake, Shoji et al.
Citation	Transactions of JWRI. 2001, 30(1), p. 135-136
Version Type	VoR
URL	https://doi.org/10.18910/8424
rights	
Note	

The University of Osaka Institutional Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

The University of Osaka

Formation of $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ Alloy Layer by an Electron Beam Cladding Method and Evaluation of the Layer Properties[†]

Nobuyuki ABE*, Masahiro TSUKAMOTO**, Shoji MIYAKE***,
Fumiaki KURIYAMA****, Junji MORIMOTO***** and Michio TOMIE*****

KEY WORDS: (Electron beam cladding) ($\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer) (Vickers hardness) (Erosion resistance) (Corrosion resistance)

The trend toward more efficient utilization of energy and resource, as well as the need for advanced functionality, has led to a growing demand for materials with high erosion and corrosion resistance. Chemical coating methods using heavy metals are no longer a viable choice because of global environmental concerns and the threat of environmental pollution. Thus, there is a pressing need for new surface modification technologies that can form surface layers with superior functional properties. The authors have been developing an electron beam cladding method employing a high energy density electron beam and a powder feeder¹⁻³⁾. In this report, a hard surfacing layers with high corrosion and erosion resistance were successfully formed on mild steel employing the electron beam cladding method with $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ mixed alloy powder, and their properties were examined.

Figure 1 shows a schematics drawing of the experimental apparatus. A 30kW-class electron beam welder with acceleration voltage of 40kV was used as the heat source. The electron beam was focused by two magnetic focusing lenses to achieve a high energy density of over $200\text{kW}/\text{cm}^2$ at a focal point when the output power was 1600W. A powder feeder designed to work stably under vacuum conditions supplied mixed powder. In order to form a hard surfacing layer with high corrosion and erosion resistance, $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy powder was used. The chemical composition of the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$

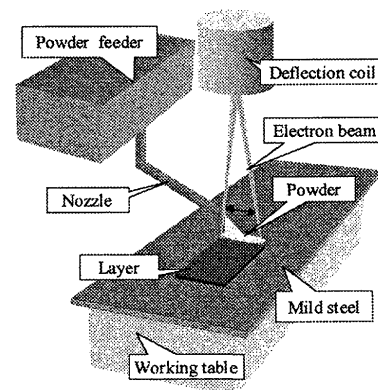


Fig. 1 Schematic drawing of the experimental apparatus

Table 1 Chemical composition of the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy powder

Cr_3C_2	Ni-Cr	Particle size (μm)
50%	50%	8.8-55

alloy powder is shown in **Table 1**.

SS400 mild steel plate was used as the substrate. The powder was stably supplied at a constant feed rate of $0.4\text{g}/\text{sec}$ onto the substrate, which moved at a constant speed of $5\text{mm}/\text{sec}$. The electron beam was oscillated at an amplitude of 20mm using a deflection coil and function generator. The $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer was formed on the substrate by the irradiation of the scanning electron beam at a high speed of $1600\text{mm}/\text{sec}$.

The cladding layers were examined using optical microscope, electron probe micro analyzer (EPMA),

[†]Received on July 31, 2001

*Associate professor

**Research Associate

***Professor

****Graduate school, Kinki University

*****Professor, Kinki University

Transactions of JWRI is published by Joining and Welding Research Institute of Osaka University, Ibaraki, Osaka 567-0047, Japan.









	Beam current (mA)			
	25	30	35	40
Surface				
Cross-section				
HV	791	723	663	612

Fig. 2 Surface appearance, cross section and Vickers hardness of $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy cladding layers

Vickers hardness test (load: 300g, load time: 15sec), sand erosion test (ACT-JP method, Abrasive: mild steel, jet air pressure: 5.0kg/cm^2) immersion corrosion test (corrosion solution: H_2SO_4 aqueous solution, corrosion time: 10 hours).

The surface appearance, cross section and Vickers hardness of $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy cladding layers formed at a variety of beam currents are shown Fig. 2. At a beam current of 25mA, porosity occurred and un-melted powder was recognized on the surface of the cladding layer. Layers without porosity were obtained at beam current of 30mA and 35mA. The layer's thickness was about $100\mu\text{m}$. At a beam current of 40mA, however, the substrate material mixed with the surface layer. The Vickers hardness of the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer formed at a beam current of 25mA was 791HV. However, with increasing beam current, Vickers hardness of the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer decreased. This is thought due to decomposition of the Cr_3C_2 particles as a high-hardness component by electron beam irradiation.

Figure 3 shows the EPMA results with the $\text{K}\alpha$ lines of Cr, Ni, Fe and C for the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer formed at a beam current of 30mA. The Cr_3C_2 particles are evenly dispersed within the matrix of the Ni-Cr alloy. There is no mixing of iron with the cladding layer.

Figure 4 shows the results of immersion corrosion tests and a sand erosion tests for SUS304 steel plate, SS400 steel plate and a $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer formed under the optimum beam condition of 35mA. The specimens were immersed in a 50% H_2SO_4 aqueous solution for 10 hours and the amount of corrosion was measured. The corrosion rate of

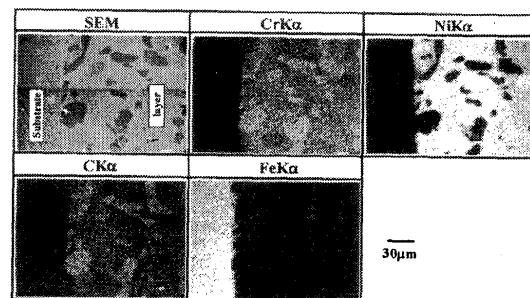


Fig. 3 EPMA results of $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer

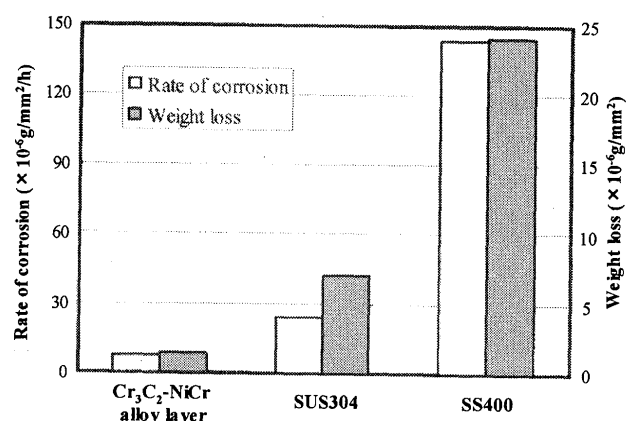


Fig. 4 The results of an immersion corrosion test and sand erosion test for $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer

the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer was very low, being only 25% that of stainless steel and 7% that of mild steel. In the sand erosion test, the abrasive (mild steel, 450HV) was sprayed onto the specimen surface with a high speed, and the erosion resistance was determined by specimen weight loss.

The erosion loss of the $\text{Cr}_3\text{C}_2/\text{Ni-Cr}$ alloy layer was also very low, being only 30% that of stainless steel and 5% that of mild steel.

By using the electron beam cladding method, a $\text{Cr}_3\text{C}_2\text{-NiCr}$ alloy layer with a high hardness of 791HV as well as high erosion and corrosion resistance was successfully formed on mild steel plate.

References

- 1) ABE N., BABA S., MORIMOTO J., and TOMIE M.; Trans. of JWRI, Vol.26, No.2, 1997, p95.
- 2) ABE N., DOI C., MORIMOTO J., and TOMIE M., Trans. of JWRI, Vol.27, No.1, 1998, p111.
- 3) ABE N., DOI C., TSUKAMOTO M., MIYAKE S., MORIMOTO J. and TOMIE M.: Trans. of JWRI, Vol.28, No.2, 1999, p75.