

Title	Supramolecular sulfur-containing polymers with hydrogen bonding
Author(s)	Kobayashi, Yuichiro; Yamagishi, Yuki; Nishimura, Ryuto et al.
Citation	Journal of Sulfur Chemistry. 2023, 44(4), p. 406-415
Version Type	AM
URL	https://hdl.handle.net/11094/91261
rights	
Note	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

Osaka University

Supramolecular sulfur-containing polymers with hydrogen bonding

Yuichiro Kobayashi,^{a,b,c*} Yuki Yamagishi,^a Ryuto Nishimura,^a Chun-Lin Xiao,^a Daiki Kitano,^a Akiyoshi Horiguchi,^a Shun Hashimoto,^a Hiroyasu Yamaguchi^{a,b,c *}

^aDepartment of Macromolecular Science, Graduate School of Science, Osaka University, 1-1 Machikaneyama-cho, Toyonaka, Osaka 560-0043, Japan

^bInnovative Catalysis Science Division, Institute for Open and Transdisciplinary Research Initiatives (ISC-OTRI), Osaka University, 2-1 Yamada-oka, Suita, Osaka 565-0871, Japan

^cProject Research Center for Fundamental Sciences, Graduate School of Science, Osaka University, Toyonaka, Osaka 560-0043, Japan

kobayashi11@chem.sci.osaka-u.ac.jp

hiroyasu@chem.sci.osaka-u.ac.jp

Supramolecular sulfur-containing polymers with hydrogen bonding

Although sulfur-containing polymers have been realized by various methods such as copolymerization and reverse vulcanization, there are few reports on the synthesis of supramolecular sulfur-containing polymers in which a supramolecular polymer is fused with a sulfur-containing polymer. Herein, we prepare a supramolecular sulfur-containing polymer by introducing a 2-ureido-4[1*H*]pyrimidinone (UPy) unit at both ends of linear sulfur and connecting between the UPys via hydrogen bonding.

Keywords: sulfur-containing polymer, sulfur, supramolecular polymer, hydrogen bonding

1. Introduction

Sulfur is an abundant resource. Sulfur-containing polymers have attracted attention as alternatives to carbon polymers fabricated from exhaustible petroleum resources.^[1-4] Additionally, sulfur-containing polymers exhibit various properties not observed in carbon polymers such as transparency and capacitance. Hence, sulfur-containing polymers have potential in lenses and lithium-ion batteries.^[5-7]

Although polysulfide polymers can be prepared by simply heating sulfur (S₈),^[8,9] the obtained polysulfide polymers are unstable. They are prone to depolymerization during the cooling process and exhibit a low solubility in common organic solvents. To overcome these problems, a radical copolymerization method and a polycondensation method have been developed.^[10,11] The resultant sulfur-containing polymers are soluble in common organic solvents. For example, a sulfur-containing polymer obtained by copolymerization of S₈ and styrene acquired the solubility derived from polystyrene and were dissolved in chloroform (CHCl₃), tetrahydrofuran (THF), and dimethyl sulfoxide (DMSO). In addition, to overcoming the shortcomings of sulfur-containing polymers, these methods realize sulfur-containing polymers with functional properties such as

self-healing.^[12-16] Recently, an inverse vulcanization method in which di-vinyl and tri-vinyl monomer and sulfur are copolymerized has been reported.^[17] The obtained sulfur-containing polymers were stable for a long time at r.t. in air and high capacitance and repeatable charge/discharge performance. Thus, they have potential as positive electrode materials in lithium-ion batteries. Due to these diverse demands and requirements for functional sulfur-containing polymer materials, polymer chemistry approaches such as a copolymerization method and an inverse vulcanization technique have been developed as method for producing polysulfide polymers. Various demands and requirements for polysulfide polymers in the recent years have prompted the development of new methodologies for obtaining polysulfide polymers.

In this research, we report a new methodology to synthesize a polysulfide polymer via a supramolecular chemistry approach. For this purpose, we focused on supramolecular polymers, which were prepared by connecting monomers with each other through non-covalent bonds.^[18-21] Unlike ordinary polymers formed from covalent bonds, supramolecular polymers exhibit reversible formation and dissociation. Consequently, they are suitable for a wide range of applications, including self-healing materials, stimuli-responsive materials, and catalysts.^[22-26] Supramolecular formation of sulfur-containing polymers may give functional supramolecular sulfur-containing polymers.^[27,28] Herein, we prepare a sulfur-containing organic compound with hydrogen bonding unit, 2-ureido-4[1*H*]pyrimidinone (UPy), at both ends to give a main-chain type supramolecular sulfur-containing polymers (poly(LS-UPy)) (Fig. 1).

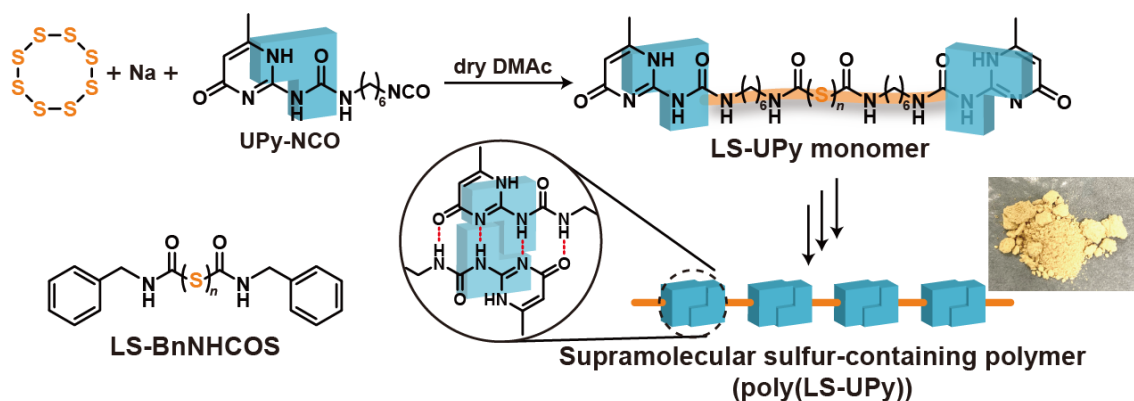


Figure 1. (a) Preparation of supramolecular sulfur-containing polymers with hydrogen bonding units (poly(LS-UPy)) and chemical structure of a reference compound (LS-BnNHCOS). The inserted photograph is poly(LS-UPy).

2. Results and Discussion

Figure 1 outlines the synthesis of the LS-UPy monomer. S_8 , sodium metal (Na), and 2-(6-isocyanatohexylaminocarbonylamino)-6-methyl-4[1H]-pyrimidinone (UPy-NCO)^[29] were stirred in dry *N,N*-dimethylacetamide (DMAc) at 70 °C under a N_2 atmosphere. Then the resultant precipitate was collected by filtration and washed with water and $CHCl_3$ to remove residual reagents. In the 1H NMR spectrum of the obtained sample, the signal of methylene protons (A, B, and C in Fig. 2) near the isocyanate groups shifted. In addition, there are no diffraction peaks for S_8 in the X-ray powder diffraction (XRD) measurement of the obtained sample (Figures S1), suggesting there are no raw materials left in the obtained sample. Elemental analysis was conducted to investigate the chain length (n) of linear sulfur in the LS-UPy, which was 2.1. These results confirm the preparation of the LS-UPy monomer.

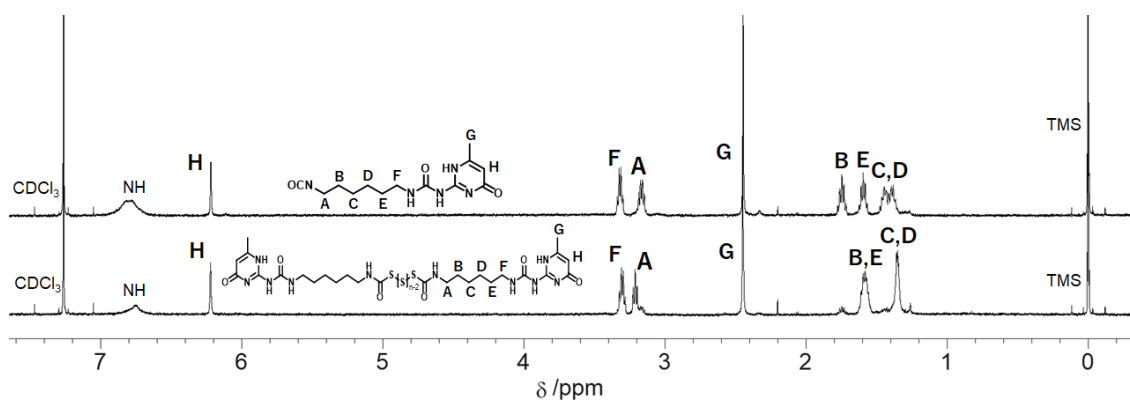


Figure 2. ^1H NMR spectra of UPy-NCO (a) and LS-UPy (b) in $\text{CDCl}_3/\text{TFA-}d$ (3.6 wt%) at r.t.

We performed FT-IR and solid-state ^1H NMR spectroscopic analyses to investigate the formation of hydrogen bonds between the UPy units in the poly(LS-UPy). The FT-IR spectrum contained peaks derived from the NH stretching vibration bands at 3145 cm^{-1} and 3220 cm^{-1} (Fig. 3a). These observations are consistent with the previous report^[30] in which quadruple hydrogen bonds appeared between UPy units. In addition, the solid-state ^1H NMR spectrum showed three amide proton peaks ($\delta = 12.2$ ppm, 13.5 ppm, and 14.6 ppm) ascribed to hydrogen bonding (Fig. 3b).^[30] These results indicate that hydrogen bonding links the LS-UPy monomers.

In order to investigate the molecular weight of poly(LS-UPy), we attempted to perform gel permeation chromatography (GPC) measurements, however, the GPC measurements were unsuccessful because poly(LS-UPy) did not dissolve in CHCl_3 due to the hydrogen bonding between the UPy units. However, when trifluoroacetic acid (TFA), a hydrogen bonding inhibitor, was added to Poly(LS-UPy) in CHCl_3 , poly(LS-UPy) immediately dissolved. Thus, the degree of polymerization (DP) of poly(LS-UPy) was calculated through end-group analysis by ^1H NMR using a mixed solvent of $\text{CDCl}_3/\text{TFA-}d$. The peaks at 3.16 and 1.74 ppm were ascribed to $\text{H}_{\text{A}'}$ and $\text{H}_{\text{B}'}$ of the end group of poly(LS-UPy), respectively (Fig. 4). Because $\text{H}_{\text{A}'}$ overlapped with H_{A} , the

ratio of $H_{B'}$ and H_B was used to determine the DP of poly(LS-UPy). DP of the poly(LS-UPy) was about 10. We also investigated the DP value using a diffusion-ordered 1H NMR (DOSY NMR) measurement in a mixed solvent of $CDCl_3/TFA-d$. The diffusion coefficient (D) value of poly(LS-UPy) dissolved in 1.4 wt% TFA in $CDCl_3$ ($5.1 \times 10^{-11} m^2 \cdot s^{-1}$) (Fig. 5a) was smaller than that of poly(LS-UPy) dissolved in 10 wt% TFA in $CDCl_3$ ($6.4 \times 10^{-11} m^2 \cdot s^{-1}$) (Fig. 5b). In the case of LS-BnNHCOS, which lacked UPy unit and had only a urethane bond, the value of D remained constant as the TFA concentration changed (Figs. 5c and 5d). The DP of the poly(LS-UPy) decreased upon the addition of TFA. The hydrodynamic radius (r_H) of the poly(LS-UPy) was determined using the Stokes-Einstein equation.^[31] The r_H value of the poly(LS-UPy) in 1.4 wt% TFA in $CDCl_3$ was 9.1 nm. The size of the LS-UPy monomer calculated using MM2 was 0.80 nm, suggesting that the DP of poly(LS-UPy) was about 11. These results are almost same as the DP calculated from the end-group analysis via 1H NMR (DP = 10), showing that poly(LS-UPy) is a supramolecular sulfur-containing polymer with molecular weight of 7,000 linked by hydrogen bonding between the UPy units.

Since poly(LS-UPy) was disassembled by addition of TFA, poly(LS-UPy) should form again by removal of TFA. We remove TFA and performed DOSY NMR measurement. poly(LS-UPy) with high r_H was observed (Figs. 6a and S4), which was similar to poly(LS-UPy) before disassembly. This result indicates that poly(LS-UPy) formed again. These results show that poly(LS-UPy) can be freely disassembled and re-assembled in response to stimuli (Fig. 6b).

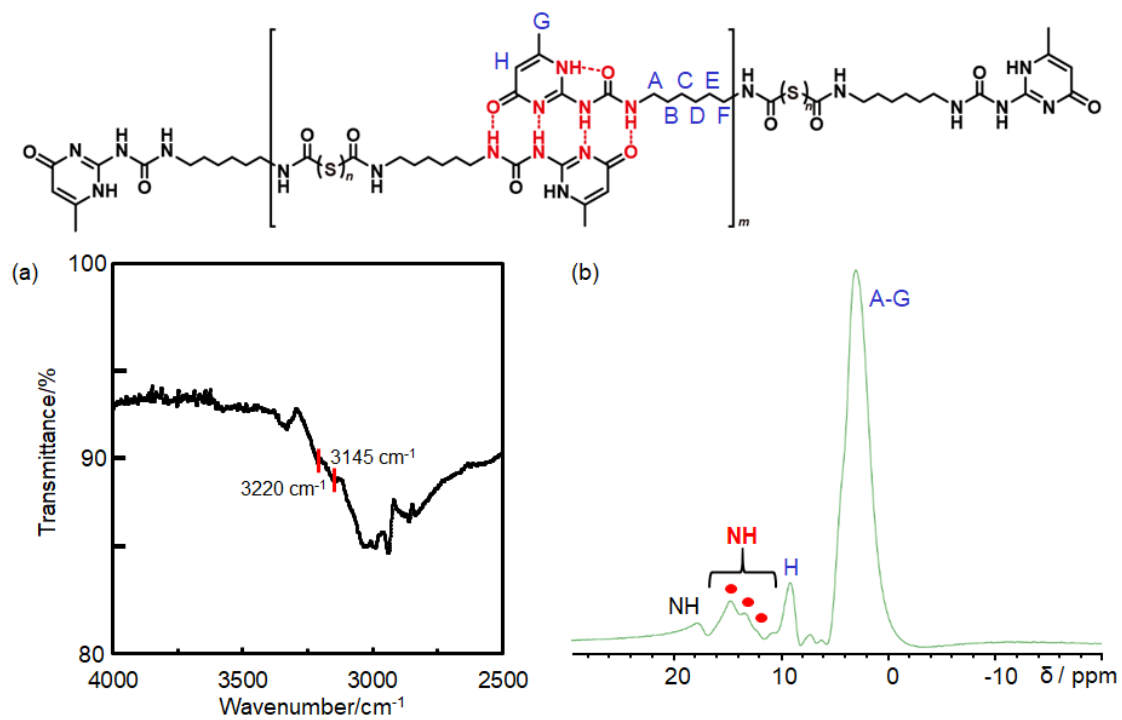


Figure 3. (a) FT-IR and (b) solid-state ¹H NMR spectra of poly(LS-UPy).

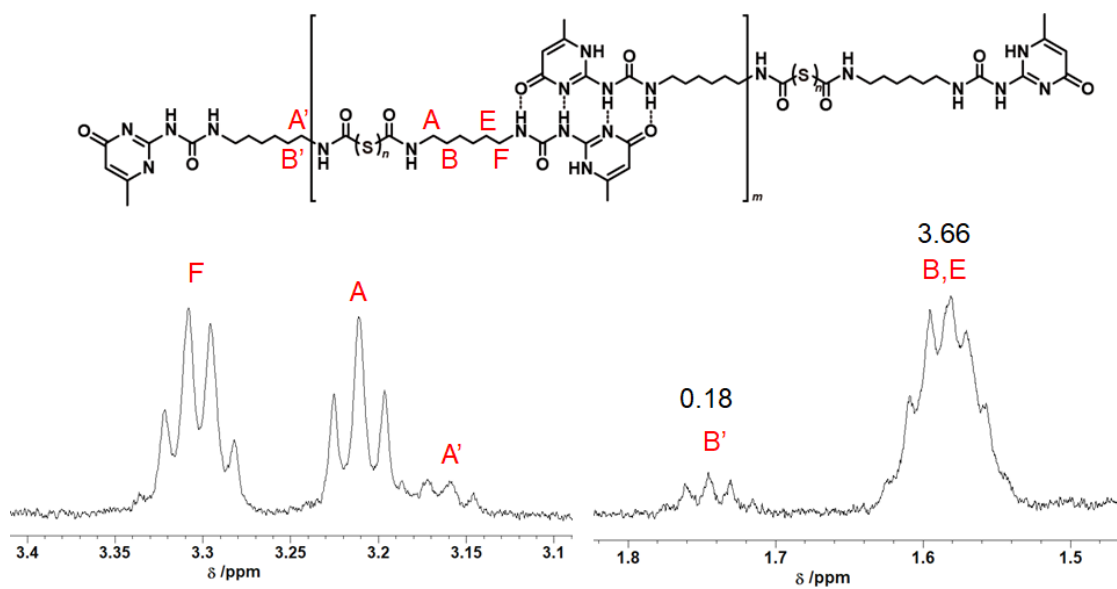


Figure 4. ¹H NMR spectrum of LS-UPy in CDCl₃/TFA-*d* (1.6 wt%) at r.t.

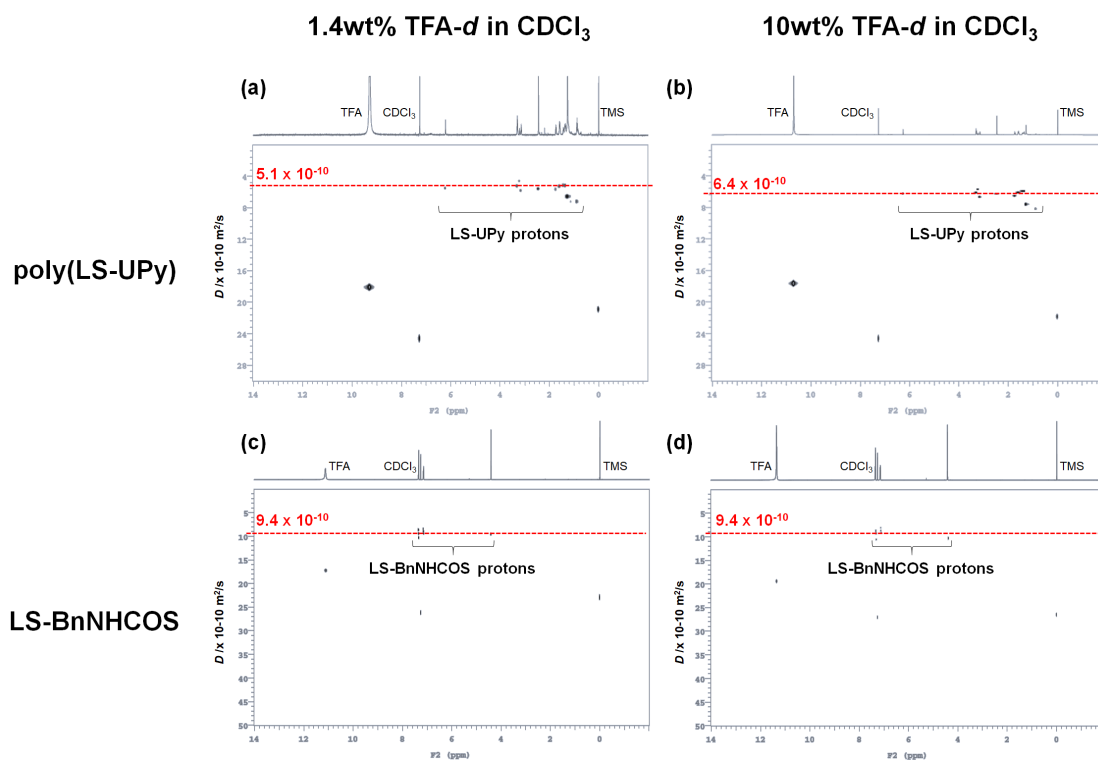


Figure 5. DOSY NMR spectra (600 MHz CDCl₃/TFA-*d*, r.t.) of poly(LS-UPy) (a and b) and LS-BnNHCOS (c and d) in 1.4 wt% (a and c) and 10 wt% (b and d) TFA-*d* in CDCl₃.

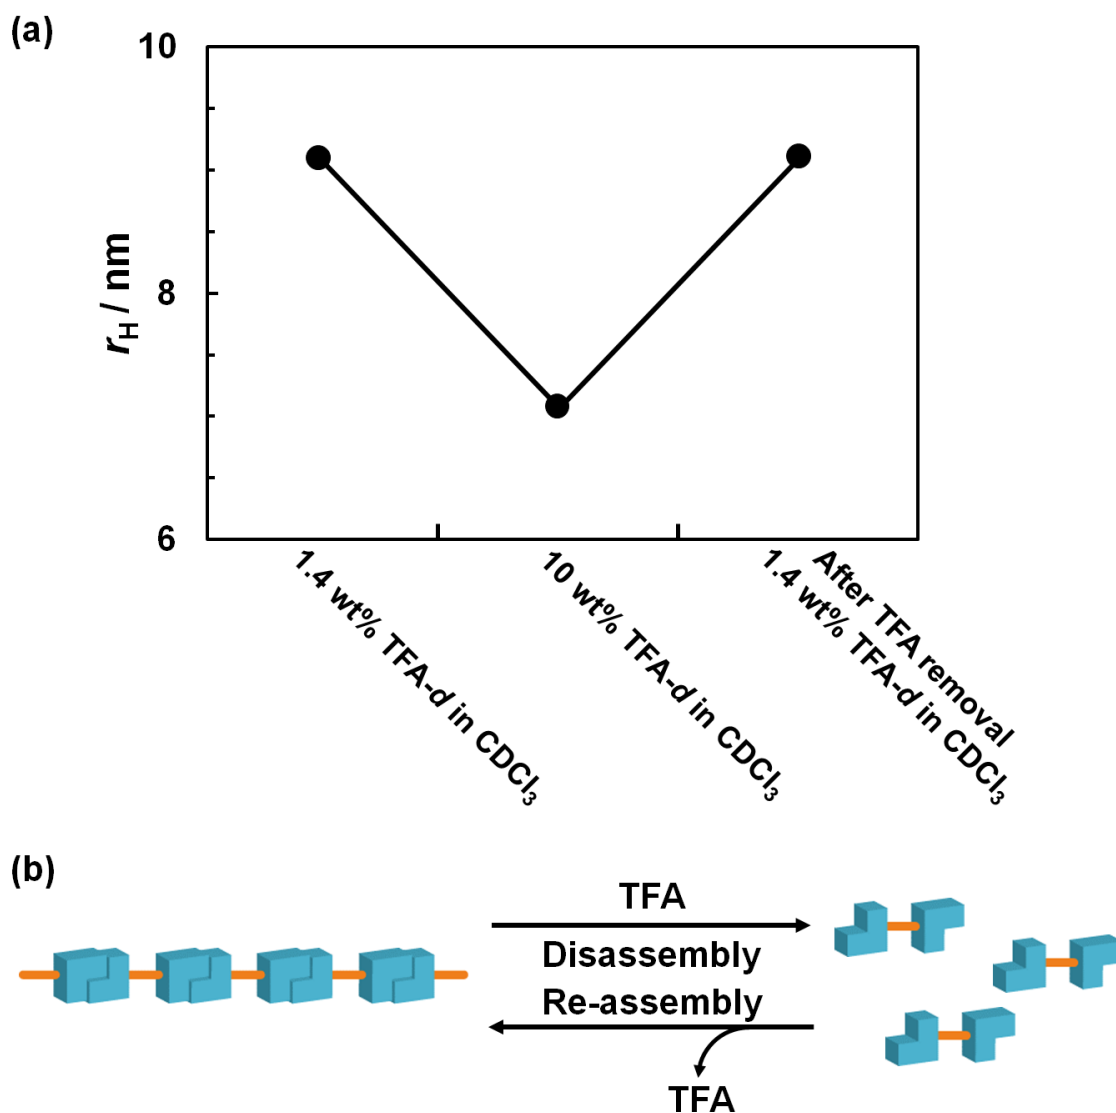


Figure 6. (a) Hydrodynamic radius (r_H) of poly(LS-UPy) in 1.4 wt% and 10 wt% TFA-*d* in $CDCl_3$ and dissolved again in 1.4 wt% TFA-*d* in $CDCl_3$ after removal of TFA. (b) Schematic image of disassembly and re-assembly of poly(LS-UPy).

3. Conclusions

A novel supramolecular sulfur-containing polymer was synthesized by introducing a UPy unit at both ends of linear sulfur-containing compound and linking the UPy units via hydrogen bonding. Disassembly and re-assembly of the supramolecular sulfur-containing polymer were controlled by dissociation and re-formation of UPy units with

the addition and removal of TFA, respectively. The methods presented here should help develop sulfur-containing polymers, which have potential as chemo-responsive materials in the future.

4. Experimental Section

4.1 Materials

All of the reagents and chemicals were obtained from commercial sources, unless otherwise noted. Sulfur was purified by recrystallization from carbon disulfide.

4.2 Measurements

The NMR spectra were acquired using JEOL JNM-ECS 400, 500, and 600 (for DOSY) MHz NMR spectrometers. Chemical shifts in the ^1H and ^{13}C spectra were referenced to tetramethylsilane (TMS) ($\delta = 0.00$ ppm) and CHCl_3 ($\delta = 77.0$ ppm) respectively. Solid-state NMR spectra were recorded using a JEOL JNM-ECZ600R spectrometer (600 MHz). The solid-state NMR experiments were carried out using a commercial JEOL 1.0 mm magic-angle-spinning (MAS) probe with a spinning frequency of 1000 kHz. The solid-state ^1H MAS NMR spectra were recorded with a single pulse excitation, a 90° pulse length of 1.0 μs , and a recycle delay of 5.0 s. All spectra were referenced to solid glycine and were collected at r. t. Fourier transform infrared (FT-IR) spectra were recorded with a JASCO FT/IR 6100 spectrophotometer. The X-ray powder diffraction (XRD) data were collected using a Rigaku MiniFlex600 diffractometer employing $\text{CuK}\alpha$ radiation and samples were measured by using flat-bed sample holder. Gel permeation chromatography (GPC) measurements were performed with in CHCl_3 at 40 $^\circ\text{C}$ with polystyrene columns [TSKgel GMHHR-M \times 2; flow rate = 1.0 mL/min] connected to a Tosoh DP-8020 pump, a CO-8020 column oven, a UV-8020 ultraviolet

detector, and an RI-8020 refractive-index detector.

4.3 Preparation of UPy-NCO

UPy-NCO was synthesized as reported before with the following procedure^[29]: 2-ureido-4-[1H]pyrimidinone (UPy, 5.0 g, 40 mmol) was reacted with hexamethylene diisocyanate (47 g, 0.28 mol) at 100 °C for 16 h under the protection of nitrogen. After hexane was added, the resulting precipitate was filtered and washed with hexane for three times. The white powder was dried under reduced pressure to give the UPy-NCO (yield 89%).

¹H NMR δ (400 MHz, CDCl₃, TMS)/ppm = 13.14 (s, -CCH₃NHC-, 1H), 11.89 (s, -CNHCO-, 1H), 10.21 (t, -CH₂NHCONH-, 1H), 5.84 (s, -CCH₃CHCO-, 1H), 3.29 (m, -NHCH₂CH₂- and -CH₂NCO, 4H), 2.25 (s, -CCH₃, 3H), 1.65 (m, -NHCH₂CH₂- and -CH₂CH₂NCO, 4H), 1.43 (m, -CH₂CH₂CH₂CH₂NCO, 4H).

4.4 Preparation of monomer (LS-UPy monomer)

S₈ (0.38 mg, 1.5 mmol) and Na (83 mg, 3.6 mmol) were added to dry DMAc (30 mL) and stirred at 70 °C for 24 h under a N₂ atmosphere. UPy-NCO (0.94 g, 3.2 mmol) was added to the solution and stirred at 70°C for 24 h under a N₂ atmosphere. Afterward, the solution was cooled to r.t. The resultant precipitate was collected by filtration. Then it was rinsed with water and CHCl₃ four times to remove the residual sulfur, Na, and UPy-NCO. The obtained solid was dried under reduced pressure to give the LS-UPy monomer (yield 40%).

¹H NMR δ (400 MHz, CDCl₃/TFA-*d*, TMS)/ppm = 13.02 (brs, -CCH₃NHC-, 2H), 11.84 (brs, -CNHCO-, 2H), 10.18 (brs, -CH₂NHCONH-, 2H), 9.28 (brs, -CNHC-, 2H), 6.76 (brs, -CH₂NHCOS-, 2H), 6.22 (s, -CCHC-, 2H), 3.36 (m, -NHCH₂CH₂-, 4H), 3.21 (m, -

SCONHCH₂CH₂-, 4H), 2.43 (s, -CCH₃, 6H), 1.61 (m, -CH₂CH₂CH₂CH₂CH₂CH₂-, 8H) 1.38 (m, -CH₂CH₂CH₂CH₂CH₂CH₂-, 8H). Anal. Calcd. for C₂₆H₄₀N₁₀O₆S₂.1: C 47.65, H 6.15, N 21.37, Found: C 47.60, H 6.91, N 21.99.

4.5 Preparation of comparison sample (LS-BnNHCOS)

S₈ (0.12 mg, 0.46 mmol) and sodium sulfate pentahydrate (0.17 mg, 1.0 mmol) were stirred in H₂O (5.0 mL) at r.t. for 24 h. The resultant solution was freeze-dried. The dried sample and benzyl isocyanate (0.12 mg, 1.1 mmol) were stirred in dry DMF (5.0 mL) at r.t. for 12 h under a N₂ atmosphere. The liquid phase was removed, and the obtained solid was purified by silica-gel column chromatography (R_f = 0.74, CH₂Cl₂/MeOH = 90:10) to give LS-BnNHCOS (yield 40%).

¹H NMR δ (500 MHz, CDCl₃, TMS)/ppm = 7.42-7.29 (m, C₆H₆-, 12H), 4.78 & 4.86 (s, -NHCH₂C₆H₆, 4H). Anal. Calcd. for C₁₆H₁₆N₂S: C 63.98, H 5.37, N 9.33, S 10.37, Found: C 64.40, H 4.77, N 9.31, S 11.3.

4.6 Calculation of the hydrodynamic radius from diffusion coefficient

The hydrodynamic radius (*r_H*) of each sample was calculated from the Stokes-Einstein relationship for a sphere with stick boundary conditions:

$$r_H = \frac{k_B T}{6\pi\eta D}$$

where *k_B*, *T*, *η*, and *D* are Boltzmann's constant, temperature (297 K), the solvent viscosity, and the diffusion coefficient, respectively.

4.7 Disassembly and re-assembly of poly(LS-UPy)

Poly(LS-UPy) (1.0 mg) was stirred in 10 wt% TFA-*d* in CDCl₃ (1.0 mL) at r.t. for 24 h to decompose poly(LS-UPy). After removing the solvent, the obtained sample was

dissolved in 1.4 wt% TFA-*d* in CDCl₃ (1.0 mL). The solution was stirred at r.t. for 24 h.

Acknowledgements

This research was funded by JSPS KAKENHI Grant Number 22H02145, 22K19066, and 20K21225. This work was supported by Noguchi institute, Masuya Memorial Basic Research Foundation, Iketani Science and Technology Foundation, Tonen General Sekiyu Research/Development Encouragement & Scholarship Foundation, and Asahi Glass Foundation. We wish to thank Mr. Iijima and Ms Hirai is the member of the Analytical Instrument Facility, Graduate School of Science, Osaka University, for the discussion about elemental analysis data. We wish to thank to Dr. N. Inazumi is the member of the Analytical Instrument Facility, Graduate School of Science, Osaka University, for the discussion about NMR data.

Disclosure statement

No potential conflict of interest was reported by the authors.

References

- [1] Ober JA. Materials Flow of Sulfur. US Geological Survey Open-File Report. 2002;02-298:1-56.
- [2] Jorzak JS, Fettes EM. Polysulfide Liquid Polymers. *Ind Eng Chem.* 1951;43:324-328.
- [3] Kausar A, Zulfiqar S, Sarwar MI. Recent Developments in Sulfur-Containing Polymers. *Polym Rev.* 2014;54:185-267.
- [4] Worthington MJH, Kucera RL, Chalker JM. Green chemistry and polymers made from sulfur. *Green Chem.* 2017;19:2748-2761.
- [5] Manthiram A, Fu YZ, Chung SH, Zu CX, Su YS Rechargeable Lithium-Sulfur Batteries. *Chem Rev.* 2014;114:11751-11787.

- [6] Zhang YY, Glass RS, Char K, Pyun J. Recent Advances in the Polymerization of Elemental Sulphur, Inverse Vulcanization and Methods to Obtain Functional Chalcogenide Hybrid Inorganic/Organic Polymers (CHIPs). *Polym Chem.* 2019;10:4078-4105.
- [7] Dirlam PT, Glass RS, Char K, Pyun J. The Use of Polymers in Li-S Batteries. *J. Polym Sci Part A Polym Chem.* 2017;55:1635–1668.
- [8] Bacon RF, Fanelli R. The Viscosity of Sulfur. *J Am Chem Soc.* 1943;65:639-648.
- [9] Fairbrother F, Gee G, Merrall GT. The Polymerization of Sulfur. *J Polym Sci.* 1955;16:459-469.
- [10] Bartlett PD, Kwart H. Some Inhibitors and Retarders in the Polymerization of Liquid Vinyl Acetate. II. 1,3,5-Trinitrobenzene and Sulfur. *J Am Chem Soc.* 1952;74:3969-3973.
- [11] Currell BR, Williams AJ, Mooney AJ, Nash BJ. Plasticization of Sulfur. *Adv Chem Ser.* 1975;140:1-17.
- [12] Sheydaei M, Kalae MR, Allahbakhsh A, Samar M, Aghili A, Dadgar M, Moosavi GS. Characterization of Synthesized Poly(aryldisulfide) Through Interfacial Polymerization Using Phase-transfer Catalyst. *J Sulfur Chem.* 2012;33:303-311.
- [13] Lundquist NA, Tikoalu AD, Worthington MJH, Shapter R, Tonkin SJ, Stojcevski F, Mann M, Gibson CT, Gascooke JR. Reactive Compression Molding Post-Inverse Vulcanization: A Method to Assemble, Recycle, and Repurpose Sulfur Polymers and Composites. *Chem Eur J.* 2020;26:10035-10044.
- [14] Herrera C, Ysinga KJ, Jenkins CL. Polysulfides Synthesized from Renewable Garlic Components and Repurposed Sulfur Form Environmentally Friendly Adhesives. *ACS Appl Mater Interfaces.* 2019;11:35312–35318.
- [15] Yan P, Zhao W, Zhang B, Jiang L, Petcher S, Smith JA, Parker DJ, Cooper AI, Lei J, Hasell T. Inverse Vulcanized Polymers with Shape Memory, Enhanced Mechanical Properties, and Vitrimer Behavior. *Angew Chem Int Ed.* 2020;59:13371-13378.
- [16] Sheydaei M. Sodium sulfide-based polysulfide polymers: synthesis, cure, thermal and mechanical properties. *J Sulfur Chem.* 2022;43:643-654.
- [17] Jiang Q, Li Y, Zhao X, Xiong P, Yu X, Xu Y, Chen L. Inverse-Vulcanization of Vinyl Functionalized Covalent Organic Frameworks as Efficient Cathode Materials for Li–S Batteries. *J Mater Chem A.* 2018;6:17977-17981.

- [18] Fouquey C, Lehn JM, Levelut AM. Molecular recognition directed self-assembly of supramolecular liquid crystalline polymers from complementary chiral components. *Adv Mater.* 1990;2:254-257.
- [19] Sijbesma RP, Beijer FH, Brunsveld L, Folmer BJB, Hirschberg JHKK, Lange RFM, Lowe JKL, Meijer EW. Reversible Polymers Formed from Self-Complementary Monomers using Quadruple Hydrogen Bonding. *Science.* 1997;278:1601-1604.
- [20] Brunsveld L, Folmer BJB, Meijer EW, Sijbesma RP. Supramolecular Polymers. *Chem Rev.* 2001;101:4071-4097.
- [21] Aida T, Meijer EW, Stupp SI. Functional Supramolecular Polymers. *Science.* 2012;335:813.
- [22] Wojtecki RJ, Meador MA, Rowan SJ. Using the Dynamic Bond to Access Macroscopically Responsive Structurally Dynamic Polymers. *Nat Mater.* 2011;10:14-27.
- [23] Harada A. *Supramolecular Polymer Chemistry.* Wiley-VCH. Weinheim. 2012.
- [24] Yan X, Wang F, Zheng B, Huang F. Stimuli-Responsive Supramolecular Polymeric Materials. *Chem Soc Rev.* 2012;41:6042-6065.
- [25] Wei Z, Yang JH, Zhou JX, Xu F, Zrinyi M, Dussault PH, Osada Y, Chen YM. Self-Healing Gels Based on Constitutional Dynamic Chemistry and Their Potential Applications. *Chem Soc Rev.* 2014;43:8114-8131.
- [26] Kobayashi Y. Precise Synthesis of Polyrotaxane and Preparation of Supramolecular Materials Based on Its Mobility. *Polym J.* 2021;53:505-513.
- [27] Kobayashi Y, Harada A, Yamaguchi H, Supramolecular Complex Formation of Polysulfide Polymers and Cyclodextrins. *Chem Commun.* 2020;56:13619-13622.
- [28] Yamagishi Y, Kobayashi Y, Horiguchi A, Kitano D, Yamaguchi H. Supramolecular polysulfide polymers with metal-ligand interactions. *ChemistrySelect.* 2022;7:e202103991.
- [29] Folmer BJB, Sijbesma RP, Versteegen RM, Rijt JAJ, Meijer EW. Supramolecular Polymer Materials: Chain Extension of Telechelic Polymers Using a Reactive Hydrogen-Bonding Synthone. *Adv Mater.* 2000;12:874-878.
- [30] Qin B, Zhang S, Huang Z, Xu JF, Zhang X. Supramolecular Interfacial Polymerization of Miscible Monomers: Fabricating Supramolecular Polymers with Tailor-Made Structures. *Macromolecules.* 2018;51:1620-1625.

[31] Chang YT, Li X, Yu J, Carri GA, Moorefield CN, Newkome GR, Wesdemiotis C.
Design, Synthesis, and Traveling Wave Ion Mobility Mass Spectrometry
Characterization of Iron(II)- and Ruthenium(II)-Terpyridine Metallomacrocycles. *J*
Am Chem Soc. 2011;133:11967-11976.